



Improvement of Water Resistance of Hemp Woody Substrates through Deposition of Functionalized Silica Hydrophobic Coating, while Retaining Excellent Moisture Buffering Properties

Yuchao Jiang, M.A. Bourebrab, N. Sid, A. Taylor, F. Collet, S. Pretot, A. Hussain, M. Ansell, M. Lawrence

► To cite this version:

Yuchao Jiang, M.A. Bourebrab, N. Sid, A. Taylor, F. Collet, et al.. Improvement of Water Resistance of Hemp Woody Substrates through Deposition of Functionalized Silica Hydrophobic Coating, while Retaining Excellent Moisture Buffering Properties. ACS Sustainable Chemistry & Engineering, 2018, 6 (8), pp.10151-10161. 10.1021/acssuschemeng.8b01475 . hal-01881086

HAL Id: hal-01881086

<https://univ-rennes.hal.science/hal-01881086>

Submitted on 27 Sep 2018

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Improvement of water resistance of hemp woody substrates through deposition of functionalised silica hydrophobic coating, whilst retaining excellent moisture buffering properties

Yunhong Jiang¹, Marion A. Bourebrab^{2,3}, Nadia Sid⁴, Alan Taylor⁴, Florence Collet⁵, Sylvie Pretot⁵, Atif Hussain¹, Martin Ansell¹, Michael Lawrence¹

1 BRE Centre for Innovative Construction Materials, Department of Architecture and Civil Engineering, University of Bath, BA2 7AY, UK

2 National Structure Integrity Research Centre, Granta Park, Great Abington, Cambridge, CB21 6AL, UK

3 School of Engineering, University of Edinburgh, Edinburgh, EH9 3FB, UK

4 TWI, Granta Park, Great Abington, Cambridge, CB21 6AL, UK

5 Université de Rennes, Laboratoire de Génie Civil et Génie Mécanique, Equipe Matériaux Thermo Rhéologie, IUT Génie Civil 3, rue du Clos Courtel, BP 90422, 35704 Rennes, France

**Corresponding author; e-mail: y.jiang@bath.ac.uk/yunhongjiang@yahoo.com*

Abstract

This paper reports on the development of a novel treatment for hemp shiv that improves resistance to liquid water and protects hemp shiv from bio-degradation without impacting the natural ability of the shiv to buffer moisture vapour. The hydrophobic surface was produced by depositing silica nanoparticles, which were prepared by the functionalisation of silica nanoparticles with hexamethyldisilazane

(HMDS). The surface chemical composition was determined showing replacement of surface silanols on the silica nanoparticles with trimethyl groups. The specific surface area of silica nanoparticles decreased after the trimethylsilyl treatment. The surface modifications reduced the level of hysteresis between absorption and desorption isotherms and also the total amount of moisture absorbed by the silica nanoparticles. The surface of the hemp shiv was initially hydrophilic, but became hydrophobic once the material was treated, demonstrating contact angle with water of 120°. The results show the coating layer of functionalised silica on the hemp shiv reduced water absorption from 400% (untreated shiv) to 250%. However, the moisture buffer value results showed that the coating films do not limit the access of moisture to adjacent pores in the hemp shiv and the functionalised silica coating layer retains the moisture buffering ability of hemp shiv.

Keywords

Hydrophobic coating; Nanostructure; Moisture adsorption; Hexamethyldisilazane; Renewable resources; Moisture buffer value

Introduction

The construction industry, in common with industry in general, now has a much greater awareness of environmental and sustainability issues, and the drive from consumers to reduce the reliance on fossil based materials. Considerable attention has been focused on the utilisation of bio-based materials for construction to offer a number of benefits including thermal¹, hygroscopic² and acoustic³ properties, whilst simultaneously delivering renewable and sustainable solutions to reduce detrimental environmental effects. Apart from timber, other bio-based materials have shown promise as construction materials, including hemp shiv, formed from the core of the hemp plant (*Cannabis Sativa* L.), since it has the ability to naturally regulate the indoor environment through a reduction in humidity variations as the material attracts, holds and releases moisture in response to changes in ambient conditions. This ability is due to the highly porous nature of hemp shiv and its hydrophilic character since it contains up to 44% cellulose^{2, 4-6}. These characteristics mean that hemp shiv is greatly influenced by the environment and is susceptible to decay if exposed to unsuitable environmental conditions. Therefore, it is a crucial step to modify the surface of hemp shiv in order to avoiding the problem of decay and to increase durability without detrimentally affecting the desirable moisture buffering characteristics.

One technique is to coat or chemically modify the hydrophilic surface to render it hydrophobic⁷⁻¹¹. Approaches have been reported in the literature where nanotechnology methods have been employed to prepare multifunctional materials

which are then deposited as coatings on plant materials¹²⁻¹⁴. This usually involves a sol-gel process to create inorganic or inorganic-organic hybrid coatings which can render a (hydrophilic) cellulose based material hydrophobic. Water sorption sites are reduced by blocking the hydroxyl groups of the cell wall through steric or chemical modification¹⁵⁻²⁰. The generic chemical reactions underpinning sol-gel chemistry are well known. In these examples the assumption is that the precursor is an alkoxide, such as a silane. During hydrolysis and condensation reactions, siloxane networks are formed by precursors such as tetraethoxy silane (TEOS). These reactions provide the structural backbone of sol-gel systems. The structural evolution of sol-gel is quite complex. The different chemical paths the materials follow are influenced by acidic or basic catalysis, which has been well described by Bergna²¹. Significant effort has been devoted to preparing organically modified silicate materials with improved hydrophobic properties to modify the hydrophilic character of silica based materials and coatings. Surface modification of silica nanoparticles to achieve hydrophobic behaviour has been widely reported. A common route is to graft trimethyl groups to the surface via silylation reactions that replace the hydrophilic surface silanols²²⁻²³. Applications of sol-gel based materials have been reported to improve water, chemical, fire and weather resistance to wood, and also confer antibacterial properties²⁴⁻²⁷. Liu et al. reported a superhydrophobic coating on the wood surface via a solution-immersion process¹⁵. A sol-gel method using methyltrimethoxysilane and hexadecyltrimethoxysilane was used to add a hydrophobic polysiloxane coating to wood reported by Tshabalala et al²⁸. Tang et al. assembled silica and silver nanoparticles on the surface of wool fabric to produce super-hydrophobic property

1
2
3 and antibacterial activity²⁹. The application of sol-gel based hydrophobic coatings to
4
5 bio-based materials (wood, cotton, etc.) has been discussed in the literature, but there
6
7 is a general lack of information on the effect on the moisture buffering capabilities of
8
9 these materials. However, the application of hydrophobic Carnauba wax particles as
10
11 a non-continuous coating was reported to maintain the moisture buffering efficiency
12
13 of wood by Lozhechnikova et al³⁰⁻³¹.
14
15
16
17
18

19 The aim of this work was to develop a modification technique that increases the
20
21 resistance of hemp shiv to liquid water while improving the chemical compatibility
22
23 of the hemp shiv with the binder without reducing the natural ability of hemp shiv
24
25 to buffer moisture vapour. This is because the presence of natural sugars on the
26
27 hemp shiv surface inhibit the setting of hydraulic binders. As a first step SiO₂
28
29 nanoparticles were prepared using the Stöber method. These colloidal dispersions of
30
31 silica in alcohol were then functionalised to give hydrophobic behaviour. The hemp
32
33 shiv were then immersed in the suspension of functionalised silica particles,
34
35 withdrawn and then dried to leave a thin film of the particles on the shiv. The
36
37 hydrophobicity and moisture buffer properties of the treated hemp shiv were
38
39 studied by sessile drop analysis and the Nordtest test³².
40
41
42
43
44
45
46

47 **Experimental**
48

49 **Materials**
50

51 The synthesis of silica nanoparticles was carried out by using tetraethoxysilane
52
53 (TEOS) (Silanes & Silicones, Stockport, UK) as precursor, ammonia, industrial
54
55
56
57
58
59
60

1
2
3 methylated spirit (IMS, 99% ethanol, 1% methanol) (Sigma-Aldrich, Gillingham, UK),
4
5 and water which was deionised in-house. The functionalising agent,
6
7 hexamethyldisilazane, was also purchased from Silanes & Silicones. The hemp shiv
8
9 were provided by Cavac Biomateriaux (Cavac, Sainte-Gemme-La-Plaine, France).
10
11 The chemical and physical characteristics of the hemp shiv materials used are as
12
13 reported by Jiang et al³³.
14
15
16
17
18

19 Synthesis and modification of SiO₂ NPs

20
21 The Stöber process was followed in order to synthesise silica nanoparticles, at room
22
23 temperature³⁴. First, a solution containing appropriate quantities of IMS, ammonia
24
25 and deionised water was stirred for 5 minutes to ensure complete mixing. Separately
26
27 the TEOS was mixed with IMS and the mixture was then added to the first solution.
28
29 The reaction proceeded at ambient temperature for 48 h according to concentrations
30
31 of reactants, similarly to the protocol followed by Bourebrab et al.¹⁹. The formulation
32
33 reached 4.3wt% silica on completion of the reaction. The silica nanoparticles are
34
35 referred to as TSS4.
36
37
38
39
40
41

42 To functionalise the silica a reaction with hexamethyldisilazane was undertaken in
43
44 the parent suspension by heating at 65 °C for 18 h so that the silanols present on the
45
46 surface of the silica nanoparticles would react with the silazane by condensation. The
47
48 functionalised silica is referred to as TSS4T1.
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

To prepare for the hydrophobic treatment of the hemp shiv, the hemp shiv was oven dried at 90°C for one hour prior to coating. The shiv was then immersed in the TSS4T1 aqueous suspension for 1 min with constant mixing. The coated hemp shiv was then shaken to remove any visible liquid which would have remained on the surface of the shiv, and then the bio-materials were oven dried at 90°C for one hour.

Sessile drop assessment

The static sessile drop method was used to determine wetting behaviour of the samples. The materials and methods used are as reported by Bourebrab et al¹⁹. Three to ten droplets of deionised water of approximately 2 µL were placed onto the samples. An image of the droplets was captured after waiting one or two seconds for the drop to reach equilibrium before taking a measurement, thus allowing key dimensions to be measured.

Materials Characterisation

The morphology of the surface coating was characterised using a scanning electron microscope (SEM) (JEOL SEM-6480LV, Tokyo, Japan) and a field emission scanning electron microscope (FE-SEM) (JEOL FESEM6301F). The materials and methods used are as reported by Jiang et al³³. TSS4T1 were also deposited on copper grids for transmission electron microscopy (TEM) (JEOL-2100 Plus) observation, and the accelerating voltage was 200 kV. The thickness of coating layers and the internal surface of hemp shiv were characterised by a dual beam FEI Quanta 3D scanning electron microscope (FIB-SEM) with a platinum deposition. The surface areas and

the pore size distributions of the samples were calculated from nitrogen adsorption-desorption isotherms at 77 K using the BET method (3Flex, UK). Size measurement of the silica particles was performed using dynamic light scattering (DLS) on a Malvern Zetasizer Nano-S (Malvern Instruments, Malvern, UK), at room temperature, via a back-scattering method. FTIR analysis of treated and untreated hemp shiv was carried out by using a PerkinElmer FTIR spectrometer model Frontier. Transmittance spectra were recorded in an Attenuated Total Reflection (ATR) mode and collected with 2 cm^{-1} resolution, and 10 scans were accumulated for each spectrum in the range $4000\text{-}600\text{ cm}^{-1}$. For this analysis the silica suspension was dried, and crushed to break down the aggregates. The same amount of sample was ground with a 1:300 dilution of KBr to produce pellets. Transmittance spectra were recorded in transmission and collected with 2 cm^{-1} resolution, and 10 scans were accumulated for each spectrum in the range $4000\text{-}600\text{ cm}^{-1}$.

Study of adsorption and desorption behaviour of water vapour on TSS4 and TSS4T1

The adsorption and desorption of water vapour were investigated on TSS4 and TSS4T1 using a Surface Measurement Systems dynamic vapour sorption apparatus (DVS, Surface Measurement Systems, UK). The materials and methods used are as reported by Hill et al³⁵.

Water absorption test

The hemp shiv samples were placed in water at room temperature without applying any additional force to immerse them. The hemp shiv pieces floated to the surface as

1
2
3 their density was lower than water. Therefore, the majority of the water absorption
4
5 took place through the capillary behaviour in the hemp shiv samples. The samples
6
7 were taken out of water at specified time intervals, and the mass readings were
8
9 taken within 30 seconds of removal using a balance with an accuracy of ± 0.1 mg.
10
11 Any water visible on the surface of hemp shiv samples was shaken off before the
12
13 measurement. The water absorption was calculated by the mass change (%) between
14
15 the initial mass and the mass after 24 hours of water absorption. The measurements
16
17 were performed in triplicate and the average reading was reported³⁶.
18
19
20
21
22
23

24 **Moisture buffering analysis**

25
26 In order to evaluate the effectiveness of moisture buffering, the Practical Moisture
27
28 Buffer Value (MBV) in $\text{g/m}^2.\%RH$ was calculated. The moisture buffering
29
30 experiments were performed in accordance with the Nordtest method³². MBV
31
32 defines the amount of moisture transported into or out of a material per unit of open
33
34 surface area, during a specified period of time, when the material is exposed to cyclic
35
36 variations in relative humidity (8 hours at 75% RH, followed by 16 hours at 33 %RH).
37
38 Samples were put in watertight cylindrical containers, 10 cm in diameter, open at the
39
40 top. Containers were chosen to be higher than the penetration depth. Full details of
41
42 the materials and methods used are as reported by Collet et al³⁷.
43
44
45
46
47
48

49 **Results and Discussion**

50
51 **Characterisation of the silica NPs and the functionalised silica NPs**
52
53
54
55
56
57
58
59
60

TEM images of the Stöber silica before and after functionalisation are shown in Fig 1. Fig. 1A shows the TSS4 nanoparticles had formed irregular agglomerations. Typically, the size of the TSS4 particle is between 15-30 nm. Fig. 1B shows that the TSS4T1 nanoparticles have a similar particle size to the untreated primary silica nanoparticles (TSS4). No distinct coating layers from the trimethylsilylation were observed on the outside of the TSS4T1 nanoparticles because the silylation will generate a surface assembled monolayer, which is likely to be less than 1 nm. Overall, silica nanoparticles did not exhibit notable changes in appearance after modification. The particles are spheroidal with both major and minor axis diameters in the range of 15-30 nm.

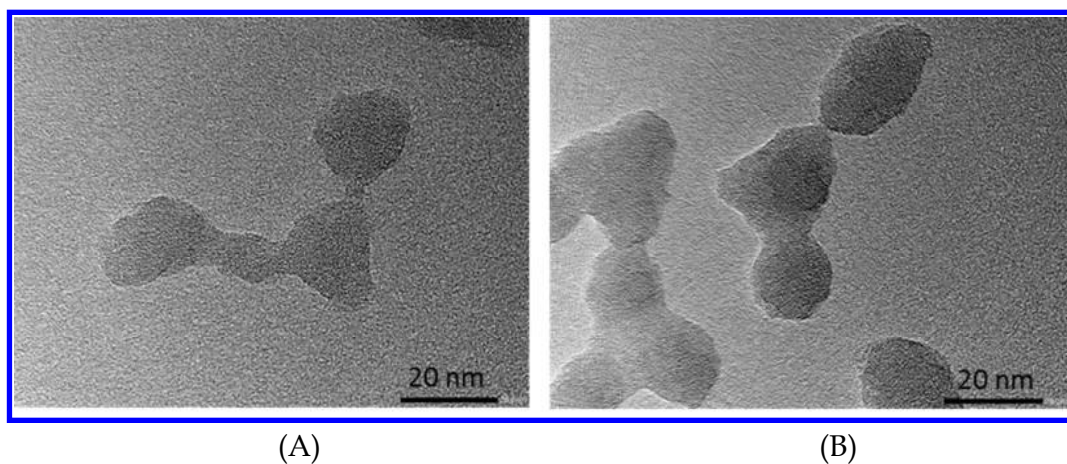


Figure 1: TEM images of the TSS4 (A) and the TSS4T1 (B)

Suspensions of both TSS4 and TSS4T1 nanoparticles were analysed by Dynamic Light Scattering (DLS), in order to provide estimates of their hydrodynamic sizes. The average measured diameters for the TSS4 and TSS4T1 nanoparticles were 22.6 and 20.8 nm, respectively, in Table 1. Fig. 2 also shows that the two suspensions had

similar size distributions. The size distribution of silica nanoparticles shifted to slightly smaller values after surface modification. The corresponding polydispersity indexes (PDI) for DLS measurement are also reported in Table 1. Stetefeld et al reported that a PDI of ~ 0.1 indicates a monodisperse system³⁸. This indicates that both suspensions are not monodispersed and there are some aggregates around a few micrometres present in both suspensions of TSS4 and TSS4T1, as shown in Fig. 2. The TEM diameter of the samples is similar to the size measured by DLS. The inserted images in Fig. 2 show that the TSS4 and TSS4T1 suspensions were transparent with a slightly blue haze due to Rayleigh scattering. No sedimentation of either TSS4 or TSS4T1 suspension was observed after two years, which showed that both suspensions have excellent colloidal stability.

Table 1. The z-average diameters and polydispersity index (PDI) obtained by Zetasizer Nano

Samples	T (°C)	Z-Ave (nm)	Std Dev	PDI	Std Dev
TSS4	25	22.6	± 0.17	0.3	± 0.002
TSS4T1	25	20.8	± 0.39	0.4	± 0.013

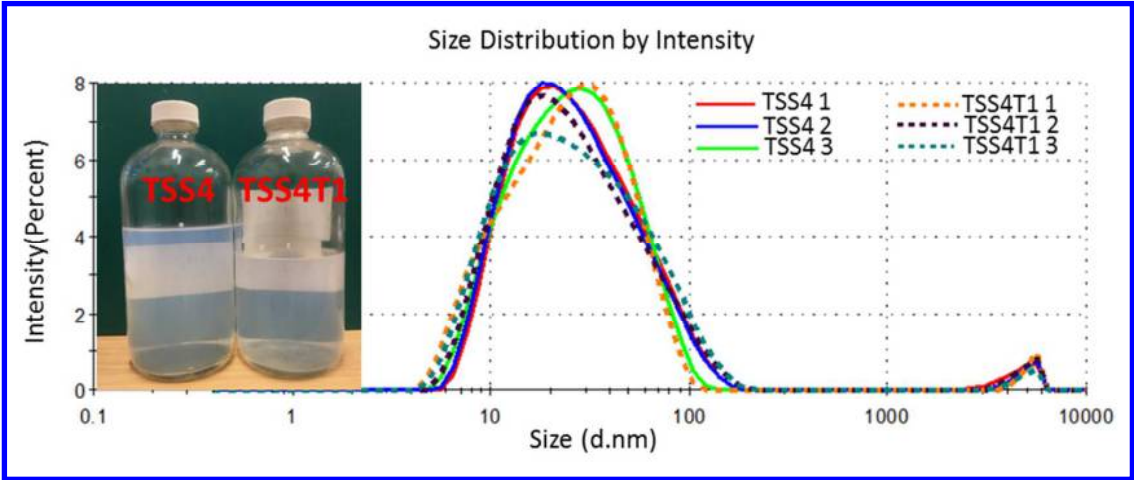


Figure 2: *The intensity size distribution of the silica NPs and the functionalised silica NPs versus particle diameter in nanometres. The different colours represent repeat measurements of the same sample. The inserts are the photo images of the sample suspension.*

The specific surface areas and the parameter C values of the BET equation for TSS4 and TSS4T1 are shown in Fig. 3 and Table 2. They both show typical type IV isotherms according to the IUPAC classification³⁹⁻⁴⁰, which is characteristic of mesoporous materials. Both the values decreased after the surface modification. Since the parameter C is related to the affinity of the solid with the adsorbate (the N₂ molecules) and so to the heat of adsorption. The higher the value of C, the higher the interaction between adsorbate and surface of sample⁴¹. TSS4T1 has a lower value for C (38) in the BET equation and TSS4 has a higher value for C (143), indicating a reduction in the strength of the interaction between the nitrogen molecules and the molecular surface. This can be explained by the ability of the TMS groups to change the silica surface to a nonpolar surface from a polar surface⁴². The pore size distributions of the samples before and after the modification are shown in Fig.3 and Table 2. The increase in pore diameter as a result of the surface modification is 0.74 nm.

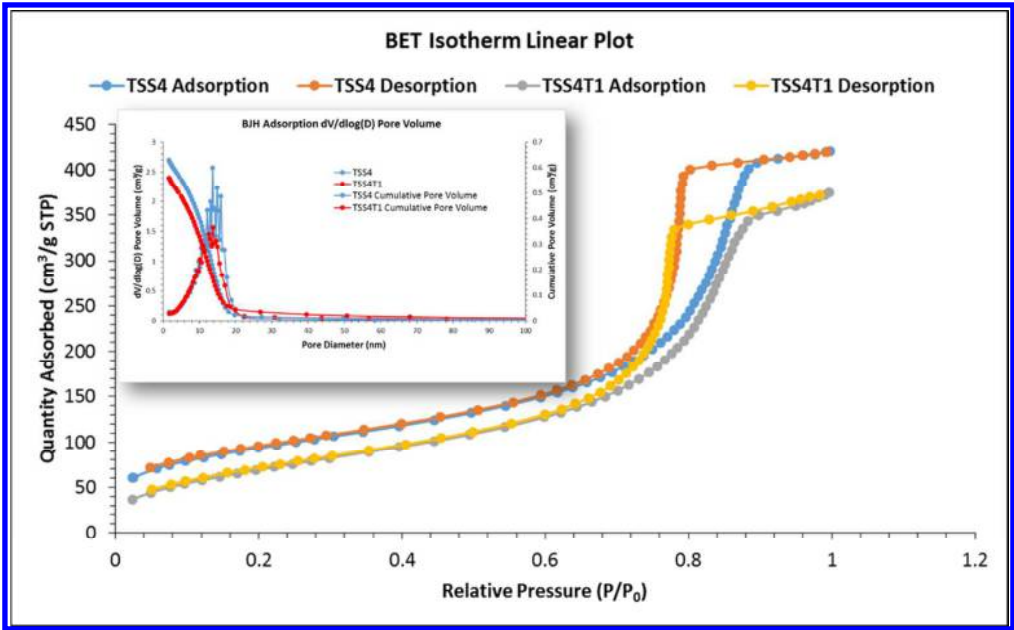


Figure 3: *N*₂ adsorption-desorption isotherms of silica (TSS4) and functionalised silica (TSS4T1). The insert is the BJH pore distribution of both samples.

Table2: Surface structure parameters of TSS4 and TSS4T1

Sample	Surface Area	Pore	C value	Average
	(m ² /g)	Volume		Pore
		(cm ³ /g)		Diameter
				(nm)
TSS4	330.78 ± 2.37	0.647	143.84	7.82
TSS4T1	266.51 ± 1.26	0.571	37.74	8.56

Fig. 4 shows the FTIR spectra of the silica nanoparticles pre- and post-trimethylsilylation to confirm whether the hydrophobic reagent had been grafted on to the surface of the silica nanoparticles. Both spectra have a very strong absorption band at 1064 cm⁻¹ and two medium intensity bands at 963 cm⁻¹ and 795 cm⁻¹ which

are as expected from the silica in the sol-gel process⁴³. The signal at 3448 cm^{-1} is due to free OH group and the signal at 1654 cm^{-1} is due to the antisymmetric vibration of Si-OH. The bending and stretching vibrations of the Si-O-Si bond are represented in the two absorption peaks near 1064 cm^{-1} and 795 cm^{-1} . The absorption peak at 963 cm^{-1} is associated with Si-OH group stretching vibrations. Whilst the FTIR spectra of TSS4 and TSS4T1 exhibit many similarities, two additional absorption peaks appear for TSS4T1, representing the Si-CH₃ stretching and bending vibrations at 845 cm^{-1} and 760 cm^{-1} ⁴⁴⁻⁴⁵. The band intensity of the free hydroxyl band and the hydrogen bonded hydroxyl groups are significantly decreased for the TSS4T1 sample compared with the TSS4 sample. The spectra shown in Fig. 4 demonstrate the successful silylation of the surface of the silica particles

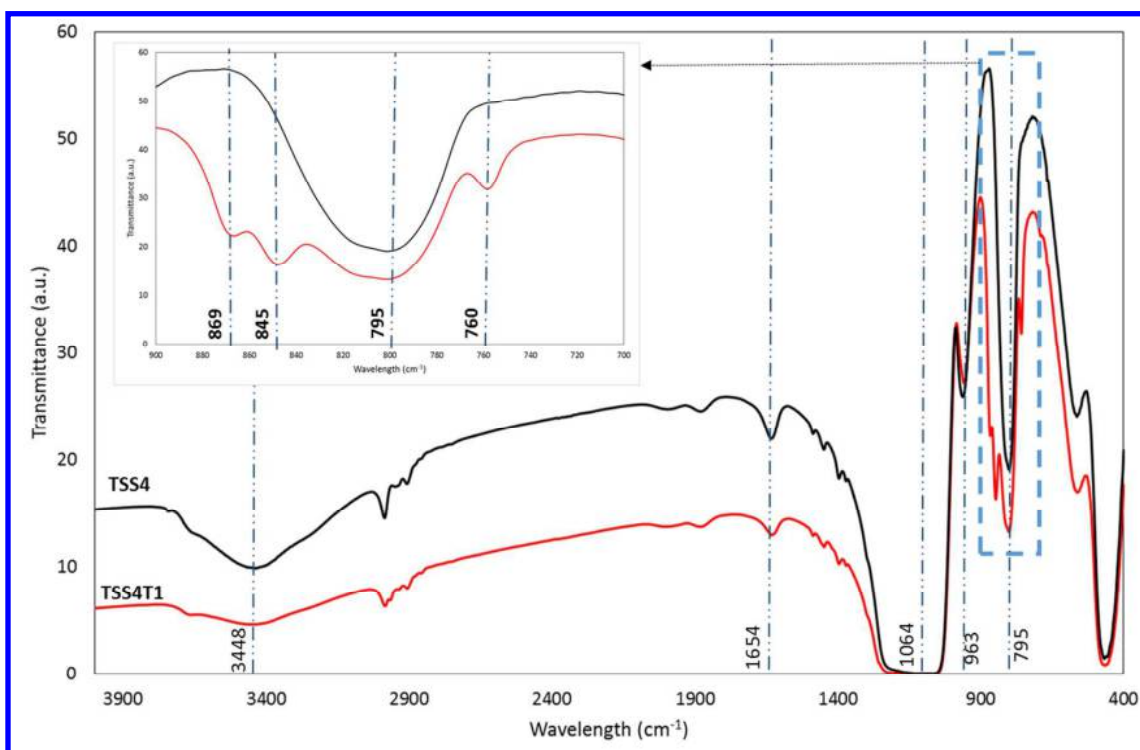


Figure 4: FTIR spectra of TSS4 and TSS4T1 between 4000 and 400 cm^{-1} at room temperature. The insert is the magnified wavelength between 700 cm^{-1} and 900 cm^{-1} .

Water vapour sorption study on TSS4 and TSS4T1

Fig. 5A shows the sorption isotherms of water vapour on TSS4 and TSS4T1 samples. The absolute hysteresis (obtained by subtracting the adsorption from desorption isotherm loop moisture content values) is given in Fig. 5B. The type of water vapour sorption according to the IUPAC classification for TSS4 is a type IV isotherm, whereas it is a type I(b) isotherm for TSS4T1⁴¹. Type I isotherms are seen in microporous solids which have relatively small external surfaces. The classification of Type I isotherms can be categorised further as Type I(a) which represents microporous materials with predominantly narrow micropores less than 1nm wide, and Type I(b) which represents those materials with a larger range of pore sizes from wider micropores to narrow mesopores. Type IV isotherms are typically found in mesoporous adsorbents. In mesopores the adsorption behaviour is driven by the adsorbent-adsorptive interactions and the interactions between molecules when in the condensed state³⁹. In this case, although the TSS4 and TSS4T1 have a similar pore size distribution, the interactions between the adsorbent-adsorptive have been changed due to the presence of TMS group on the surface of TSS4T1. The amount of water vapour adsorbed on the samples at the same relative pressure decreases significantly after surface modification, especially at higher RH levels. There is a significant reduction in hysteresis between TSS4 and TSS4T1 in the upper part of the hygroscopic range. The reduction of water vapour adsorption and hysteresis on the

TSS4T1 sample is attributed to the superficial hydroxyl groups (-OH) being replaced by silazane (Si-N) groups, which is also evident in the FTIR curves (Fig. 4). The water vapour isotherm for the TSS4T1 sample still shows a clear knee at lower RH levels, and therefore does not display the typical type III isotherm characteristics, which would have been expected where water adsorption occurs on a hydrophobic surface⁴². This may be because TSS4T1 has many active sites for water vapour adsorption despite the silylation which is indicative of residual silanols, a finding which is supported by the FTIR analysis. The absence of capillary condensation of water is also of note in the TSS4T1 samples, as can be seen in Fig.5, where the TSS4T1 isotherm shows minimal mass increase and no measurable hysteresis, in contrast to TSS4. The possible reason is that the increased hydrophobicity decreases surface energy of pore walls and thus decreases the tendency for capillary condensation.

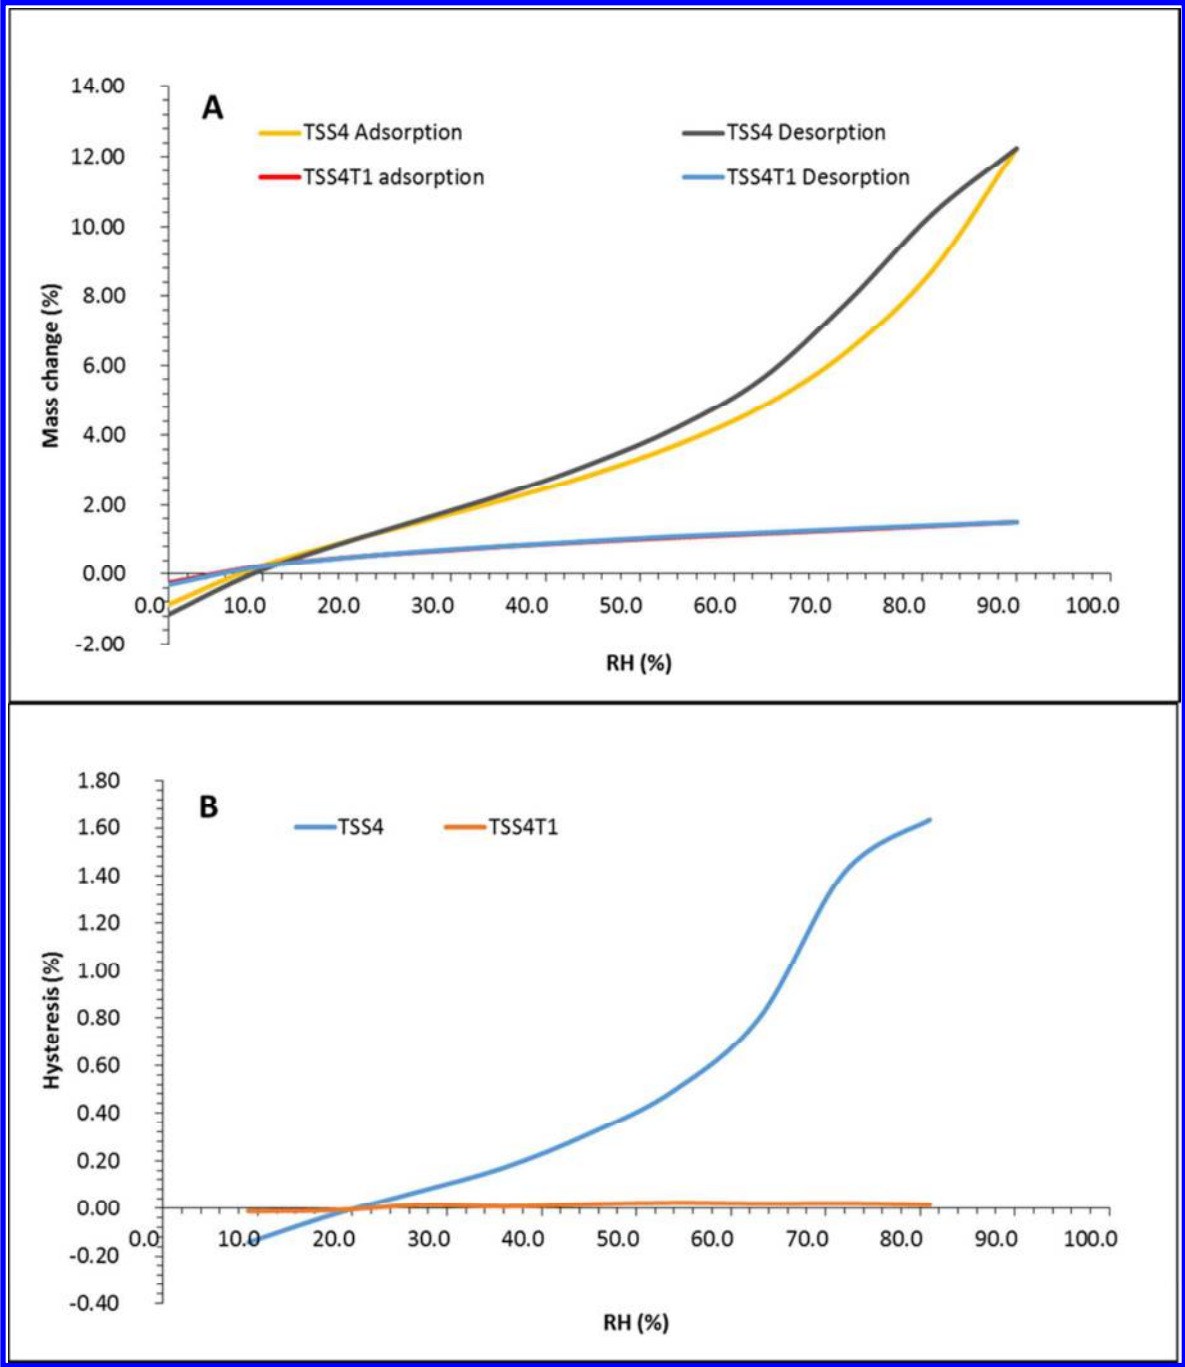


Figure 5: *Water vapour adsorption-desorption isotherms of TSS4 and TSS4T1 (A) and absolute hysteresis plotted as a function of RH.*

Characterisation of the hemp shiv and coated hemp shiv

The surface morphologies of the hemp shiv samples were observed by FESEM. Fig. 6 shows characteristic views of the raw hemp shiv and the dip-coated hemp shiv. The raw hemp shiv shown in Fig. 6, A and B, exhibits a microscale cell structure (pits) with a typically smooth surface. The diameter of pits is around 2 μm . Fig. 6, C and D show even coating layers of TSS4T1, together with some agglomerated nanoparticles. The coating is cracked at the edges of the pits. The coating layers masked the anatomical details, and the pits are in some cases filled in with TSS4T1 but not completely occluded by the particles. The surface of the coating is very rough according to Fig. 6, E and F. These particles arise from the assembly and aggregation of the silica nanoparticles on the surface of the hemp shiv. The particle size of modified silica were around 20 nm according to the TEM data (Fig.1). There are a great number of voids among these silica nanoparticles. The voids serve to create the conditions required for a hydrophobic coating, as they are able to repel water and trap air.

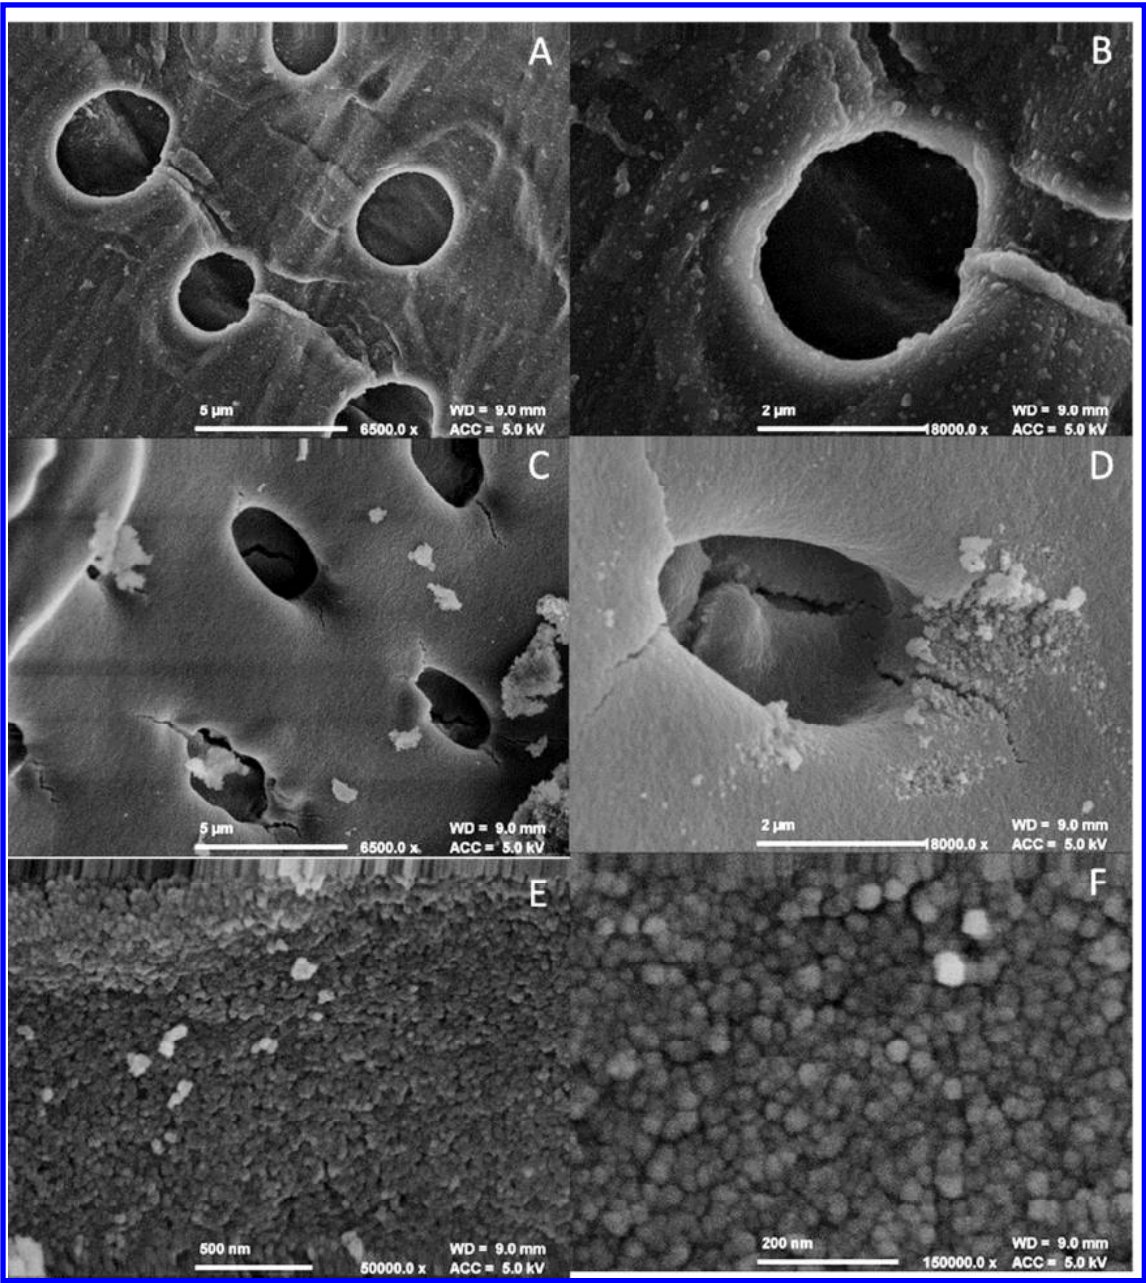


Figure 6: Field emission SEM micrographs of (A) and (B) untreated hemp shiv (C), (D), (E) and (F) dip-coated hemp shiv

Fig.7 shows ‘slice and view’ on dip-coated hemp shiv using the FIB-SEM. Fig. 7A images a 25 μm diameter hole cut using an ion beam. Fig. 7B and 7C reveal the hidden layered structure of the coating layer. The modified silica coated on the

surface of hemp shiv with multiple layers has a thickness between 130 and 160 nm. A sputtered gold coating was also applied to increase electrical conductivity for imaging and platinum deposition for protection of samples is also visible. Fig. 7D shows that the cell lumens were empty, and a thin layer of silica coating with a thickness of 65 nm was observed on the surface of the void cell wall. It indicates that the modified silica not only coated the exterior of the hemp shiv but also penetrated into the hemp shiv and was deposited onto the internal cell walls.

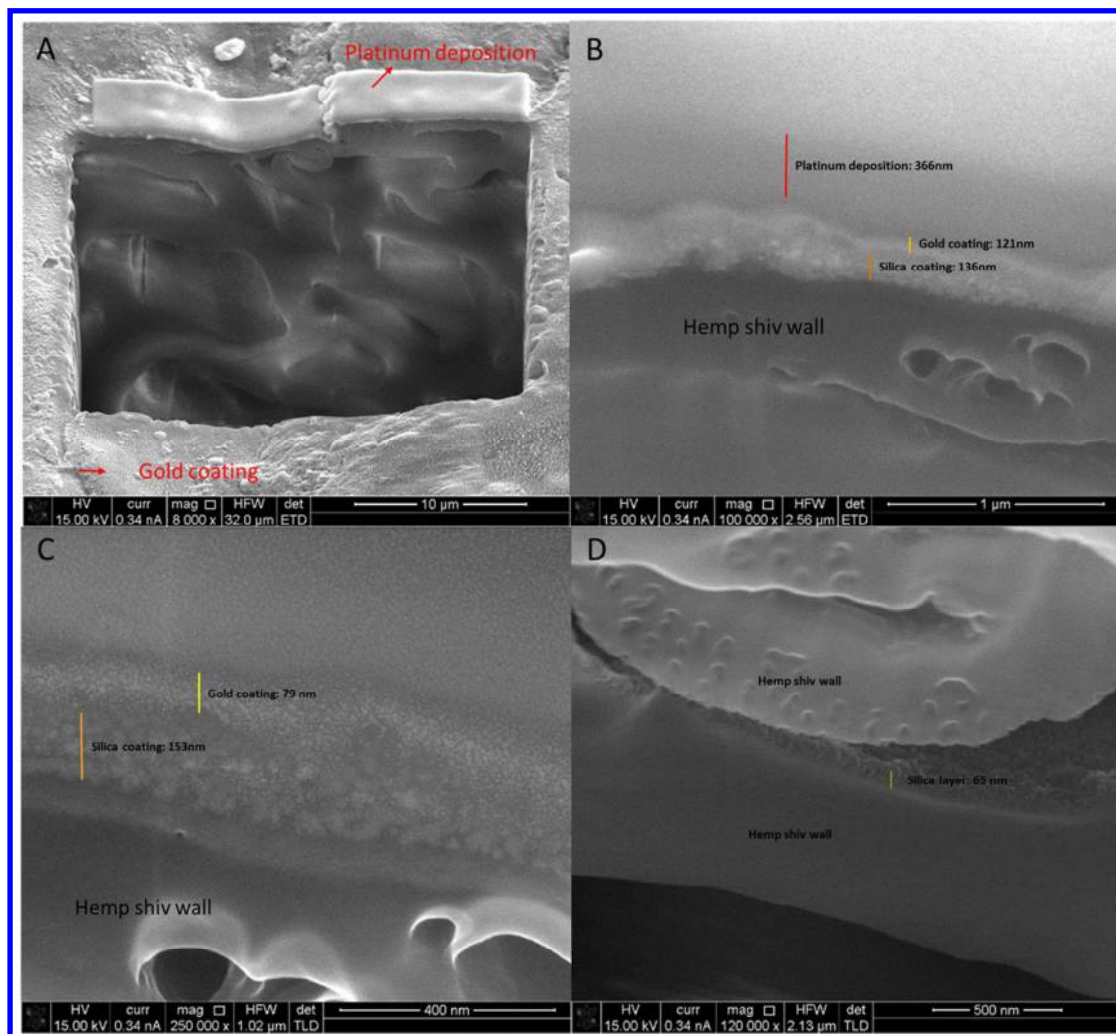


Figure 7: FIBSEM cross-section micrographs of dip-coated hemp shiv. (A) the surface of dip-coated hemp shiv with gold coating and platinum deposition as viewed using a SEM. The dark region in the centre of the image represents a microscopic hole where material has been machined out by a beam of ions. (B) and (C) magnified views of the previous image reveals the hidden layered structure of a coating layer and clear silica and gold nano-films. (D) voids in the hemp shiv are more clearly shown in this cross-sectional image. A very thin coating layer was observed just above the hemp shiv cell wall.

Fig. 8 shows typical FTIR spectra in an ATR mode for the control and coated hemp shiv samples. The chemical composition of hemp shiv is mainly cellulose, hemicellulose and lignin. Fig. 8 shows a raw hemp shiv FTIR spectrum with broad bands at 3448 cm^{-1} (-OH stretch from polysaccharides), 2918 cm^{-1} (-C-H stretch in methyl and methylene groups from polysaccharides), 1733 cm^{-1} (C=O stretch in unconjugated ketone, carbonyl and ester group from hemicellulose), 1605 cm^{-1} (Aromatic vibration, C=O stretch), 1417 cm^{-1} (CH_2 bending, C=C stretching in aromatic group from lignin), 1369 cm^{-1} (CH_2 bonding from polysaccharides), 1319 cm^{-1} (C-H vibration from cellulose) and 1241 cm^{-1} (C= stretch from lignin and xylan). The fingerprint region is dominated by bands at approximately $1050\text{ -}1030\text{ cm}^{-1}$ attributed to C-O deformation from various polysaccharide vibrations⁴⁶⁻⁴⁸. The characteristic peaks of the dip-coated hemp shiv are shown in Fig. 8. It can be seen that the absorption peaks at 795 , 845 , 963 and 1064 cm^{-1} , are in good agreement with the observed absorption peaks from the pure coating material analysed in Fig. 4. As reported in the literature, the peak at 1064 cm^{-1} represented the asymmetric stretching of the oxygen atoms of two adjacent Si-O-Si units. The bending vibrational

mode of Si-O-Si units is seen in the broad peak at 795 cm^{-1} and the presence of Si-OH group stretching vibrations create the peak at 963 cm^{-1} ⁴⁹⁻⁵¹. The band at 3448 cm^{-1} (-OH stretch), seen on the raw shiv, has almost disappeared on the coated shiv. This is attributed to the replacement of the surface OH groups with trimethyl [-(CH₃)₃] groups²². The FTIR data confirms that the functionalised silica NPs coated on hemp shiv significantly alter the surface chemistry.

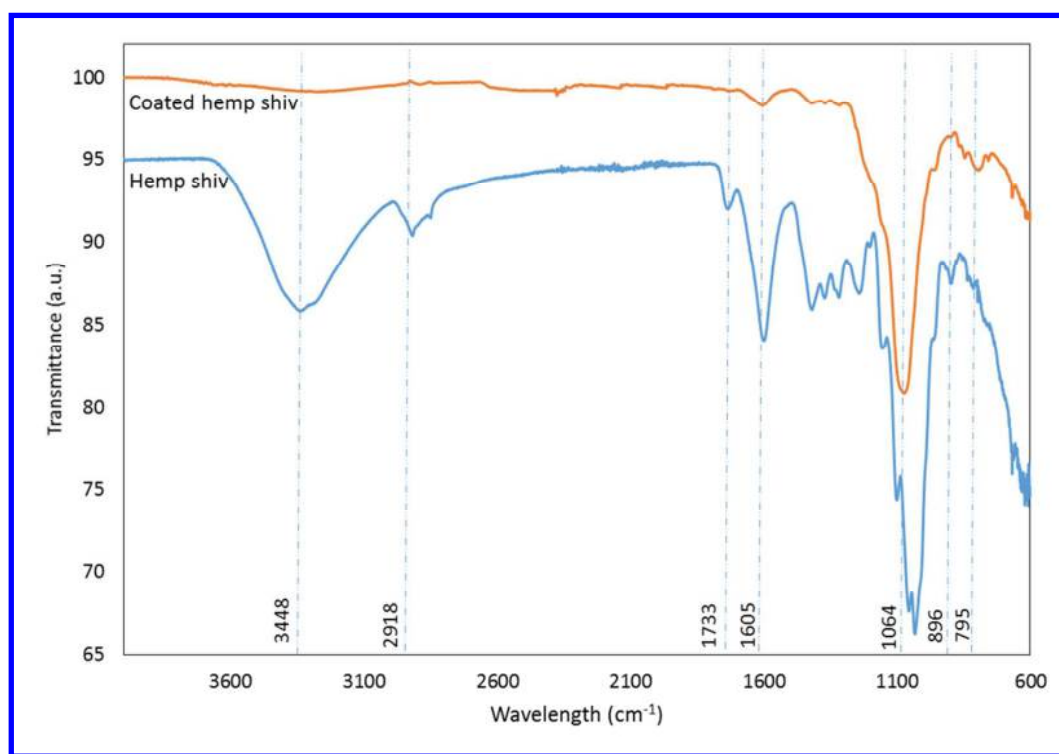


Figure 8: FTIR spectra of the control hemp shiv and the dip-coated hemp shiv

The composition of the untreated and treated hemp shiv was determined by energy dispersive spectroscopy (EDX) analysis. Fig 9A clearly shows the main peaks detected for hemp shiv were carbon and oxygen in the EDX spectrum plus Au peak, from the sputtered coating for SEM preparation, dip-coated hemp shiv also shows a

high silicon content attributable to the TSS4T1 as shown in Fib.9B. By considering the FTIR data in conjunction with the SEM/EDX data, it appears that the modified silica coating is linked to the cell wall. In order to confirm this, further studies utilising solid state nuclear magnetic resonance spectroscopy are required on the link between the silica nanoparticles and cell wall components

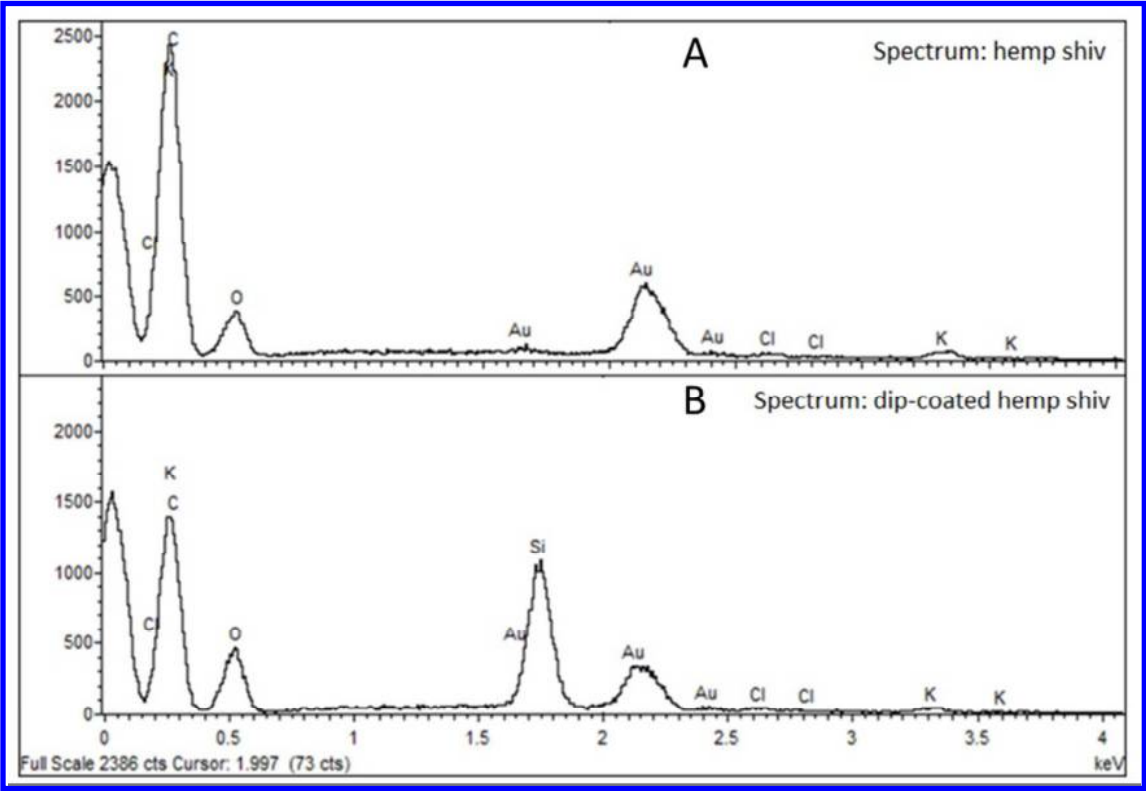


Figure 9: EDX spectra of (A) untreated hemp shiv and (B) dip-coated hemp shiv

Water contact angle and water sorption

In order to identify a change in the surface property of hemp shiv after TSS4T1 coating, the water contact angles of hemp shiv and coated hemp shiv were measured. Fig. 10A shows the hemp shiv has a hydrophilic property with a water contact angle of approximately $65.0^{\circ} \pm 0.9^{\circ}$. When the surface of hemp shiv was changed to be

hydrophobic as a result of treatment with TSS4T1, the water contact angle increased to $120.0^\circ \pm 1.2^\circ$, which is much higher than that of the raw hemp shiv. The readings reported were the average of five measurements. The water contact angle of coated hemp shiv was re-measured after immersing the shiv in DI water for 24 hours with constant stirring in the beaker. The resulting water contact angle of $115.0^\circ \pm 0.8^\circ$ as shown in the supporting document, is only marginally lower than that achieved in the first set of measurements, confirming the robustness of the coating. The equipment used has a reproducibility of $\pm 2^\circ$.

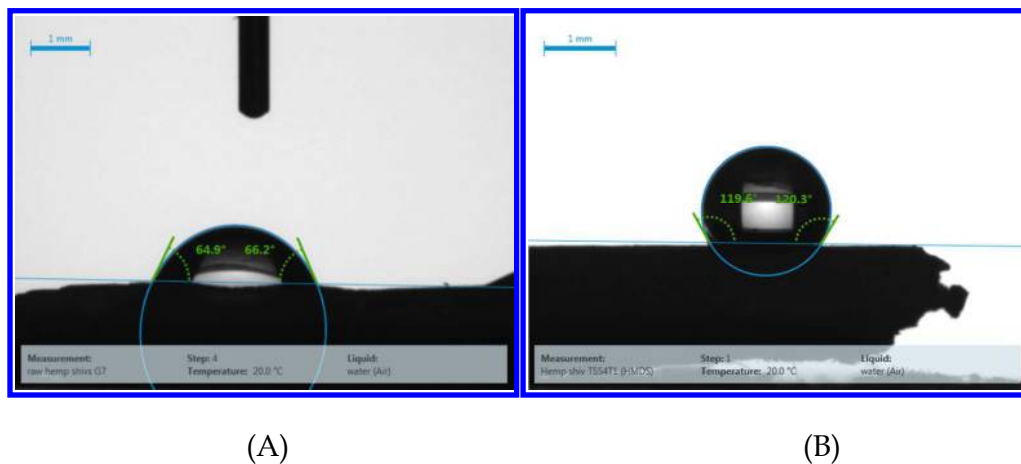


Figure 10: *Water contact angle of raw hemp shiv (A) and coated hemp shiv (B). Note: Image is one of five measurements*

The hydrophobic silica coating acts as a barrier to liquid water to reduce the water sorption. Fig. 11 shows the rate of distilled water absorption for raw hemp shiv and hemp shiv coated with TSS4T1 when held at room temperature over a period of 24 h. The raw hemp shiv had a maximum water absorption of approximately 400% increase in mass, and absorbed more than half of this amount within the first few

minutes of dipping. The highly porous structure and hydrophilic characteristics of hemp shiv are responsible for the water absorption performance. A functionalised silica coating layer on the hemp shiv reduced the water absorption from 400% for the untreated shiv to 250% for the treated shiv, which is 150% less than the uncoated shiv. This reduction in water absorption is due to a large decrease in the absorption of water within the cell walls, with the remaining water being held within the capillaries of the highly open structure. This demonstrates that treating the shiv with functionalised hydrophobic silica provides enhanced water resistance and hence resistance to bio-decay is assumed.

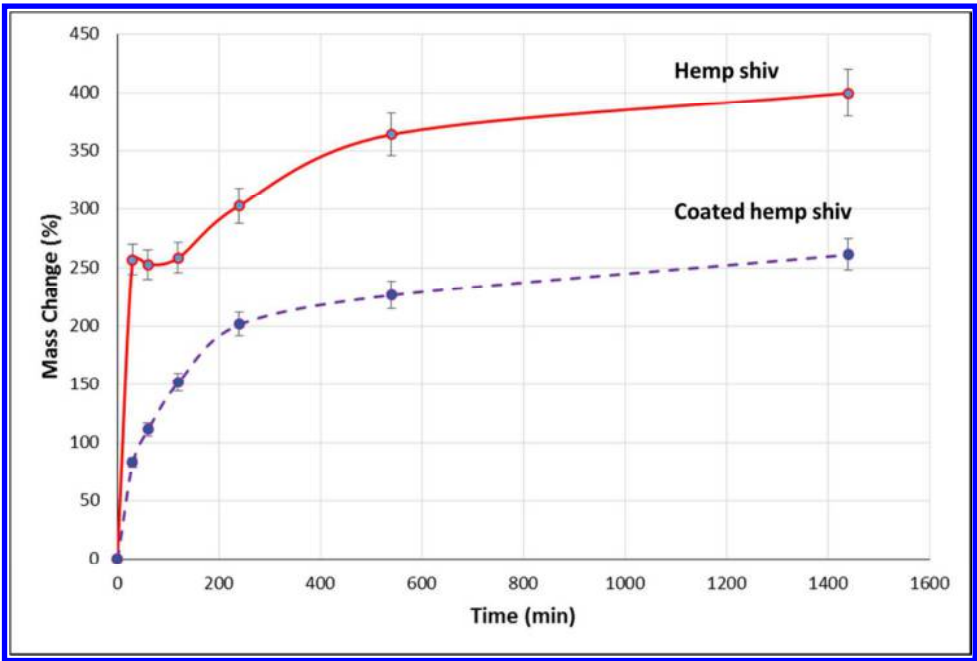


Figure 11. Dependence of water absorption on time for hemp shiv and coated hemp shiv

Moisture sorption analysis

Moisture buffering is an energy-efficient material characteristic which enables the absorption, storage and release of moisture, which in turn can regulate the indoor environment by avoiding extremes of humidity and reducing excessive variations. It is a very important parameter for building materials. The MBV values for the hemp shiv and coated hemp shiv are shown in Fig. 12. The coated hemp shiv shows a MBV value of $2.25 \text{ g}/(\text{m}^2.\%RH)$, while the MBV value of hemp shiv is around $2.07 \text{ g}/(\text{m}^2.\%RH)$. A slight increase of MBV is obtained with the coating. Therefore, according to the Nordtest classification, both untreated and treated hemp shiv exhibit excellent hydric regulation properties, which remain in the level of moisture buffering ($MBV > 2$). The research undertaken by Lozhechnikova et al. has shown that the use of wax particles can preserve moisture buffering ability, and may even deliver improvements, describing an example where the MBV was increased to 1.08 and 1.09 on the radial and tangential surfaces respectively, whereas solid wax films are seen to reduce the moisture buffering ability to limited levels ($0.2 < MBV < 0.5$) or even less³⁰. In addition, Lozhechnikova et al. also reported CA values around 160 degrees and MBV around 1.4 using wax particles with layer-by-layer deposition³¹. From these data, it can be seen that particles of functionalised silica or wax offer substantial improvements in the preservation of the efficiency of wood as a natural moisture buffering material when compared to the performances offered by a continuous wax layer. Similarly, commercial treatments such as linseed oil coating and lacquer coating were also found to decrease moisture buffering to moderate or limited levels. The hydrophobic coatings form an impermeable barrier on the hemp shiv that water droplets cannot penetrate. The noticeable advantage of

the functionalised silica NPs or wax particles is that they are too small to block the primary pores found in the hemp shiv, therefore water vapour can permeate freely, thus allowing the excellent moisture buffering properties of the underlying material to be retained.

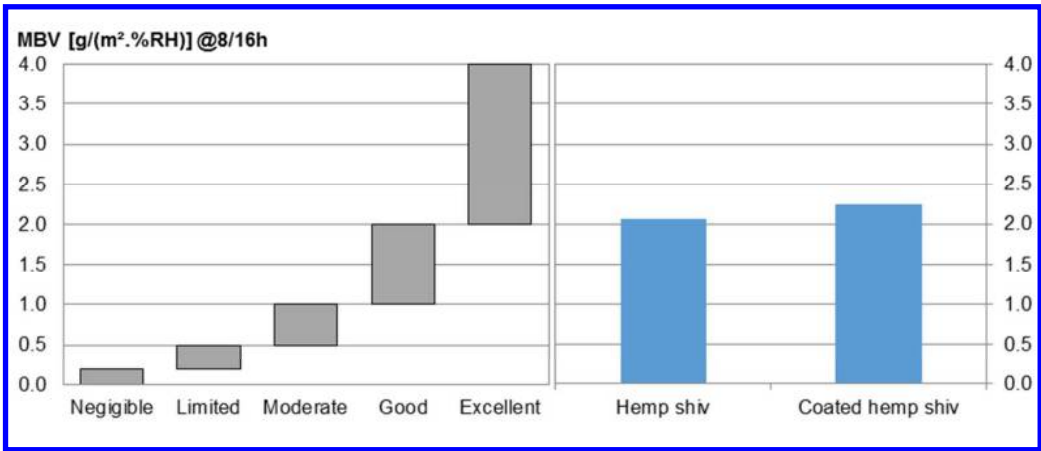


Figure 12: Practical moisture buffer value classes and moisture buffer values of hemp shiv and coated hemp shiv

Conclusions

In conclusion, this work has shown that a simple dip-coating method can create a coating of functionalised silica nanoparticles which enables the fabrication of hydrophobic hemp shiv. Uniform and multiple layers of silica coating were achieved on the surface of both external and internal voids of hemp shiv by using a dip-coating method. FTIR analysis showed that trimethylsilyl groups were introduced onto the surface of silica nanoparticles and replaced the hydroxyl groups (-OH). The specific surface areas of silica NPs decreased after modification by HMDS. The surface modification decreased the moisture adsorption content and reduced the

level of hysteresis shown between the isotherms for adsorption and desorption. In addition, the results revealed that the functionalised silica nanoparticles were deposited uniformly over the hemp shiv surface with multiple layers. The initially hydrophilic hemp surface was made hydrophobic with the silica treatment, and exhibited a water contact angle of 120° or higher. The functionalised silica coating deposited on the hemp shiv surface led to a reduction in water absorption of 150% of the mass of the hemp shiv (from 400% for the untreated shiv to 250% for the treated shiv) whilst still retaining excellent moisture buffering properties of the hemp shiv.

Competing interest

We declare we have no competing interests.

Acknowledgements

The work presented here was carried out under the ISOBIO project, which has received funding from the European Union's Horizon 2020 research and innovation programme, under grant agreement No. 636835.

Supporting Information

Durability test of silica-coating on the hemp shiv

References

1. Collet, F.; Pretot, S., Thermal conductivity of hemp concretes: Variation with formulation, density and water content. *Construction and Building Materials* **2014**, *65*, 612-619, DOI 10.1016/j.conbuildmat.2014.05.039.


2. Lawrence, M.; Fodde, E.; Paine, K.; Walker, P. In *Hygrothermal Performance of an Experimental Hemp-Lime Building*, Key Engineering Materials, Trans Tech Publ: **2012**; pp 413-421, DOI 10.1016/j.conbuildmat.2012.04.123.
3. Kinnane, O.; Reilly, A.; Grimes, J.; Pavia, S.; Walker, R., Acoustic absorption of hemp-lime construction. *Construction and Building Materials* **2016**, 122 (Supplement C), 674-682, DOI 10.1016/j.conbuildmat.2016.06.106.
4. Latif, E.; Tucker, S.; Ciupala, M. A.; Wijeyesekera, D. C.; Newport, D., Hygric properties of hemp bio-insulations with differing compositions. *Construction and Building Materials* **2014**, 66, 702-711, DOI 10.1016/j.conbuildmat.2014.06.021.
5. Collet, F.; Pretot, S., Experimental highlight of hygrothermal phenomena in hemp concrete wall. *Building and Environment* **2014**, 82, 459-466, DOI 10.1016/j.buildenv.2014.09.018.
6. Collet, F.; Chamoin, J.; Pretot, S.; Lanos, C., Comparison of the hygric behaviour of three hemp concretes. *Energy and Buildings* **2013**, 62, 294-303, DOI 10.1016/j.enbuild.2013.03.010.
7. Celia, E.; Darmanin, T.; Taffin de Givenchy, E.; Amigoni, S.; Guittard, F., Recent advances in designing superhydrophobic surfaces. *Journal of Colloid and Interface Science* **2013**, 402, 1-18, DOI 10.1016/j.jcis.2013.03.041.
8. Bellanger, H.; Darmanin, T.; Taffin de Givenchy, E.; Guittard, F., Chemical and Physical Pathways for the Preparation of Superoleophobic Surfaces and Related Wetting Theories. *Chemical Reviews* **2014**, 114 (5), 2694-2716, DOI 10.1021/cr400169m.
9. Gao, J.; Huang, X.; Xue, H.; Tang, L.; Li, R. K. Y., Facile preparation of hybrid microspheres for super-hydrophobic coating and oil-water separation. *Chemical Engineering Journal* **2017**, 326 (Supplement C), 443-453, DOI 10.1016/j.cej.2017.05.175.
10. Maleki, H., Recent advances in aerogels for environmental remediation applications: A review. *Chemical Engineering Journal* **2016**, 300 (Supplement C), 98-118, DOI 10.1016/j.cej.2016.04.098.
11. Saha, P.; Chowdhury, S.; Manna, S.; Roy, D.; Adhikari, B.; Thomas, S., New Biobased Surface Treatment to Improve Strength and Durability of Bombax ceiba. **2016**, 4 (1), 76-84, DOI 10.1021/acssuschemeng.5b01057.
12. Chang, H.; Tu, K.; Wang, X.; Liu, J., Facile Preparation of Stable Superhydrophobic Coatings on Wood Surfaces using Silica-Polymer Nanocomposites. *BioResources* **2015**, 10 (2), 2585-2596, DOI 10.15376/biores.10.2.2585-2596.
13. Lee, J. H.; Kim, D. H.; Han, S. W.; Kim, B. R.; Park, E. J.; Jeong, M.-G.; Kim, J. H.; Kim, Y. D., Fabrication of superhydrophobic fibre and its application to selective oil spill removal. *Chemical Engineering Journal* **2016**, 289 (Supplement C), 1-6, DOI 10.1016/j.cej.2015.12.026.
14. Li, C.; Sun, Y.; Cheng, M.; Sun, S.; Hu, S., Fabrication and characterization of a TiO₂/polysiloxane resin composite coating with full-thickness super-hydrophobicity. *Chemical Engineering Journal* **2018**, 333 (Supplement C), 361-369, DOI 10.1016/j.cej.2017.09.165.
15. Liu, C.; Wang, S.; Shi, J.; Wang, C., Fabrication of superhydrophobic wood surfaces via a solution-immersion process. *Applied Surface Science* **2011**, 258 (2), 761-765, DOI 10.1016/j.apsusc.2011.08.077.
16. Lu, Y.; Feng, M.; Zhan, H., Preparation of SiO₂-wood composites by an ultrasonic-assisted sol-gel technique. *Cellulose* **2014**, 21 (6), 4393-4403, DOI 10.1007/s10570-014-0437-6.
17. Nadargi, D. Y.; Gurav, J. L.; El Hawi, N.; Rao, A. V.; Koebel, M., Synthesis and characterization of transparent hydrophobic silica thin films by single step sol-gel process and dip coating. *Journal of Alloys and Compounds* **2010**, 496 (1-2), 436-441, DOI 10.1016/j.jallcom.2010.01.157.
18. Peng, Y.-T.; Lo, K.-F.; Juang, Y.-J., Constructing a Superhydrophobic Surface on Polydimethylsiloxane via Spin Coating and Vapor-Liquid Sol-Gel Process. *Langmuir* **2010**, 26 (7), 5167-5171, DOI 10.1021/la903646h@proofing.
19. Bourebrab, M.; Durand, G.; Taylor, A., Development of Highly Repellent Silica Particles for Protection of Hemp Shiv Used as Insulation Materials. *Materials* **2018**, 11 (1), 4, DOI 10.3390/ma11010004.

20. Hussain, A.; Calabria-Holley, J.; Schorr, D.; Jiang, Y.; Lawrence, M.; Blanchet, P., Hydrophobicity of hemp shiv treated with sol-gel coatings. *Applied Surface Science* **2018**, *434*, 850-860, DOI 10.1016/j.apsusc.2017.10.210.
21. Bergna, H. E., *The Colloid Chemistry of Silica*. American Chemical Society: 1994; Vol. 234, p 724, DOI 10.1021/ba-1994-0234.
22. Suratwala, T. I.; Hanna, M. L.; Miller, E. L.; Whitman, P. K.; Thomas, I. M.; Ehrmann, P. R.; Maxwell, R. S.; Burnham, A. K., Surface chemistry and trimethylsilyl functionalization of Stöber silica sols. *Journal of Non-Crystalline Solids* **2003**, *316* (2), 349-363, DOI 10.1016/S0022-3093(02)01629-0.
23. PHILIPAVIČIUS, J.; Kazadojev, I.; Beganskiene, A.; A., M.; Sirutkaitis V. Kareiva, A., Hydrophobic Antireflective Silica Coatings via Sol-gel Process. *Materials Science* **2008**, *14* (4), 283-287.
24. Qiu, X.; Li, Z.; Li, X.; Zhang, Z., Flame retardant coatings prepared using layer by layer assembly: A review. *Chemical Engineering Journal* **2018**, *334* (Supplement C), 108-122, DOI 10.1016/j.cej.2017.09.194.
25. Machovsky, M.; Kuritka, I.; Bazant, P.; Vesela, D.; Saha, P., Antibacterial performance of ZnO-based fillers with mesoscale structured morphology in model medical PVC composites. *Materials Science and Engineering: C* **2014**, *41*, 70-77, DOI 10.1016/j.msec.2014.04.034.
26. Rassam, G.; Abdi, Y.; Abdi, A., Deposition of TiO₂ nano-particles on wood surfaces for UV and moisture protection. *Journal of Experimental Nanoscience* **2012**, *7* (4), 468-476, DOI 10.1080/17458080.2010.538086.
27. Graziola, F.; Girardi, F.; Di Maggio, R.; Callone, E.; Miorin, E.; Negri, M.; Müller, K.; Gross, S., Three-components organic-inorganic hybrid materials as protective coatings for wood: Optimisation, synthesis, and characterisation. *Progress in Organic Coatings* **2012**, *74* (3), 479-490, DOI 10.1016/j.porgcoat.2012.01.013.
28. Tshabalala, M. A.; Kingshott, P.; VanLandingham, M. R.; Plackett, D., Surface chemistry and moisture sorption properties of wood coated with multifunctional alkoxysilanes by sol-gel process. *Journal of Applied Polymer Science* **2003**, *88* (12), 2828-2841, DOI 10.1002/app.12142.
29. Tang, B.; Wang, J.; Xu, S.; Afrin, T.; Tao, J.; Xu, W.; Sun, L.; Wang, X., Function improvement of wool fabric based on surface assembly of silica and silver nanoparticles. *Chemical Engineering Journal* **2012**, *185-186* (Supplement C), 366-373, DOI 10.1016/j.cej.2012.01.082.
30. Lozhechnikova, A.; Vahtikari, K.; Hughes, M.; Österberg, M., Toward energy efficiency through an optimized use of wood: The development of natural hydrophobic coatings that retain moisture-buffering ability. *Energy and Buildings* **2015**, *105* (Supplement C), 37-42, DOI 10.1016/j.enbuild.2015.07.052.
31. Lozhechnikova, A.; Bellanger, H.; Michen, B.; Burgert, I.; Österberg, M., Surfactant-free carnauba wax dispersion and its use for layer-by-layer assembled protective surface coatings on wood. *Applied Surface Science* **2017**, *396*, 1273-1281, DOI 10.1016/j.apsusc.2016.11.132.
32. Rode, C., Moisture buffering of building materials. *Department of Civil Engineering, Technical University of Denmark BYG DTU-126 Report* **2005**.
33. Jiang, Y.; Lawrence, M.; Ansell, M. P.; Hussain, A., Cell wall microstructure, pore size distribution and absolute density of hemp shiv. *Royal Society Open Science* **2018**, *5* (4), DOI 10.1098/rsos.171945.
34. Stöber, W.; Fink, A.; Bohn, E., Controlled growth of monodisperse silica spheres in the micron size range. *Journal of Colloid and Interface Science* **1968**, *26* (1), 62-69, DOI 10.1016/0021-9797(68)90272-5.
35. S., H. C. A.; Andrew, N.; Gary, N., The water vapor sorption behavior of natural fibers. *Journal of Applied Polymer Science* **2009**, *112* (3), 1524-1537, DOI 10.1002/app.29725.
36. Hussain, A.; Calabria-Holley, J.; Jiang, Y.; Lawrence, M., Modification of hemp shiv properties using water-repellent sol-gel coatings. *Journal of Sol-Gel Science and Technology* **2018**, *86* (1), 187-197, DOI 10.1007/s1097.

37. Collet, F.; Prétot, S.; Lanos, C., Hemp-Straw Composites: Thermal And Hygric Performances. *Energy Procedia* **2017**, *139*, 294-300, DOI 10.1016/j.egypro.2017.11.211.
38. Stetefeld, J.; McKenna, S. A.; Patel, T. R., Dynamic light scattering: a practical guide and applications in biomedical sciences. *Biophysical Reviews* **2016**, *8* (4), 409-427, DOI 10.1007/s12551-016-0218-6.
39. Thommes, M.; Kaneko, K.; Neimark Alexander, V.; Olivier James, P.; Rodriguez-Reinoso, F.; Rouquerol, J.; Sing Kenneth, S. W., Physisorption of gases, with special reference to the evaluation of surface area and pore size distribution (IUPAC Technical Report). In *Pure and Applied Chemistry*, 2015; Vol. 87, p 1051, DOI 10.1515/ci-2016-0119.
40. Sing, K. S. W.; Everett, D. H.; Haul, R. A. W.; Moscou, L.; Pierotti, R. A.; Rouquerol, J.; Siemieniowska, T., Reporting Physisorption Data for Gas/Solid Systems. In *Handbook of Heterogeneous Catalysis*, Wiley-VCH Verlag GmbH & Co. KGaA: 2008, DOI 10.1002/9783527610044.hetcat0065.
41. Brunauer, S.; Emmett, P. H.; Teller, E., Adsorption of Gases in Multimolecular Layers. *Journal of the American Chemical Society* **1938**, *60* (2), 309-319, DOI 10.1021/ja01269a023.
42. Takei, T.; Yamazaki, A.; Watanabe, T.; Chikazawa, M., Water Adsorption Properties on Porous Silica Glass Surface Modified by Trimethylsilyl Groups. *Journal of Colloid and Interface Science* **1997**, *188* (2), 409-414, DOI 10.1006/jcis.1997.4777.
43. Zhang, X.; Zheng, F.; Ye, L.; Xiong, P.; Yan, L.; Yang, W.; Jiang, B., A one-pot sol-gel process to prepare a superhydrophobic and environment-resistant thin film from ORMOSIL nanoparticles. *RSC Advances* **2014**, *4* (19), 9838-9841, DOI 10.1039/c3ra47185c.
44. Chang, C.-C.; Wu, Y.-T.; Cheng, L.-P., Preparation of HMDS-modified silica/polyacrylate hydrophobic hard coatings on PMMA substrates. *Journal of Coatings Technology and Research* **2016**, *13* (6), 999-1007, DOI 10.1007/s11998-016-9820-6.
45. He, J.; Li, X.; Su, D.; Ji, H.; Zhang, X.; Zhang, W., Super-hydrophobic hexamethyl-disilazane modified ZrO₂-SiO₂ aerogels with excellent thermal stability. *Journal of Materials Chemistry A* **2016**, *4* (15), 5632-5638, DOI 10.1039/c6ta00568c.
46. Esteves, B.; Velez Marques, A.; Domingos, I.; Pereira, H., Chemical changes of heat treated pine and eucalypt wood monitored by FTIR. *Maderas. Ciencia y tecnología* **2013**, *15*, 245-258, DOI 10.4067/S0718-221X2013005000020.
47. Rana, R.; Langenfeld-Heyser, R.; Finkeldey, R.; Polle, A., FTIR spectroscopy, chemical and histochemical characterisation of wood and lignin of five tropical timber wood species of the family of Dipterocarpaceae. *Wood Science and Technology* **2010**, *44* (2), 225-242, DOI 10.1007/s00226-009-0281-2.
48. Pandey, K. K., A study of chemical structure of soft and hardwood and wood polymers by FTIR spectroscopy. *Journal of Applied Polymer Science* **1999**, *71* (12), 1969-1975, DOI 10.1002/(SICI)1097-4628(19990321)71:12<1969::AID-APP6>3.0.CO;2-D.
49. Rosso-Vasic, M.; Spruijt, E.; van Lagen, B.; De Cola, L.; Zuilhof, H., Alkyl-Functionalized Oxide-Free Silicon Nanoparticles: Synthesis and Optical Properties. *Small* **2008**, *4* (10), 1835-1841, DOI 10.1002/smll.200990114.
50. Bywalez, R.; Karacuban, H.; Nienhaus, H.; Schulz, C.; Wiggers, H., Stabilization of mid-sized silicon nanoparticles by functionalization with acrylic acid. *Nanoscale Research Letters* **2012**, *7* (1), 76, DOI 10.1186/1556-276X-7-76.
51. Zou, J.; Baldwin, R. K.; Pattingrew, K. A.; Kauzlarich, S. M., Solution synthesis of ultrastable luminescent siloxane-coated silicon nanoparticles. *Nano Lett* **2004**, *4*, DOI 10.1021/nl0497373.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

For Table of Contents Use Only:

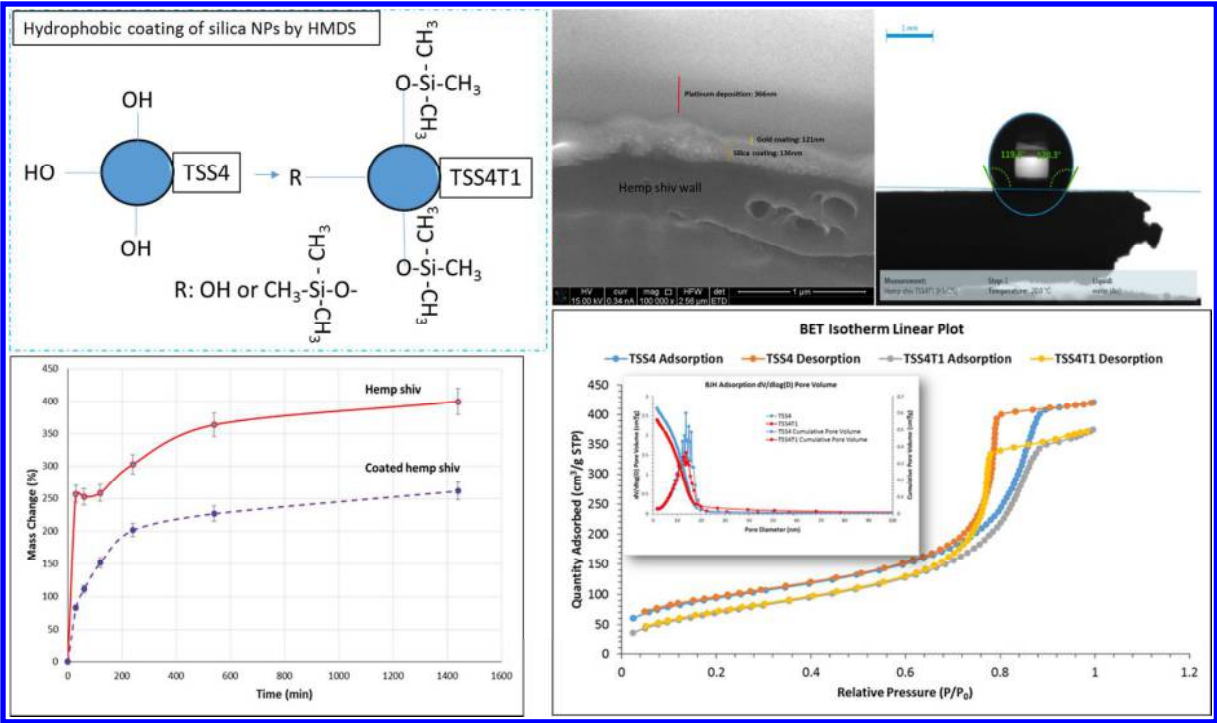

Synopsis:

This work develops bio-based materials for construction to offer a number of benefits as well as desirable environmental characteristics such as sustainability and renewability.