



HAL
open science

**Understanding the carbonation of concrete with
supplementary cementitious materials: a critical review
by RILEM TC 281-CCC**

Stefanie von Greve-Dierfeld, Barbara Lothenbach, Anya Vollpracht, Bei Wu,
Bruno Huet, Carmen Andrade, Cesar Medina, Charlotte Thiel, Elke Gruyaert,
Hanne Vanoutrive, et al.

► **To cite this version:**

Stefanie von Greve-Dierfeld, Barbara Lothenbach, Anya Vollpracht, Bei Wu, Bruno Huet, et al..
Understanding the carbonation of concrete with supplementary cementitious materials: a critical
review by RILEM TC 281-CCC. *Materials and structures*, 2020, 53 (6), 10.1617/s11527-020-01558-
w. hal-03122519

HAL Id: hal-03122519

<https://univ-rennes.hal.science/hal-03122519>

Submitted on 2 Mar 2021

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

[Click here to view linked References](#)

Understanding the Carbonation of Concrete with Supplementary Cementitious Materials – a critical review by RILEM TC 281-CCC

Stefanie v. Greve-Dierfeld, Barbara Lothenbach, Anya Vollpracht, Bei Wu, Bruno Huet, Carmen Andrade, César Medina, Charlotte Thiel, Elke Gruyaert, Hanne Vanoutrive, Isabel F. Saéz del Bosque, Ivan Ignjatovic, Jan Elsen, John L. Provis, Karen Scrivener, Karl-Christian Thienel, Kosmas Sideris, Maciej Zajac, Natalia Alderete, Özlem Cizer, Philip Van den Heede, Robert Douglas Hooton, Siham Kamali-Bernard, Susan A. Bernal, Zengfeng Zhao, Zhenguo Shi, Nele De Belie

Stefanie v. Greve-Dierfeld, TFB Technology and Research for Concrete Structures, Wildegg, Switzerland, orcid.org/0000-0002-9556-2027

Barbara Lothenbach, Swiss Federal Laboratories for Materials Science and Technology (Empa), Laboratory for Concrete & Construction Chemistry, Dübendorf, Switzerland, orcid.org/0000-0002-9020-6488

Anya Vollpracht, Institute of Building Materials Research, Faculty of Civil Engineering, RWTH Aachen University, Aachen, Germany, orcid.org/0000-0002-9950-5046

Bei Wu, Microlab, Faculty of Civil Engineering and Geosciences, Delft University of Technology, Delft, The Netherlands, orcid.org/0000-0002-2772-1065

Bruno Huet, LafargeHolcim Innovation Center, Saint-Quentin-Fallavier Cedex, France, orcid.org/0000-0002-9101-4605

Carmen Andrade, International Centre for Numerical Methods in Engineering (CIMNE), Barcelona, Spain, orcid.org/0000-0003-2374-0928

César Medina, University of Extremadura, Department of Construction, Institute for Sustainable Regional Development (INTERRA), Cáceres, Spain, orcid.org/0000-0001-7707-3118

Charlotte Thiel, Technical University of Munich, center for building materials, Munich, Germany, orcid.org/0000-0002-0092-468X

Elke Gruyaert, KU Leuven, Department of Civil Engineering, Structural Mechanics and Building Materials, Ghent, Belgium, orcid.org/0000-0003-0117-2544

Hanne Vanoutrive, KU Leuven, Department of Civil Engineering, Structural Mechanics and Building Materials, Ghent, Belgium, orcid.org/0000-0003-0356-8307

Isabel F. Saéz del Bosque; University of Extremadura, Department of Construction, Institute for Sustainable Regional Development (INTERRA), Cáceres, Spain, orcid.org/0000-0003-3786-9730

Ivan Ignjatovic; Department of materials and structures, Institute of materials and structures, Faculty of Civil Engineering, University of Belgrade, Belgrade, Serbia, orcid.org/0000-0002-2679-0982

Jan Elsen, KU Leuven, Department of Earth and Environmental Sciences, Leuven, Belgium. orcid.org/0000-0002-4370-3852

John L. Provis, Department of Materials Science & Engineering, University of Sheffield, Sheffield S1 3JD, United Kingdom, orcid.org/0000-0003-3372-8922

Karen Scrivener, Construction Materials Laboratory, École polytechnique fédérale de Lausanne, Lausanne, Switzerland, orcid.org/0000-0003-2640-1497

Karl-Christian Thienel; University of the Bundeswehr Munich, Department of Civil Engineering and Environmental Sciences, Neubiberg, Germany, orcid.org/0000-0002-4087-6205

1 Kosmas Sideris, Democritus University of Thrace, Department of Civil Engineering, Xanthi, Greece.
2 orcid.org/0000-0001-5005-2763

3 Maciej Zajac, Global R&D, HeidelbergCement AG, Leimen, Germany

4 Natalia Alderete, Ghent University, Department of Structural Engineering and Building Materials,
5 Ghent, Belgium, orcid.org/0000-0001-7967-1955

6 Özlem Cizer, KU Leuven, Departement of Civil Engineering, Leuven Belgium, orcid.org/0000-0003-
7 4281-8663

8 Philip Van den Heede, Ghent University, Department of Structural Engineering and Building
9 Materials, Ghent, Belgium, orcid.org/0000-0003-1307-2831

10 Robert Doug Hooton, Department of Civil & Mineral Engineering, University of Toronto, Toronto,
11 Kanada, orcid.org/0000-0003-2436-2738

12 Siham Kamali-Bernard, National Institute of Applied Sciences of Rennes, Rennes, France,
13 orcid.org/0000-0003-4263-811X

14 Susan A. Bernal, School of Civil Engineering, University of Leeds, Leeds, United Kingdom,
15 orcid.org/0000-0002-9647-3106

16 Zengfeng Zhao, University of Liège, Building Materials, Urban and Environment Research, Liège,
17 Belgium, orcid.org/0000-0002-7059-9085

18 Zhenguo Shi, Swiss Federal Laboratories for Materials Science and Technology (Empa), Laboratory for
19 Concrete & Construction Chemistry, Dübendorf, Switzerland, orcid.org/0000-0003-0000-6560

20 Nele De Belie, Ghent University, Department of Structural Engineering and Building Materials, Ghent,
21 Belgium, orcid.org/0000-0002-0851-6242

22
23
24
25
26 Corresponding author: stefanie.vongreve@tfb.ch

27 28 Abstract

29
30 Blended cements, where Portland cement clinker is partially replaced by supplementary
31 cementitious materials (SCMs), provide the most feasible route for reducing carbon dioxide
32 emissions associated with concrete production. However, lowering the clinker content can lead to an
33 increasing risk of neutralisation of the concrete pore solution and potential reinforcement corrosion
34 due to carbonation. Carbonation of concrete with SCMs differs from carbonation of concrete solely
35 based on Portland cement (PC). This is a consequence of the differences in the hydrate phase
36 assemblage and pore solution chemistry, as well as the pore structure and transport properties,
37 when varying the binder composition, age and curing conditions of the concretes. The carbonation
38 mechanism and kinetics also depend on the saturation degree of the concrete and CO₂ partial
39 pressure which in turn depends on exposure conditions (e.g. relative humidity, volume, and duration
40 of water in contact with the concrete surface and temperature conditions). This in turn influence the
41 microstructural changes identified upon carbonation. This literature review, prepared by members of
42 RILEM technical committee 281-CCC Carbonation of Concrete with Supplementary Cementitious
43 Materials, working groups 1 and 2, elucidates the effect of numerous SCM characteristics, exposure
44 environments and curing conditions on the carbonation mechanism, kinetics and structural
45 alterations in cementitious systems containing SCMs.

46
47
48
49
50
51 **Keywords** Carbonation, Supplementary Cementitious Materials, Aggregate, Environmental impact,
52 Transport properties

53
54
55 This article has been prepared by work group 1 and 2 within RILEM TC 281. The recommendation has
56 been reviewed and approved by all members of the TC

57
58 Chair: Nele de Belie

59
60 Deputy Chair: Susan Bernal

1 TC Members: Nele De Belie, Elke Gruyaert, Philip Van den Heede, Natalia Alderete, Ueli Angst,
2 Deepankar Kumar Ashish, Veronique Baroghel-Bouny, Muhammed Basheer, Leon Black, Patrick
3 Dangla, Susan Bernal, Aires Camões, Özlem Cizer, Martin Cyr, Vilma Ducman, Ana Fernández
4 Jiménez, Christoph Gehlen, Mette Geiker, Gregor Gluth, R. Doug Hooton, Bruno Huet, Ivan Ignjatović,
5 Siham Kamali-Bernard, Sylvia Kessler, Olonade Kolawole A, Tung-Chai Ling, Barbara Lothenbach,
6 Marija Nedeljkovic, César Medina Martínez, José Fernando Martirena Hernández, Jose Pacheco,
7 Angel Palomo, Solmoi Park, Ravi Patel, John Provis, Francisca Puertas, Javier Sanchez, Karen
8 Scrivener, Marijana Serdar, Kosmas Sideris, Ruben Snellings, Charlotte Thiel, Yury Villagrán Zaccardi,
9 Anya Vollpracht, Stefanie von Greve-Dierfeld, Brant Walkley, Fazhou Wang, Ling Wang, Li Juan, Yan
10 Yao, Guang Ye, Christian Thienel, Kei-ichi Imamoto, Fabrizio Moro, Jan Elsen, Hanne Vanoutrive,
11 Xinyuan Ke, Andres Idiart, Luca Valentini, Maciej Zajac, Shiju Joseph, Antonis Kanellopoulos, Shishir
12 Mundra, Quoc Tri Phung, Janez Perko, Bei Wu, Carmen Andrade, Isabel Fuencisla Saez del Bosque,
13 Zhenguo Shi, Heejeong Kim, Katja Dombrowski-Daube, Cyrill Grengg, Anna Varzina, Bahman Ghiassi,
14 Yogarajah Elakneswaran, Qing-feng Liu, Miren Etxeberria, Zhiyuan Liu, Zengfeng Zhao, Hans
15 Beushausen, Cassandre Le Galliard, Ning Li, Daniel Geddes, Semion Zhutovsky
16
17
18
19

20 1. Mechanisms of carbonation in cementitious hydrates, and CO₂ 21 sequestration 22

23 This section summarises the chemical reactions occurring during carbonation of cementitious
24 hydrate phases, and the effects of these reactions on hydrated reaction products and pore solution
25 chemistry. In Portland cement-based systems, the term carbonation describes the reaction of
26 dissolved carbonates with cementitious products, mainly through interaction with calcium ions that
27 are extracted from hydrate phases. Once CO₂ enters the material, at pH > 10, gaseous CO₂ rapidly
28 dissolves into the alkaline pore solution and subsequently hydrolyses to bicarbonate (HCO₃⁻) and
29 carbonate ions (CO₃²⁻) via a multi-step reaction sequence that can be summarised as: CO₂ + OH⁻ →
30 HCO₃⁻ → CO₃²⁻ + H⁺ [1-2]. At pH < 8, direct hydration of CO₂ occurs and results in carbonic acid H₂CO₃
31 (via CO₂ + H₂O → H₂CO₃), which can then dissociate into HCO₃⁻ and CO₃²⁻ ions [3] at higher pH. At pH
32 8-10, both mechanisms are important. In the pore solution the carbonate ions react with calcium
33 ions that are re-solubilised from the solid products, and precipitate as calcium carbonate.
34 Carbonation is a reactive transport process. The presence of water lowers the diffusion of gaseous
35 CO₂. At the same time, the presence of water is essential for calcium and carbon dioxide to dissolve
36 and react.
37

38 The main carbonation reaction product is calcium carbonate, which can precipitate in three
39 crystalline polymorphs: calcite, aragonite and vaterite, depending on the internal concrete conditions
40 (e.g. pH, temperature and supersaturation) [4], and the presence of impurities or additives [5-7].
41 Calcite is the most stable polymorph under ambient conditions, while metastable phases including
42 amorphous calcium carbonate, monohydrocalcite, vaterite and aragonite can form prior to or along
43 with calcite precipitation (Ostwald's rule of stages) [8-9]. Amorphous calcium carbonate and vaterite
44 form in the early stages of atmospheric carbonation and also during carbonation in a CO₂-rich
45 atmosphere [10-11]. Calcite and vaterite are the most common forms of CaCO₃ found in carbonated
46 cement paste [12-13] at ambient or close to ambient conditions.
47

48 The formation of calcium carbonate through carbonation leads to the release of some of the water
49 that was bound in portlandite and other hydrates, and results in changes in the total solid volume as
50 illustrated in Figure 1. These changes might be positive or negative dependent on the cement
51 chemistry and can have a major impact on porosity and hence on the transport properties of the
52 carbonated cement paste. Thermodynamic modelling of the carbonation of hydrated cement can be
53
54
55
56
57
58
59
60
61
62

1 used to understand the pH changes and the destabilisation sequence of the different Portland
2 cement hydrated products. The thermodynamic model depicted in Figure 1 shows the phase
3 assemblage of a white Portland cement as a function of the amount of CO₂ that has reacted with the
4 cement paste, and the corresponding decrease of pH and of the Ca/Si ratio of the calcium silicate
5 hydrate (C-S-H). Carbonation proceeds according to the following steps:
6

- 7 • Initially any monosulfate- and hemicarboxylate-AFm phases, if present, will destabilise to
8 monocarbonate-AFm [14], leading to small changes of the solid volume (molar volume of
9 monosulphate: 332 cm³/mol; hemicarboxylate: 285 cm³/mol and monocarbonate-AFm: 262
10 cm³/mol) (not shown in Figure 1).
- 11 • Portlandite is the first major hydrate that decomposes to calcium carbonate during
12 carbonation, leading to a moderate volume increase ($\Delta V=12\%$ of portlandite) as the molar
13 volume of calcite (36.9 cm³/mol) is greater than that of portlandite (33.0 cm³/mol). The pH
14 remains stable at around ~ 12.5 [12].
- 15 • After all accessible portlandite is consumed, C-S-H starts to decalcify down to a Ca/Si ratio of
16 ~ 1.3 . The pH decreases only marginally during this step. This decalcification is not
17 accompanied by significant volume change.
- 18 • Monocarbonate decomposes to strätlingite, which accommodates the released aluminium
19 and silicon from the C-S-H; C-S-H continues to be consumed without change of its Ca/Si ratio.
20 This reaction also leads to some changes of the solid volume. The molar volume of
21 monocarbonate (262 cm³/mol) is greater than that of strätlingite (216 cm³/mol), which is
22 compensated by the formation of calcium carbonate and consumption of C-S-H.
- 23 • After monocarbonate is consumed, the decalcification and decomposition of the C-S-H
24 continues down to Ca/Si of ~ 0.75 and pH of ~ 11 . This step is accompanied by the largest drop
25 in pH.
- 26 • Upon further carbonation strätlingite decomposes, followed by ettringite at pH around 10.
27 The released aluminium and sulphur are bound in aluminium hydroxide or zeolites [15] and
28 gypsum, respectively. In parallel, the C-S-H decalcifies to Ca/Si of around 0.67 while the pH is
29 lowered to 10.
- 30 • Upon further carbonation, C-S-H decomposed into calcite and hydrated amorphous silica and
31 the pH drops rapidly below 10 to 8.5.
- 32 • At the final stage, hydrotalcite decomposes at pH around 8.5.
- 33 • The total CO₂ bound is around 40 to 50 g CO₂/ 100 g Portland cement.

34
35
36
37
38
39
40
41 The same sequence of destabilisation is also observed in PC blended with fly ash [15], metakaolin
42 [16] and in calcium sulfoaluminate cements [14]. The consumption of calcium during the carbonation
43 reaction lowers the pH in pore solution from initially 13.5 to 14 (in the absence of carbonation) to
44 below 8, when the cement hydrates have completely carbonated. This decrease happens stepwise,
45 as the pH is buffered by different hydrate assemblages, which are destabilised [17-20]. This buffering
46 capacity, i.e. the amount of calcium oxide available, as well as the buffered pH depend on the type of
47 the hydrates [14, 21].
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

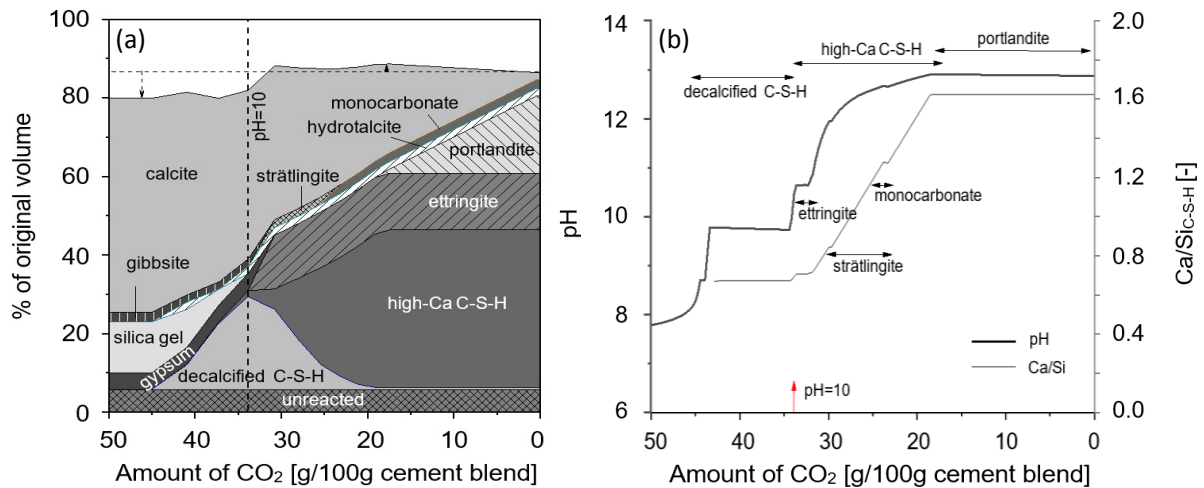


Figure 1 Thermodynamic modelling of the phase assemblage during carbonation of a white PC w/b = 0.5 and degree of hydration 90% (a), and changes of pH and Ca/Si of the C-S-H during carbonation (b). In both graphics, the undamaged cement paste is shown on the right-hand side, moving to the left as more CO₂ reacts with the hydrates. Adapted from [16]

It is worth noting, however, that under real carbonation exposure conditions different steps might occur simultaneously, and/or may halt before completion for kinetic or microstructural reasons, although the general sequence will be the same as indicated by thermodynamic modelling. For example, it has often been observed that not all portlandite and C-S-H are carbonated, particularly at low RH [13, 22-23]. From a thermodynamic point of view initially no C-S-H should decalcify, which does not agree with what has been reported in real carbonated pastes [24, 25].

Portlandite carbonation occurs as a consequence of a dissolution-precipitation reaction and the reaction kinetic is initially more rapid than the carbonation of C-S-H [13]. Calcium carbonate grows on the portlandite surfaces as illustrated in Figure 2, which slows down the further carbonation by limiting the transport of water and CO₂ [22-23]. CH carbonation releases water, while C-S-H loses water mainly upon complete carbonation [27].

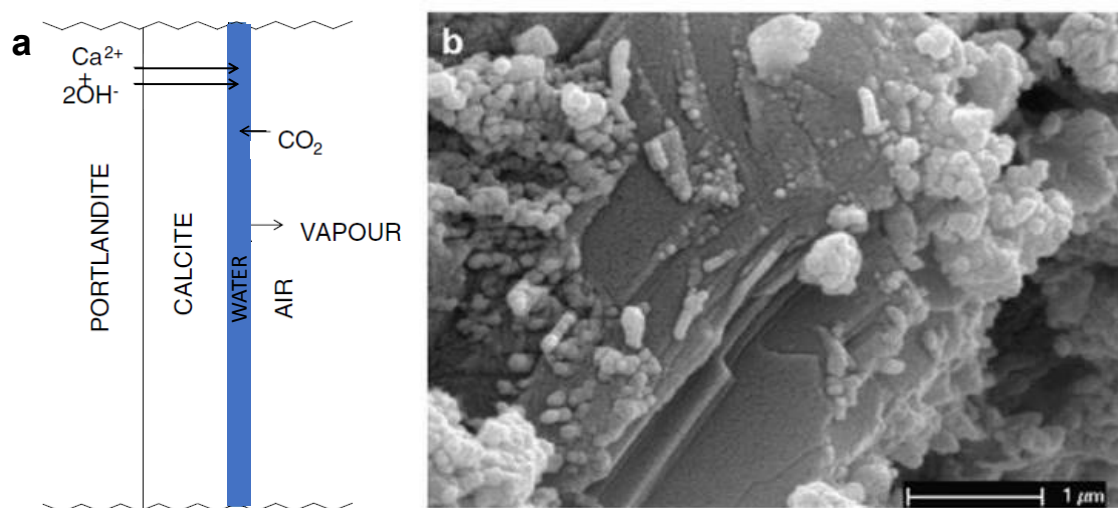


Figure 2. a) Schematic of diffusion through calcium carbonate layer formed on the top of portlandite during carbonation, from [22]; b) formation of calcite on the basal faces of portlandite, from [23]

1 The most abundant calcium-bearing phase in hydrated cement paste is C-S-H, and this is also the
2 phase that displays the most complex carbonation behaviour. The carbonation process of C-S-H
3 depends on its original Ca/Si ratio, CO₂ concentration, and on the presence of portlandite [28]. The C-
4 S-H carbonation proceeds in steps; first CaO is removed from the interlayer space. The initially short
5 silicate chains present in high-Ca C-S-H become longer until a C-S-H with a very low Ca/Si ratio of
6 around 0.7 and a pH value of 10 is reached. Only then is the main CaO in C-S-H also consumed,
7 leading to the formation of amorphous silica [11, 29] and further reduction of pH to around 8.5. The
8 destabilisation of C-S-H to silica gel, however, often remains incomplete, particularly at lower relative
9 humidity [27, 30].

11 The extent of C-S-H carbonation also depends on the CO₂ concentration [31]. Above 3 % of CO₂ in the
12 gas phase, C-S-H can fully decompose into calcium-modified silica gel, while below this
13 concentration, partially decalcified C-S-H was found after the “completion” of carbonation [29-32].
14 The behaviour of C-S-H gels also varies depending on Ca/Si, due to the composition dependence of
15 the thermodynamic stability of C-S-H [33].

17 Initial C-S-H decalcification, involving interlayer calcium, is not accompanied by significant volume
18 changes (see [Figure 1](#)), and C-S-H carbonation can thus contribute significantly to the densification of
19 cement paste microstructure by calcite precipitation. However, below a Ca/Si ratio of ~1.3, significant
20 decalcification shrinkage has been observed [34]. The fine-textured initial microstructure of C-S-H is
21 preserved after the initial decalcification [35], and both inner and outer C-S-H undergo a comparable
22 decalcification although only outer C-S-H shows morphological changes upon decalcification [35].
23 These morphological changes involve coarsening of the porosity and precipitation of calcium
24 carbonate at the tips of the C-S-H fibrils. Carbonation shrinkage has been observed to increase with
25 CO₂ concentration and with decreasing Ca/Si ratio, and shows a maximum at high to moderate
26 relative humidity [36], mainly attributed to the polymerisation of C-S-H.

27 The total amount of CO₂ that can be bound (binding or buffering capacity of a cement) depends
28 directly on the amount of CaO available to form CaCO₃ [9, 12, 23, 37], i.e., all CaO in the hydrates
29 minus calcium bound in calcium carbonate or calcium sulfates. Thus, the CO₂ binding capacity of
30 blended cements and calcium sulfoaluminate cements is generally lower than that of plain PC, since
31 the available CaO content is lower [14, 16-21]. Additionally, a lower degree of carbonation of
32 portlandite and calcium silicate hydrate in specific conditions alters the buffering capacity. These
33 differences mean that a direct application of the understanding of the carbonation mechanism and
34 CO₂ binding capacity for plain PC cannot be used to infer how concretes with SCMs will perform
35 when exposed to different environments.

45 2. Carbonation kinetics and carbonation coefficient

46 The dependence of carbonation resistance on CO₂ diffusion and the amount of carbonatable matter
47 is also clear from the well-known square-root-time relation (Equation 1) for carbonation rate,
48 mentioned in various literature including [38-40], which is essentially a solution to Fick's first law of
49 diffusion.

$$52 \quad x_c(t) = \sqrt{\frac{2 \cdot D_c \cdot c_s \cdot t}{a_c}} = \sqrt{\frac{2 \cdot c_s \cdot t}{R_{carb}}} = k \cdot \sqrt{t} \quad (1)$$

53 Here x_c is the carbonation depth (m), D_c is the diffusion coefficient of CO₂ (m²/s), c_s is the CO₂
54 concentration at the concrete surface (kg/m³), a_c is the amount of carbonatable material per unit
55 volume (kg/m³), t is the time (s), R_{carb} ($= a_c/D_c$) is the carbonation resistance ((kg/m³)/(m²/s)), and k ($=$
56
57
58
59
60
61
62
63
64
65

1 $\sqrt{2 \cdot c_s / R_{carb}}$ is the carbonation coefficient (m/√s). Eq. (1) assumes a linear decline of CO₂
2 concentration across the surface layer, from the CO₂ concentration at the concrete surface (c_s), down
3 to the concentration at the carbonation front, which has a negligible value. The carbonation progress
4 is accelerated with increasing CO₂ concentration (c_s) and increasing CO₂ diffusion coefficient (D_c) but
5 slows down with increasing amount of carbonatable material (a_c).
6

7 The formula containing the carbonation coefficient k in Eq. (1) is commonly used in experimental
8 studies. When plotting carbonation depths as a function of the square-root of the exposure time, a
9 more or less linear relationship is obtained, the slope of which is taken as the carbonation
10 coefficient.
11

12 It should be noted, though, that Equation 1 assumes a steady-state condition (i.e. constant
13 carbonation coefficient). However, since carbonation reaction products tend to block the pores in
14 concrete and cause a reduction in gas diffusivity, and because cementitious materials continue to
15 hydrate and refine the pores inside the material, the carbonation coefficient should decrease with
16 time (or depth). When carbonation coefficient becomes time dependent, Equation 2 can be applied
17 as used in [41, 42].
18

$$19 \quad k(t) = k_0 \cdot t^n \quad (2)$$

20
21 Here the exponent *n* should be negative, to account for pore blockage by reaction products, wetting
22 events, increased moisture content and ageing effects; a value of zero would define pure diffusion
23 control and an unchanging material, neither with depth nor time. A positive value indicates that the
24 material dries out and/or cracks due to carbonation shrinkage. The empirical exponent *n* was found
25 to be between 0.0 and -0.2 in [42]. They observed that *n* depends on curing duration and binder
26 type. Hunkeler and Greve-Dierfeld [43] showed for three days water cured samples a decrease in *n*
27 with decreasing w/b ratio and increasing relative humidity.
28
29

30
31 The carbonation resistance of a cement paste or a concrete – which is usually expressed in terms of
32 the depth to which atmospheric CO₂ has penetrated the material at a given time, or as a coefficient
33 describing this rate of ingress – depends not only on its CO₂ binding capacity, but also on its porosity
34 and pore size distribution [16, 21, 44]. Changes in the effective permeability due to
35 hydrate/carbonate volume changes and microcracking can be a significant consequence of
36 carbonation [45]. In concretes with conventional SCMs, an increase in porosity upon carbonation is
37 typically reported, in contrast to plain PC systems where carbonation decreases their permeability
38 due to pore blocking as discussed above [46]. However, the correlation between the hydrate
39 products in blended PCs and the associated volume and permeability changes is not yet clear. Of
40 more concern, it is not clear what mechanism is leading to microcracking, and to what extent these
41 microcracks might modify the transport properties of the carbonated layer, reducing the resistance to
42 ingress of CO₂. Due to the large variety of SCMs used in the production of modern concretes and the
43 broad range of properties exhibited by concretes produced with them, in the following sections the
44 main effects of the type and amount of SCM added are discussed, as well as the influence of concrete
45 mix design parameters and other factors on the carbonation process of SCM-containing materials.
46
47
48
49
50
51
52

53 3. Concrete mix design and its effect on carbonation

54 3.1. Effect of SCM type

55
56 When PC is blended with SCMs, the phase assemblages and chemistry of the pore solution change
57 significantly. In PC blended with siliceous SCMs, a reduced content of portlandite is present, as
58 consequence of pozzolanic or latent-hydraulic reactions. The main reaction product observed is an
59
60
61
62
63
64
65

1 Al-substituted C-S-H type phase, with lower Ca/Si than in plain PC systems [47]. Formation of
2 different secondary reaction products such as layered double hydroxides (e.g. AFm phases and Mg-Al
3 hydroxides) is also reported when using Al-rich SCMs [48].

4 The effect of SCMs on the chemistry and properties of cementitious materials has been extensively
5 evaluated, including by recent RILEM technical committees, and the reader can find more detailed
6 information in [49-51]. In this review a brief description of the chemistry of SCM-blended cements is
7 presented to explain potential correlations between material properties and carbonation
8 performance.
9

10
11 Addition of SCMs can increase the early reactivity of PC clinker due to its (physical) filler effect
12 promoting nucleation and growth of the hydrates, and the higher effective water/cement (w/c) ratio
13 [52-53]. In the pozzolanic reaction SiO_2 and Al_2O_3 react with water and CH to form additional C-S-H
14 with a reduced Ca/Si ratio, an increased silicate mean chain length, and some incorporation of Al [54-
15 55]. Thermodynamic calculations indicate that for complete consumption of portlandite, the
16 required ratio of SCM to total binder content is approximately 75 wt.% for blast furnace slag (BFS)
17 [44, 53], 35 wt.% for Class F/siliceous fly ash (FA), 18 wt.% for silica fume (SF) [47, 57-58] and 6-
18 18 wt.% for metakaolin (MK) [59], although microstructural (kinetic) constraints can lead to the
19 persistence of portlandite at higher SCM contents than would be indicated from thermodynamics
20 alone [60]. The consumption of portlandite leads to a reduced pH value in the pore solution, which is
21 in the range of $\text{pH}_{\text{PC,LS}} \approx 12.7-13.8$, $\text{pH}_{\text{BFS,FA,MK}} \approx 12-13$, $\text{pH}_{\text{SF}} \approx 11.0-12.5$ at high clinker replacement
22 levels, according to [57, 61-62] and is accompanied by reduced K^+ and Na^+ concentration [15, 57].
23 Furthermore, a reduction of coarse porosity and an improvement in quality of the interfacial
24 transition zone are generally noticed [61, 63].
25
26
27
28
29

30 Limestone (LS) provides CaO mainly in form of CaCO_3 . The replacement of a small amount of PC by
31 limestone is beneficial as it promotes nucleation and increases the effective w/c ratio for hydration
32 [64]. In addition, CaCO_3 can react with C_3A to form monocarboaluminate, which indirectly stabilises
33 ettringite by increasing sulfate availability, leading to an increase of the total volume of hydrate
34 phases [16, 64-66]. According to [67], 15 wt.% LS addition with a similar size distribution to PC, and
35 used as an addition instead of interground, increases porosity of the hydrated binder, while a smaller
36 size distribution and intergrinding decreases porosity.
37
38
39

40 Figure 3a shows a Ca-Si-Al ternary diagram, highlighting the regions corresponding to the major SCM
41 groups and Portland cement [68]. Figure 3b shows cement hydrate phases that commonly form from
42 Portland cement – SCM blends in the $\text{H}_2\text{O}-\text{CaO}-\text{Al}_2\text{O}_3-\text{SiO}_2$ system [47]. The precise extent of the C-S-
43 H and C-A-S-H domains is the subject of ongoing research, but these graphics do highlight the broad
44 range of compositions of the main binding phases forming in SCM blended cementitious systems, as
45 a function of the type of SCM used.
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

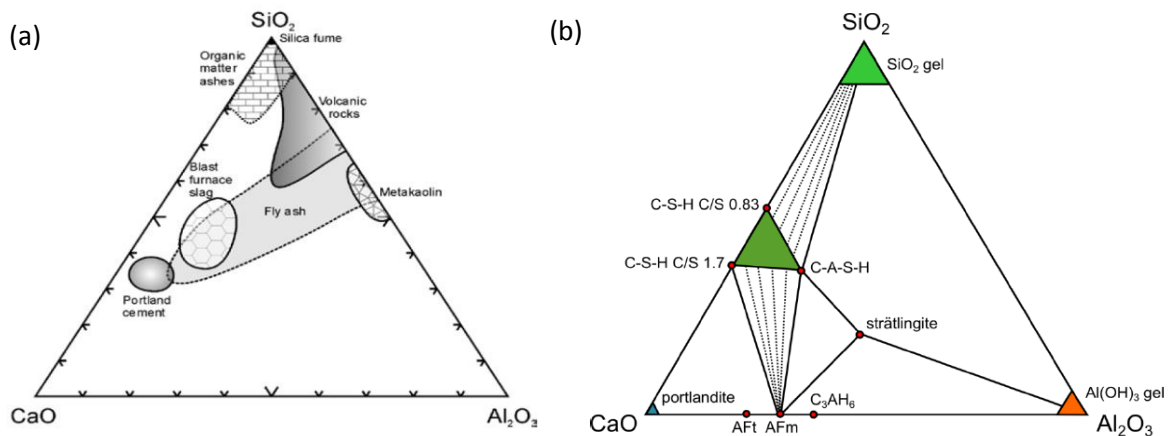


Figure 3 Pseudo ternary diagrams, presented on a wt.-% basis, of (a) the major SCM groups and Portland cement [68]; and (b) hydrate phases from Portland cement – SCM blends [47]

The significant difference in Al_2O_3 contained in SCMs influences the composition and structure of the C-A-S-H phases and secondary reaction products forming in these materials [44]. Therefore, the role of Al in defining the carbonation rates and mechanisms of C(-A)-S-H has received some attention in the recent literature. Irbe [69] found faster carbonation of C-A-S-H than a comparable C-S-H gel when testing synthetic gels of molar ratio $\text{Ca}/(\text{Al}+\text{Si}) = 0.96\text{-}0.97$, under 0.04%, 2% and 4% CO_2 conditions. The thermogravimetry data of [70] show a significant increase in CaCO_3 formation after 28 days of carbonation of synthetic gels of molar ratio $\text{Ca}/(\text{Al}+\text{Si}) \sim 1$ when moving from zero Al content to $\text{Al}/\text{Si} = 0.02$, but no notable trend when increasing Al content further up to $\text{Al}/\text{Si} = 0.14$. In this study and other publications [29, 71] the formation of an additional Al-enriched silicate gel as a carbonation product is described when C-A-S-H gels are decalcified. This phase (and/or the formation of additional potential Al-containing reaction products) deserves further attention in characterisation, as its formation may alter the energetics of the carbonation process sufficiently to induce changes in its rate or mechanism.

According to several studies [42, 72-74], PC carbonation under moderate environmental conditions is governed by the reaction of portlandite to mainly form calcite, yielding a denser microstructure due to the positive difference of molar volume of calcite compared to CH (+4 cm^3/mol as mentioned in section 1), which more than compensates the shrinkage induced by C-S-H decomposition and subsequent microcracking e.g. [74-75].

In the case of BFS-blended cements, with increasing C-A-S-H carbonation the percentage of the CaCO_3 that is present as calcite is found to be reduced, while the metastable aragonite and vaterite tend to increase [21, 75-77]. The microstructural changes identified in these materials lead to higher permeability [75] and diffusivity [78] after carbonation, compared to PC with the same water to binder (w/b) ratio. The reduced calcium and alkali contents lead to a lower buffering capacity in BFS blended cements, and polymerisation shrinkage may lead to increased porosity. Experimental results from [79-80] indicate that at a replacement level $\geq 25\%$, the carbonation resistance is decreased compared to plain PC. Several researchers have determined that, under moderately accelerated carbonation conditions (3-5 vol.-% CO_2), not all portlandite and C-A-S-H were consumed during carbonation of BFS-blended cements [21, 26]. However, especially at high BFS replacement levels, the degree of portlandite and C-A-S-H carbonation is higher compared to plain Portland cement systems [21, 74]. This may compensate for the lowered buffering capacity to some extent, because if the degree of portlandite and C-A-S-H carbonation is increased, the actual available Ca is increased. However, if the maximum possible degree of portlandite carbonation is reduced, for example

1 because portlandite is covered by calcium carbonate crystals and therefore the release of Ca from
2 portlandite into the pore solution is hindered, the available Ca to buffer carbonation is reduced.

3 Compared to BFS, low calcium fly ash (FA) provides less initial CaO to blended systems. At the same
4 FA replacement level (30 wt.%), portlandite reduction compared to PC is higher for FA than for BFS
5 [15, 64-65, 76, 81]. A higher degree of C-A-S-H carbonation (full polymerisation) was identified at
6 > 20 wt.% FA replacement levels [73]. A less pronounced decrease in mercury and water intruded
7 porosity upon carbonation has been found in FA blended systems compared to plain PC and BFS-
8 containing concretes [24, 27, 77, 82-83] and an increase in pore size threshold upon carbonation
9 [82]. The slow pozzolanic reaction of FA compared with slag hydration, and the higher degree of C-A-
10 S-H carbonation accompanied by a release of physical water [73] may be a reason for the deviation
11 from Fick's first law that has been observed in these systems [42, 84-85]. There is an increase in the
12 partly carbonated zone with increasing FA replacement, determined through depth dependent pH
13 measurements by the ex-situ leaching method [86], indicating divergence from the assumption of
14 pure diffusion-controlled kinetics required for Fickian diffusion (and formation of a sharp
15 carbonation front). In several studies [87-90], a significant increase in carbonation progress
16 compared to PC was found with increasing FA replacement levels between 30 and 50 wt.% for the
17 same w/b ratio. The difference was more pronounced for longer water curing durations (> 7 days)
18 and high relative humidity during carbonation exposure. Thomas and Matthews [91] found that
19 concretes with the same strength grade containing 15-30 wt.% FA in the cementitious fraction
20 carbonated to only a slightly greater extent than plain PC. However, concretes containing 50 wt.% FA
21 carbonated at a significantly higher rate than PC concrete.

22 From a thermodynamic point of view, less CO₂ can be bound if less calcium is available in the liquid
23 and solid phases (except CaO already bound in CaCO₃ or CaSO₄) and if less Na⁺ or K⁺ are available in
24 the pore solution. When using highly siliceous SCMs such as SF, where Al₂O₃ and CaO are solely
25 provided by the Portland clinker, the carbonation reaction process is comparable to that identified in
26 plain Portland cement systems, as the main reaction product forming is C-S-H. For synthetic C-S-H it
27 has been reported [33, 92] that with an increasing molar ratio of C-S-H versus portlandite, i.e. with
28 increasing C-S-H carbonation, decalcification shrinkage may be dominant, leading to a coarsening of
29 the pore structure. The carbonation (decalcification) shrinkage seems to increase with the degree of
30 C-S-H polymerisation, and with a decrease in Ca/Si molar ratio. Carbonation shrinkage may reverse
31 the beneficial, experimentally determined, porosity reduction that is related to portlandite
32 carbonation to CaCO₃ [27].


33 The C-S-H amount in SF blended paste is high and the amounts of ettringite and AFm are reduced
34 compared to PC or blends containing FA or BFS. However, the higher extents of self-desiccation and
35 autogenous shrinkage leading to high internal stresses and micro-cracking, a pronounced reduction
36 of pH, challenges of early-age workability, and high increase in strength provided by small amounts of
37 SF addition usually lead to its application at low replacement levels. The number of published
38 research papers on carbonation of SF-blended binary [78, 93, 96] and ternary [74] cement pastes is
39 limited compared to BFS or FA blends. According to Leemann et al. [96], the reduction in total
40 porosity of SF blended cement paste is less pronounced and coarse porosity is increased compared to
41 PC upon carbonation. Consequently, higher oxygen diffusion coefficients are expected for carbonated
42 SF blended cementitious materials than for PC and BFS blended cements for similar replacement
43 levels. A decreasing carbonation resistance compared to PC was found for constant w/b [96] and for
44 constant strength grade [93].

45 MK provides less CaO than FA but makes available more Al₂O₃ into the cementitious system than
46 other SCMs. Carbonation when using MK or other calcined clays as SCMs has been investigated in an

1 increasing number of studies [16, 25, 83, 93-94]. At moderate replacement levels, a negligible
 2 amount of portlandite was found prior to carbonation due to pozzolanic reaction, and the C-A-S-H
 3 carbonation degree was higher than for PC (polymerised C-A-S-H for MK, decalcified C-S-H for PC)
 4 [16]. Consequently, the accessible porosity was on a similar level [16, 83] and the threshold pore
 5 radius was increased compared to PC upon carbonation [16]. Higher carbonation rates were found
 6 for MK blended cementitious materials either for a constant strength grade [93] or for constant w/b
 7 [16] upon carbonation compared to PC, but lower than for SF blends [93] or for LS blends [16] at the
 8 same replacement level.
 9

10 Initial portlandite contents in LS blended cement pastes are slightly lower than in PC pastes [16, 64,
 11 66]. The LS-containing pastes were found to carbonate to a higher degree [16, 95]. Both the initial
 12 porosity and the porosity upon carbonation were increased compared to PC. A similar reduction in
 13 accessible porosity compared to plain PC was found after carbonation [16, 96], leading to a reduced
 14 diffusivity.
 15
 16

17 Figure 4 shows some effects of clinker replacement levels on the change in carbonation coefficient
 18 relative to PC mixes as reported by different authors - all samples have been cured for 28 days.
 19 According to these analyses, at the same replacement level the reduction in carbonation resistance is
 20 more pronounced for FA and SF blended concretes and mortars, than for LS or BFS blended concretes
 21 and mortars. It should be stated that differences in w/b, aggregate type and grading, execution and
 22 carbonation conditions can affect these results.
 23
 24
 25
 26
 27

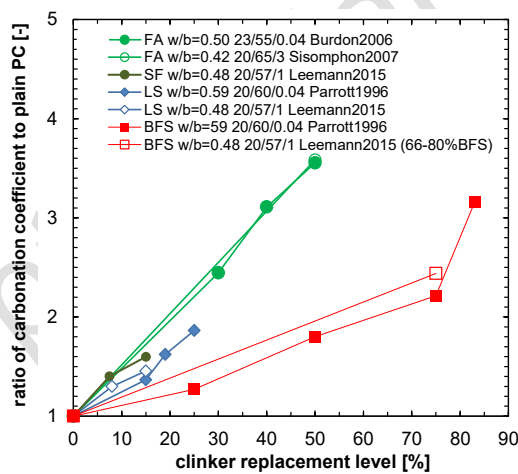

28 Figure 4 Effect of clinker replacement on carbonation coefficients for 28-day water cured concrete
 29 and mortar samples. The notation 20/65/0.04 indicates T [°C] / RH [%] / CO₂ [vol.%]. Data from [79,
 30 87, 96]
 31
 32
 33
 34
 35
 36
 37
 38
 39
 40
 41
 42

43 In order to assess the carbonation resistance of a specific cementitious material from its composition
 44 three main approaches have been developed:
 45
 46
 47

- 48 (a) estimating carbonation resistance based on the clinker content and water to binder ratio
 49 (w/b) [41, 97]
- 50 (b) k-value concept (EN 206), using the type of SCM and water/(cement + k-addition) (w/c_{eq}) [99]
- 51 (c) assessing buffering capacity based on the ratio of mixing water to reactive calcium oxide
 52 (w/CaO_{reactive}), see Section 1 [44, 96, 100]

53 Figure 5 a), b), c) illustrate the approaches (a), (b) and (c), respectively.
 54
 55
 56
 57
 58
 59
 60
 61
 62
 63
 64
 65

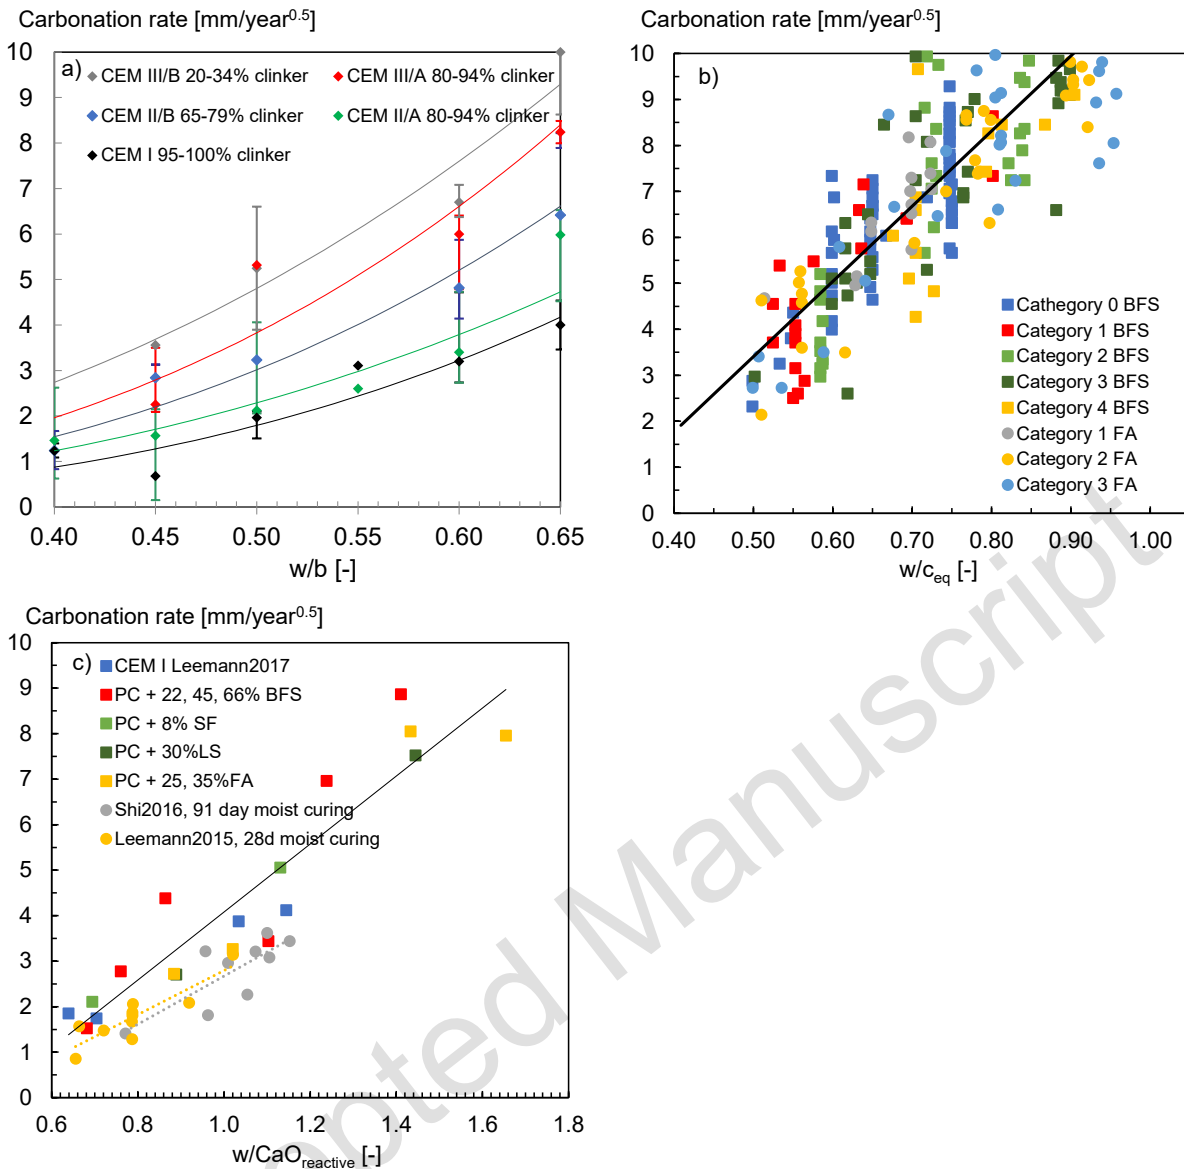


Figure 5 approach (a) carbonation resistance in dependency of w/b and clinker content for 7-day water cured concretes (20°C / 65% RH / 0.04 vol.% CO₂) [41, 97]. Error bars indicate \pm standard deviation; b) approach (b) carbonation resistance in dependency of w/c_{eq} of concretes [99] c) approach (c) carbonation resistance in dependency of $w/CaO_{reactive}$ of samples tested according to SIA262-1 [44] and samples cured for 91-day [100] and 28-day [96] carbonated at 1% CO₂ and related to 0.04 % CO₂

The approach (a), which uses the clinker content and w/b [41, 97], shows carbonation rates of concretes water cured for 7-day and carbonated at 65% RH, 20°C under natural CO₂ concentration. The lines show the potential regression curves to the mean carbonation rates of groups of concretes summarized in dependency of the ranges of clinker content according to EN197-1, including CEM I (95-100% clinker), CEM II/A (80-94% clinker), CEM II/B (65-79% clinker), CEM III/A (35-64% clinker) and CEM III/B (20-34% clinker). In addition the effect of maximum grain size (4 - 32 mm), admixtures (retarder, water reducers, air-entrainment agent), binder content, cement strength grade and clinker replacement level by specific types of SCM has been evaluated for mixes with the same w/b ratio. No systematic effect has been found for the maximum grain size, binder content and the admixture except for the air-entrainment admixture. With air-entrainment admixture the carbonation rate increased at fresh concrete air content > 8 %. A small decrease in carbonation rate has been found

1 with increasing cement strength grade in this curing protocol. The increase in carbonation rate with
2 increasing replacement level was higher for LS than for BFS.

3 The k-value concept, approach (b) according to [99], shows carbonation rates of concretes water
4 cured for 7-day and carbonated at 65% RH, 20°C under natural CO₂ concentration. Based on the
5 equivalent performance concept for type II additions in CEN/TR 16639 the efficiency factor k_c has
6 been determined for the concrete property carbonation rate. The efficiency factor is used to reduce
7 the creditable amount of mineral addition when calculating the w/c_{eq} with $c_{eq} = \text{clinker} + k_c \cdot \text{addition}$.
8 Using the w/c_{eq} the same performance shall be reached as if pure Portland cement would have been
9 used with the same $w/c = w/c_{eq}$ ratio. Hence, plain PC concrete has the efficiency factor $k_c = 1.0$,
10 which is named category 0. For BFS and FA blended cements 3 and 2 categories have been built,
11 respectively. Increasing category represents increasing amount of type II addition. For example, CEM
12 III/B concretes are allocated to category 3 BFS. Efficiency factors were in the range of 0.8-0.6 for BFS
13 blended cement concretes and 0.3-0.35 for FA blended cement concretes. For BFS blends the
14 efficiency factors were in the range of those determined in [101] with 0.65-0.81 and higher than
15 determined in [98] with 0.2-0.4. For FA blends the efficiency factor was similar with those
16 determined in [101] with 0.25-0.58 and [98] with 0.05-0.3.

17 Approach (c) [44, 96, 100] replaces the clinker content in approach (a) by the amount of all CaO
18 available to react with CO₂, i.e. $w/\text{CaO}_{\text{reactive}}$ ($w/\text{CaO}_{\text{reactive}}$). In order to determine the $\text{CaO}_{\text{reactive}}$
19 Papadakis et al. [38] suggested a simplified mass balance equation to calculate CaO: $[\text{Ca}(\text{OH})_2] + 3[\text{C-S-}$
20 $\text{H}] + 3[\text{C}_3\text{S}] + 2[\text{C}_2\text{S}]$, this expression however, neglects CaO present in aluminates or ferrite phases. For
21 modern cements, which can contain significant amounts of calcium carbonate as an SCM or minor
22 additional constituent, the fraction of CaO already bound by CaCO₃ has also to be considered as well
23 as the amount of SO₃, as SO₃ will be present as CaSO₄ in completely carbonated cements [14, 21].
24 Also, the amount of CaO present in unreacted cement clinker and supplementary cementitious
25 material must be accounted for [14, 21, 44]. Thus, the CaO available for carbonation can be
26 calculated according to: $\text{CaO}_{\text{reactive}} = \text{CaO}_{\text{total}} - \text{CaO}_{\text{CaCO}_3\text{-init}} - \text{CaO}_{\text{CaSO}_4} - \text{CaO}_{\text{unreacted clinker}} - \text{CaO}_{\text{unreacted SCM}}$
27 where each term can be determined using thermodynamic modelling (see Figure 1) or mass balance
28 calculations.

29 The simplified approaches (a-c) used to describe the carbonation resistance in dependency of
30 parameters of the mix design have their benefits and drawbacks. Approach (a), clinker content and
31 w/b , is simple to apply, but it neglects the buffering capacity of the specific type of SCM and their
32 differences regarding alteration in pore size distribution upon carbonation. The K-value concept,
33 approach (b) is less simple to apply because it requires the allocation of the specific concretes to
34 efficiency factor required for each type of SCM. Approach (c), is the most scientific approach. It also
35 accounts for the contribution of SCM on CO₂ binding capacity. But for its application, the reactive
36 CaO content has to be known or assessed and the effect of specific types of SCM on pore size
37 distribution are little accounted for. Approach (a) and (b) are restrictive regarding the
38 implementation of new materials, while in approach (c) new materials can be simply included. All
39 three approaches are highly dependent on degree of hydration. In all three approaches, the mixing
40 water w accounts for the diffusivity i.e. the volume of capillary pores. Alteration of porosity prior and
41 upon carbonation due to the use of alternative materials and SCM's is little accounted for.

42 In addition to those three approaches, which describe the carbonation resistance based on the mix
43 design, other approaches have been developed, which describe carbonation resistance based on
44 compressive strength [101-102] or permeability [103]. For a 7 day compressive strength between 20
45 and 25 MPa the carbonation rate was found to be in the range between 4 to 7 mm/year^{0.5} in [102]
46 for concrete samples water cured for 7 day and carbonated at 65% RH, 20°C and natural CO₂. The

concretes where prepared with CEM I, CEM III/A, CEM II/B-M and CEM IV as well as CEM II/C-M cements and the carbonation rate was the highest for concretes with high clinker replacement levels within the same strength grade. Similar were the results from [101] for samples carbonated in 2% CO₂ converted to 0.04 vol.-% with $k(0.04\% \text{ CO}_2) = k(2\% \text{ CO}_2) \cdot \sqrt{(0.04/2)}$. Imamoto et al. [103] used the correlation between air permeability and carbonation rate determined from existing structures, and thus under variable environmental conditions (moisture, temperature, CO₂ concentration) in Japan, Switzerland and Portugal to rate the quality of the placed concrete. For example, for a coefficient of air permeability between 0.1 and 1 10⁻¹⁶ m² the concrete was classified moderate and the carbonation rate was found in the broad range between > 0 and 5 mm/year^{0.5}. Compressive strength as well as the air permeability are indicators for the air tightness of a concrete and hence also its resistance against CO₂ diffusion; however compressive strength does not account for the CO₂ binding capacity of the specific type of binder and the differences in alteration of pore size distribution upon carbonation. This may explain to some extent the high scatter observed for this correlation. The benefit of both approaches is that the compressive strength is usually available and the air permeability [103] may be determined non-destructively.

To summarize, the carbonation resistance is depending on more factors than just the clinker replacement level, FA or BFS, the calcium oxide content, compressive strength or air permeability. In addition, the binder specific alteration of porosity, the reaction products formed, the composition dependent reaction kinetics, the degree of hydration, the water retention and hence the testing conditions are important parameters, which leads to a limited precision in all the correlations discussed above.

3.2. Aggregate volume and grading: paste-mortar-concrete

The carbonation coefficients reported in [38-39] for plain Portland cement concrete samples carbonated at 50 vol.% CO₂, 30°C and 65% RH increased by a factor of 1.1 and 1.5 when the aggregate to cement ratio (a/c) increased by a factor of 1.7 and 2.3, respectively. Similar results have been reported at 5 vol.% CO₂ [104]. If a coarser aggregate was used (unchanged total volume of aggregate), the measured carbonation depth was similar or slightly higher [38-39]. In contrast, Jung et al. [105] found no significant differences in the effective CO₂ diffusion coefficients between concrete and mortar, but a significant increase in diffusivity was observed for cement paste systems upon carbonation (i.e. if the a/c ratio decreases). The increase of gas diffusion coefficient for paste systems was explained by the larger porosity per unit of volume hydrated paste compared to hydrated concrete. This is in line with investigations of plain Portland cement pastes and mortars from [27, 105-106].

Carbonation rates of cement paste, mortar and concrete systems have been compared in [107]. Figure 6 plots the carbonation coefficients obtained after 7 weeks in 2 and 10 vol.% CO₂ for cement paste, mortar and concrete, manufactured with either 30 wt.% PC replacement by FA (70PC30FA), or 70 wt.% PC replacement by BFS (30PC70S). Carbonation coefficients of mortar and cement paste (w/b=0.5) were higher by a factor of 1.2-1.3 and 1.6-2.3, respectively (depending on binder type and CO₂ concentration), compared to the carbonation coefficients of concrete. The increase in carbonation coefficient for cement paste compared to concrete is more pronounced for FA than for slag systems, and more pronounced at higher CO₂ concentration. A better correlation has been observed between mortar and concrete (R² = 0.96) than between cement paste and concrete (R² = 0.82 for w/b ratio of 0.50).

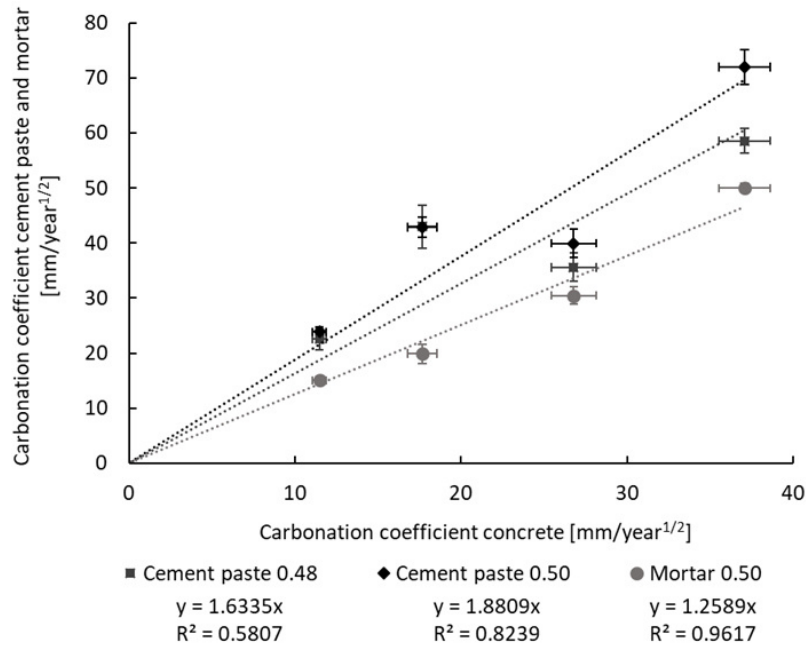


Figure 6 Carbonation coefficient of cement pastes with w/b ratios of 0.5 and 0.48 (based on the concrete equivalent mortar principle [108]), and concrete equivalent mortar (w/b ratio of 0.5) versus carbonation coefficient of concrete (w/b ratio of 0.5), according to [107].

The increase in carbonation coefficient with increasing a/c for PC concretes reported in [38-39, 104] may be attributed to the increasing fraction of more porous portlandite-rich interfacial transition zone (ITZ) providing paths for fast CO₂ diffusion [77]. In contrast, the faster carbonation in the presence of less aggregate reported in [107] could be related to more autogenous and drying shrinkage in case of cement paste system and subsequent increase of porosity [106-109].

The majority of studies evaluating carbonation resistance when using SCMs are conducted in paste and mortars, with the assumption that the observations for these systems can be directly translated into concrete. However, this is not the case for the data shown here due to the differences in CO₂ diffusivity, consistent with variations in pore structure based on the different paste contents and ITZ zones; differences in the degree of water saturation in materials with diverse permeability; and the different type and amount of carbonation products expected to be forming at a given time. The porosity of carbonated and partly carbonated regions as well as the amount of cement phases buffering the reactions involving CO₂, will modify the carbonation reaction kinetics. This has important implications for the development of modelling tools for prediction of the long-term performance of concretes with SCMs, and for the determination of the real carbonation resistance of these materials.

3.3. Effect of recycled and lightweight aggregate

Independent of the SCM used, concretes produced with recycled and lightweight aggregate show to some extent different carbonation performance from those produced with conventional dense aggregates. Recycled aggregate (RA) may contain mortar, unbound aggregate, ceramics, floating particles and bituminous matter. Its different physical (e.g. water absorption, porosity) and mechanical properties (e.g. Los Angeles coefficient) compared with natural aggregate may impact concrete performance. In recent reviews on the durability of concretes with recycled aggregates, Guo et al. [110] and Silva et al. [111] reported that concrete carbonation resistance is affected adversely

1 by the aggregate replacement ratio, w/c ratio, adhered mortar, aggregate size, and exposure time,
2 particularly in concretes with SCMs. Carbonation resistance improves with addition of
3 superplasticisers, consistent with a reduced water content in the concrete, and can also be improved
4 by RA pre-treatment.

5
6 Even in the absence of major RA contaminants, due to the heterogeneity and wide variability in the
7 properties of recycled concrete aggregate (RCA), which depend on its source and service history, it is
8 impossible to draw general conclusions about its potential effect on carbonation performance of
9 concretes with SCMs. However, numerous authors [112-124] studying the effect of the RCA
10 replacement ratio on carbonation resistance of concretes with and without SCMs found that in the
11 case of coarse aggregate replacement the carbonation depth, relative to normal concrete, increased
12 1.06 to 2.00-fold. However, some studies report higher carbonation resistance in RCA concrete [119,
13 125-126], which can be explained by two mutually opposing effects, as the adverse effect of larger
14 porosity counteracts the benefits of greater amounts of (alkaline) carbonatable matter
15 (uncarbonated mortar). Using recycled aggregate as fine rather than as coarse aggregates seems to
16 increase the carbonation depth, so that concrete with RCA showed carbonation depths up to 3.75 to
17 12.25 times greater than for concrete with natural aggregate [127-130].

18
19 The use of porous and gas-permeable lightweight aggregate (LWA) requires a concrete cover at least
20 5 mm thicker than the maximum particle size [131]. LWA nonetheless lowers concrete gas
21 permeability, as it absorbs the water in fresh concrete which can form an adhesive water layer on a
22 `dense` aggregate surface. The water adsorption may reduce the water/binder ratio around the LWA
23 in the aggregate-matrix interface, and thus eliminates the interfacial transition zone (ITZ) typically
24 identified when using natural aggregates (Figure 7). As cement hydration reactions proceed, the
25 absorbed water migrates from the LWA to the hydrating cement paste, favouring internal curing. The
26 outcome is a larger high-quality paste-aggregate transition zone (larger grey zone in figure 7 bottom
27 left), less permeable in lightweight than in normal concrete [132-133]. Research on existing
28 structures confirms the beneficial impact of LWA on the carbonation coefficient [134-136].
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

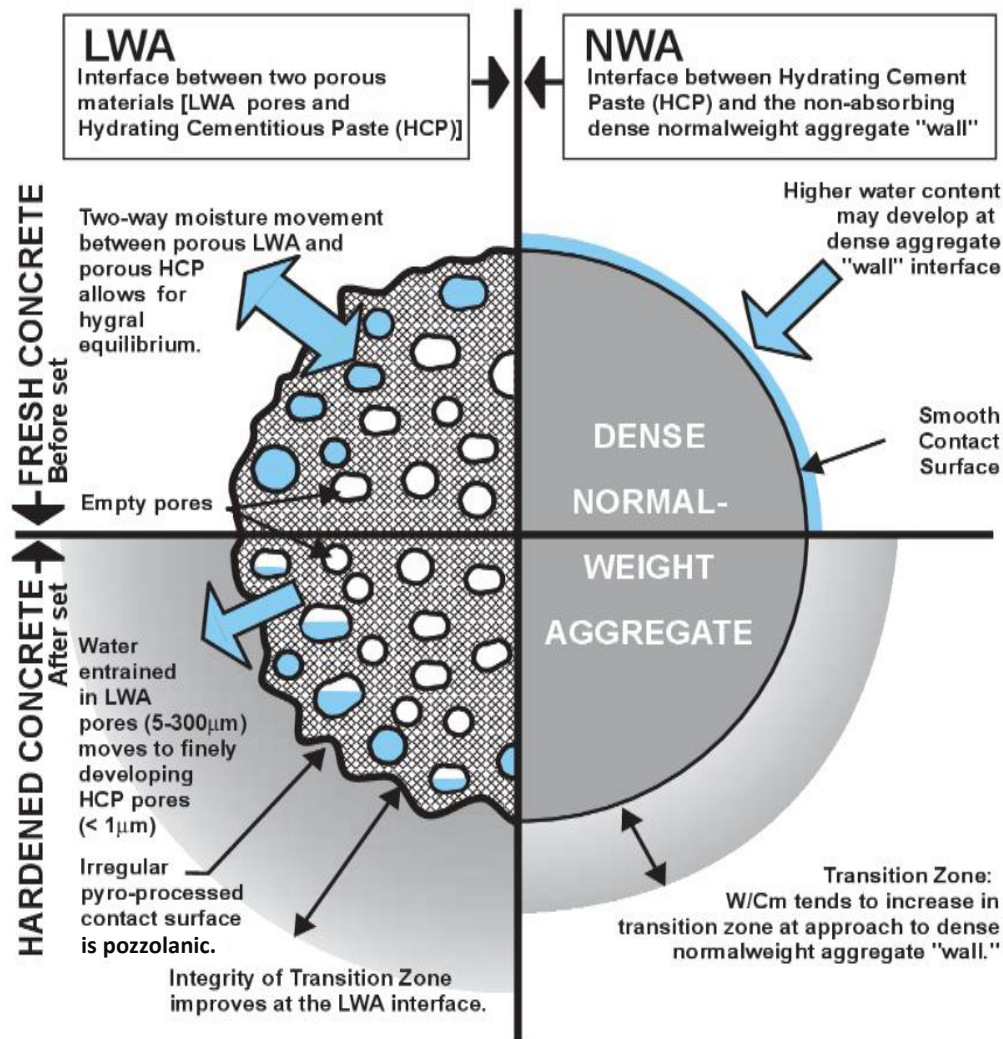


Figure 7 Interface between lightweight aggregate (expanded clay) and matrix. Reproduced from [133, 137]


4. Effect of curing on carbonation resistance

Curing has an important effect on the carbonation resistance of concrete as it influences the pore structure and the degree of hydration of the cement, and consequently the amount of carbonatable material. The effect is less pronounced for plain PC concrete than for concrete with SCMs due to their slower reaction. Nevertheless, if adequate precautions are taken, e.g. sufficiently long curing and reduced w/c ratio, the depth of carbonation of concrete with binders containing SCMs may be the same as for concrete with PC [138]. Thus, the type of curing, its duration and temperature as well as other environmental and geometrical conditions like wind speed, size of structural element, and type of formwork need to be considered when estimating the impact on the carbonation resistance. Typical curing methods in practice are in air, moist, sealed, heat or steam curing, or the use of a chemical curing compound. The type of curing drastically affects the carbonation rate as shown by [139], who reported that the carbonation rate of water-cured samples was only 17% of the carbonation rate of air-cured samples (28 days), in a chamber filled continuously with 100 % CO₂ (carbonation measurements between 1-28 days).

In the laboratory, curing at > 95 % RH is common practice but is not representative for on-site hydration circumstances. The duration of curing on construction sites is typically a few days. For

1 varying replacement levels by FA and BFS, researchers have reported that the carbonation coefficient
 2 increases dramatically when shortening the curing periods from 7 to 1 day [140-142]. In [143], it is
 3 shown for concretes (grades C16/20 to C30/37) with blended cements (CEM II A-M and CEM IV A-M)
 4 based on natural carbonation tests for 1 year, how the period of wet curing, and the type of curing
 5 (wet curing vs. use of a membrane), affect the carbonation rate and therefore the service life of
 6 reinforced concrete structures. In that study, an extension of the wet curing period from 1 to 3 days
 7 increased the predicted service life by a factor of more than 2, and a factor of 4 improvement is
 8 gained by increasing from 1 to 7 days of wet curing. It was found that 3 days of curing should be
 9 enough for replacement levels of less than 30 wt.% for FA or 50 wt.% for BFS [141-142]. For higher
 10 replacement levels, longer curing periods are desirable.

11
 12 For accelerated carbonation testing in the laboratory, longer curing periods are in most cases
 13 recommended to obtain a more realistic and representative microstructure before subjecting the
 14 concrete to high CO₂ levels. Continuous curing over periods longer than 1 month can significantly
 15 increase the durability of BFS concrete (50-85 wt.% cement replacement), but periods longer than 3
 16 months were found not to considerably affect the resistance to carbonation anymore [52]. In
 17 contrast, Sailio [144] showed that the carbonation depth of systems containing slag cement, or
 18 30 wt.% FA, seems to decrease progressively and continuously also with curing times exceeding 3
 19 months. However, no significant effect of wet curing beyond 3 months was observed for Portland
 20 cement systems containing 10 wt.% or 25 wt.% MK [143-145]. Atis [146] reported for concrete with
 21 FA (50 wt.% and 70 wt.% cement replacement) the importance of a longer initial curing before
 22 testing at 5 vol % CO₂ (testing from 3 days up to 3 months of moist curing), which resulted in lower
 23 carbonation depths. Burdon [87] found that the carbonation rate significantly increases with
 24 increasing FA replacement between 30-50 wt.% for the same w/b ratio, but that the relative
 25 difference to PC concrete decreases with moist curing time. Parrott [79] examined the effect of 15-
 26 25 wt.% LS replacement (at the same w/b=0.59) on carbonation rate on samples water cured for 1, 3
 27 and 28 days prior to natural carbonation exposure. Compared to plain cement, the carbonation rate
 28 increased with increasing LS replacement; the difference was smallest for 1-day curing for both
 29 exposure times under temporal variable outdoor conditions, see Figure 8. With increasing exposure
 30 time and therefore decreasing moisture and temperature variations at the carbonation front, the
 31 differences decrease compared to plain PC after 1.5 years of exposure.
 32
 33
 34
 35
 36
 37
 38
 39

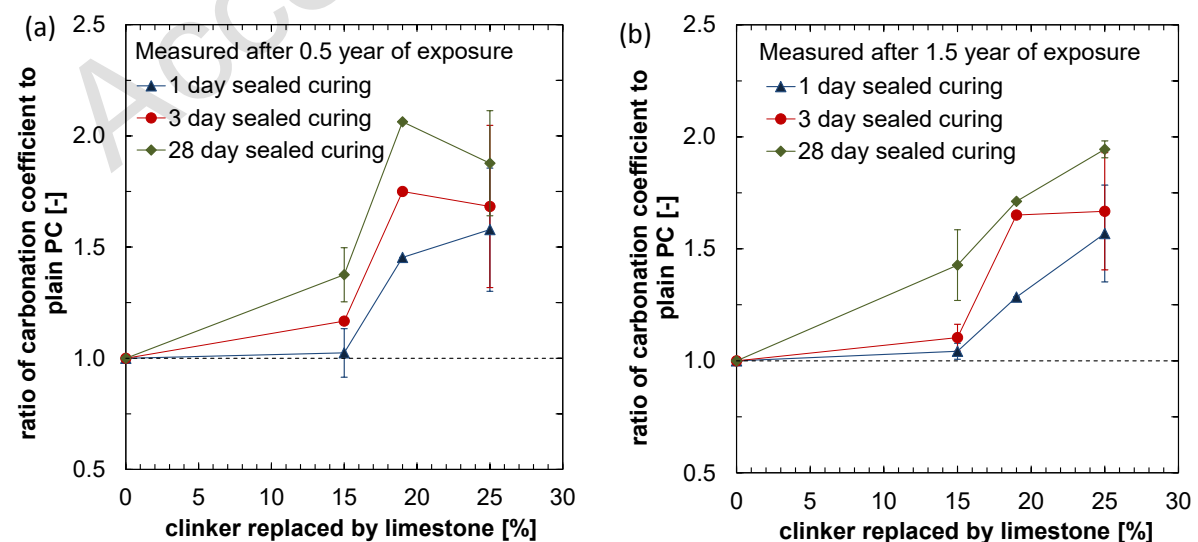


40
 41
 42
 43
 44
 45
 46
 47
 48
 49
 50
 51
 52
 53
 54
 55
 56
 57
 58
 59
 60
 61
 62
 63
 64
 65

Figure 8 Effect of sealed curing duration on carbonation rate for different limestone replacement levels, compared to PC [79] concretes for the same w/b ratio

Also, the temperature during curing has an impact on the carbonation resistance. Borges et al. [75] concluded that, for a curing period of 90 days, raising temperature from 20°C to 60°C reduced the carbonation rate by 10 – 30 % for cement pastes with high replacement levels by BFS. Li et al. [148] investigated the effect of high temperature curing (water curing at 20°C, 40°C, 60°C, 80°C until equal strength grade) of concrete made of PC and with FA, FA and BFS, and SF. The minimal carbonation depth was found for samples cured at 60°C, pronounced for blended cements and less pronounced for PC.

In different models e.g. fib MC 2006 bulletin 34 [149] an execution transfer parameter is introduced to take into account the influence of curing on the effective carbonation resistance. It should be noted that all actions preventing premature desiccation of the concrete close to the surface are here considered as curing measures, and that no distinction is made for the type of curing and type of binder. However, Van den Heede et al. [85] emphasise the importance of a binder-dependent curing parameter. The effect of curing on carbonation rate as obtained from [42, 79, 91, 147, 150-152] has been evaluated in Figure 9. It can be seen that for slag and LS blended cements, increasing curing time from 7 to 28 days is less effective with regard to improving carbonation resistance, despite the expected further reaction processes involving LS and slag with time [66]. In contrast, the FA blended samples showed a pronounced reduction of carbonation rate when increasing curing from 7 to 28 days, especially for the samples exposed outside under sheltered conditions with variable RH and temperature (exposed samples). It should be mentioned that moisture conditions in sheltered small samples differ from large structural elements; i.e., more homogeneous micro- and macro-climates in small samples than in structural elements may lead to different moisture transport processes.

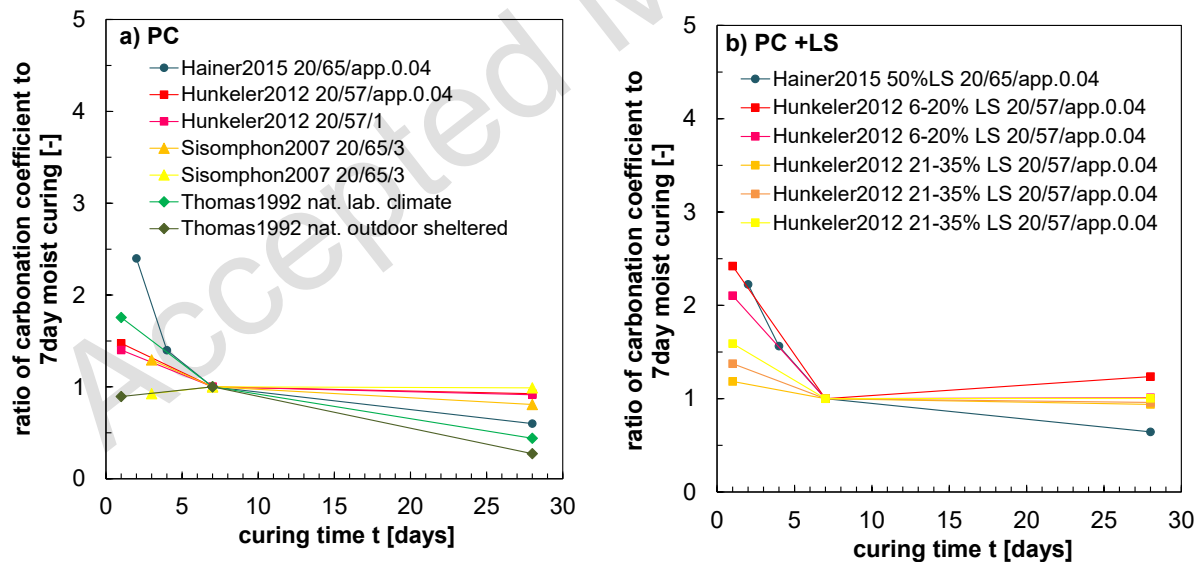

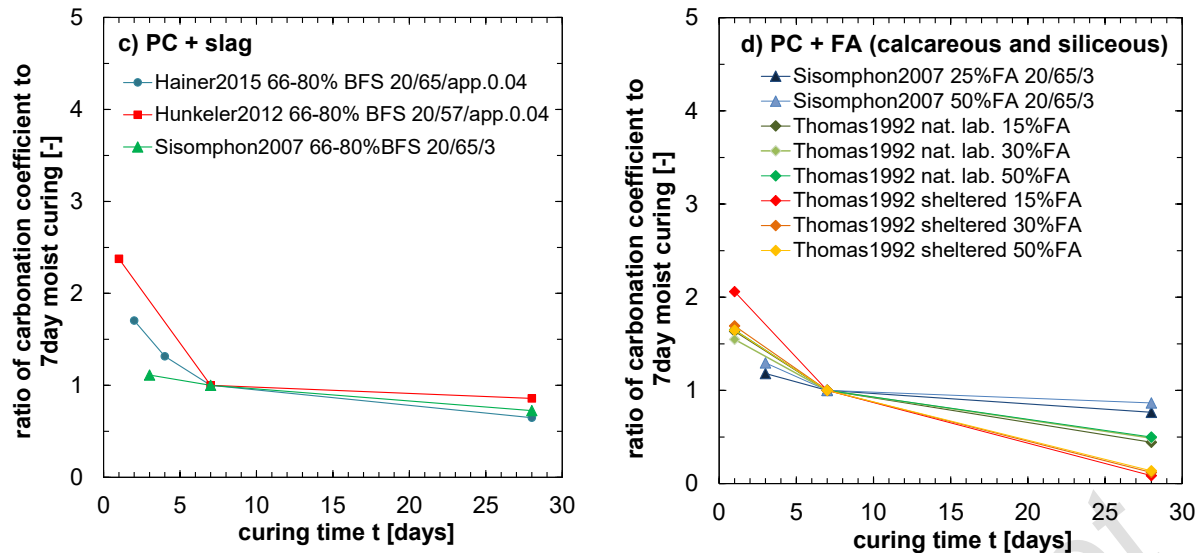


Figure 9 Increase in carbonation resistance in dependency of moist curing time relative to 7 days curing for (a) PC, (b) PC with LS addition (c) PC with BFS addition (d) PC with FA addition. Data from [42, 79, 91, 147, 150-152]; i.e. 20/65/3 indicates T [°C] / RH [%] / CO₂ [vol.-%] where the climate conditions are given in the original literature source.

5. Effect of relative humidity, temperature and CO₂ concentration on carbonation

5.1. Relative humidity and temperature

Carbonation of cementitious materials occurs when CO₂ diffuses through the material and dissolves in the pore solution where it reacts with the solid phases. At very low RH, there is not enough water in the pores to dissolve CO₂ for the chemical reaction to happen. At very high RH, the pores become saturated and consequently the diffusion of CO₂ is slowed down significantly. For Portland cement-based materials, the carbonation rate at 20°C reaches maximum values at RH between 40 % and 80 % [38-39, 153-155]. This RH range is quite large because the literature results relate to different CO₂ concentrations with various preconditioning conditions (temperature and relative humidity, duration) and different curing times, as well as different material compositions (paste vs. mortar, water-to-cement ratio). In recent studies, the fastest carbonation has been observed at approximately 50-55% RH for plain cementitious materials; the carbonation coefficient of plain cementitious material is reduced by a factor of 0.6 ± 0.4 , 0.5 ± 0.4 and 0.4 ± 0.4 if the relative humidity increases to 70%, 80% and 90% respectively [43-44, 72]. The carbonation coefficient has been observed to be reduced to zero in the range 10 to 30% RH [72]. These broad ranges and various conditions involve varying degrees of saturation of the test specimens. For example, in the accelerated carbonation tests for both French standard XP P 18-458 [159] and European standard EN 12390-12 [157], the RH during carbonation is fixed at 57 ± 3 %, while conditions specified for sample preconditioning are different.

For materials containing SCMs, the RH range at which carbonation proceeds the fastest may differ from the values determined for Portland cement systems (Figure 10). Drouet et al. [72] found the most rapid carbonation RH around 33 % for CEM V/A paste (containing slag and fly ash) carbonated at a CO₂ concentration of 50 % at 20 °C, which is a much lower RH value than was obtained for plain Portland cement paste (CEM I) in the same study, which was around 50 %. Leemann and Moro [44] studied mixtures with different SCMs: BFS, SF, FA and LS. They found that increasing RH from 57 % to 70 % or 80 %, at a CO₂ concentration of 4 % not only decreases the carbonation coefficient but also changes the ranking of the different concrete mixtures. The authors explained these differences via

the effect of pore size effect on capillary condensation. For cementitious materials with a higher amount of fine pores, such as those containing blast furnace slag and pozzolans, the pore volume filled with water due to condensation is higher at a fixed value of RH [72, 158-159]. De Ceukelaire et al. [160] found a maximum carbonation progress at 50 % RH for concretes containing BFS, at different CO₂ concentrations. A decrease of carbonation coefficient with increasing RH (40 % to 60 % to 80 %) for different binders containing SCMs was also reported in [25].

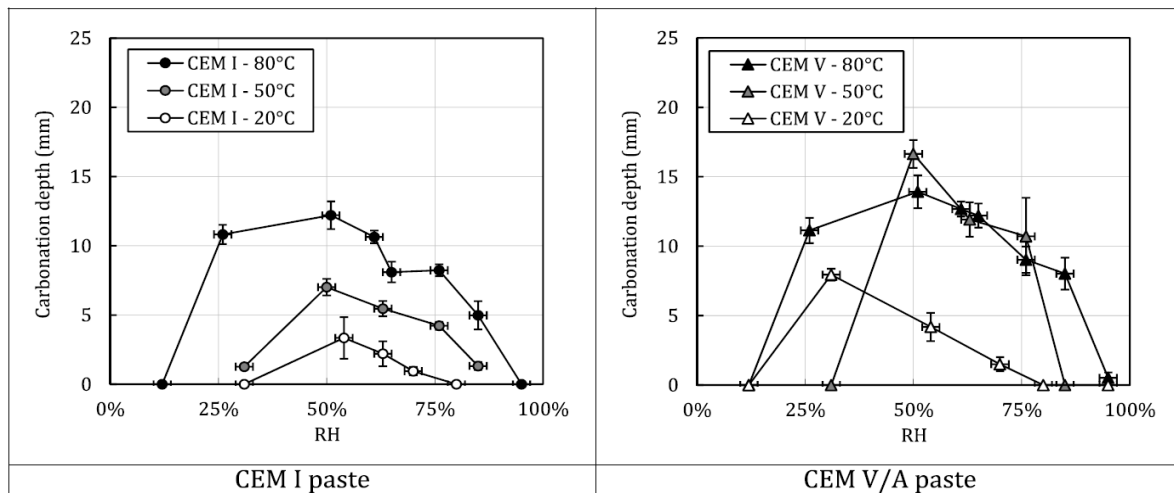


Figure 10 7-day carbonation depth as a function of RH, for CEM I and CEM V/A pastes with w/b = 0.40, at a CO₂ concentration of 50 % [72].

It should be noted that apart from the externally imposed humidity conditions, the applied CO₂ concentration during carbonation testing could also affect the internal humidity and saturation degree of cementitious binders. According to [161], excessive water production during carbonation at high CO₂ levels could have a pore blocking effect. Hence, the humidity range at which carbonation is most rapid is most probably dependent on CO₂ concentration for any concentrations above the natural atmospheric levels.

In addition to RH, temperature is a main external parameter that affects carbonation of cementitious materials. Higher temperature accelerates carbonation as chemical reactions and diffusion are faster. However, higher temperature also decreases the solubility of portlandite and CO₂ in water [2, 162-163].

The carbonation coefficient increases by a factor of approximately 1.1 from 20°C to 30°C and from 30°C to 40°C for plain and for blended cements (e.g. limestone and low calcium FA). For calcined clay blended cements, a higher increase of the carbonation coefficient was determined (by approximately a factor of 1.3) [25]. The decrease in carbonation coefficient when the temperature decreases from 20°C to 10°C is less pronounced (multiplicative factor of 0.95) [25, 38, 164].

Temperature also affects the stability of the calcium carbonate polymorphs that precipitate during carbonation. Tai and Chen [165] have shown that the formation of these polymorphs by precipitation from a CaCl₂/Na₂CO₃ solution is a function of pH and temperature (Figure 11). At high pH, calcite is the main polymorph regardless of temperature (24°C and 58°C). At lower pH, the dominant polymorph changes as a function of temperature; for high temperature (58°C), aragonite will be the main polymorph to precipitate while for ambient temperature (24°C) vaterite has been observed. Drouet et al. [72] have studied the effect of both temperature and RH on the stability of calcium carbonate polymorphs. They found that the two metastable forms of calcium carbonate (aragonite and vaterite) were observed in varying amounts for both Portland cement and CEM V pastes. The

amount of aragonite and vaterite increased when the RH decreased. This increase is more significant at higher temperature.

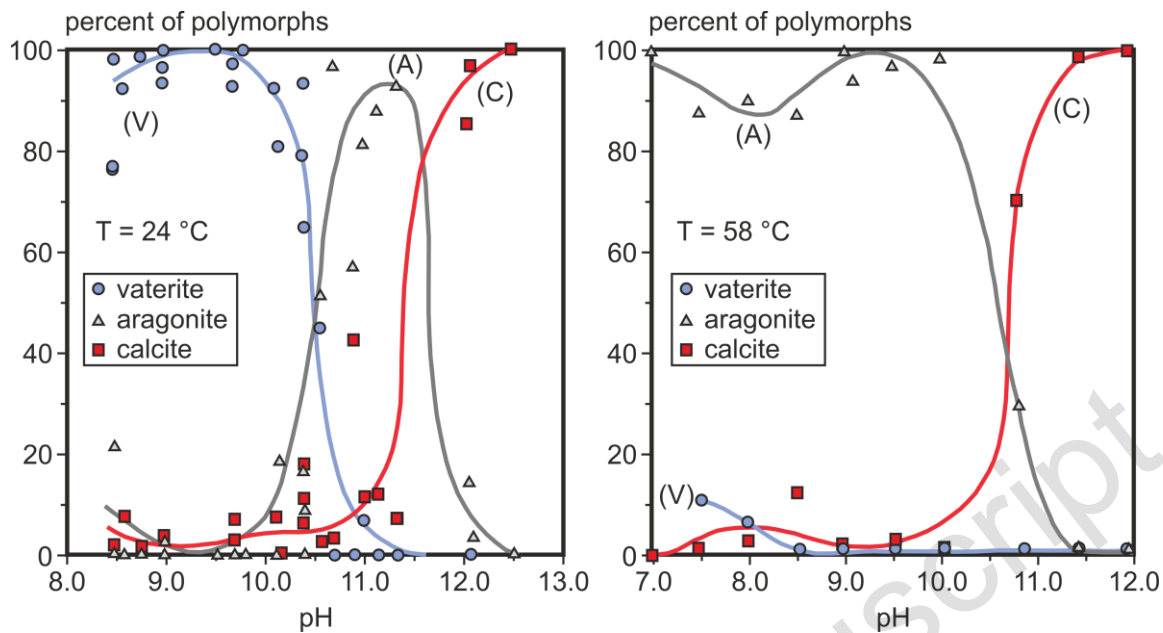


Figure 11 Polymorphs of calcium carbonate observed to precipitate from a 1:1 molar mix of CaCl_2 and Na_2CO_3 at a supersaturation of 5.5, according to pH (controlled by NaOH or HCl addition) and temperature [165].

One key aspect is that if the temperature increases without maintaining a fixed RH, a part of the water from the specimen evaporates and the carbonation could be lower in spite of the increased temperature. The literature results reflect these contradictory effects. Drouet et al. [72] observed that the carbonation depth of Portland cement paste increased continuously with temperature at a fixed RH, whereas the carbonation depth of CEM V/A reached a maximum at around 50°C.

These findings are particularly important considering that when evaluating carbonation resistance of concretes according to accelerated carbonation standardised testing methodologies, the exposure temperature is generally set to be between 20 - 25°C, which is not representative of all climates, and can yield carbonation results that can be far from being a realistic representation of what can be expected of concretes with SCMs under natural carbonation conditions in the field.

5.2. CO_2 concentration

Increasing the CO_2 concentration is a common approach to accelerate carbonation for testing purposes, and the results of accelerated tests are often used as performance criteria for validation of new concrete mixes and service life prediction models. Different factors and equations have been proposed to transform the results from accelerated carbonation testing to predict natural carbonation [151, 166-167]. However, there is still need for research to define relations applicable for different concrete compositions [142].

From a thermodynamic viewpoint, increasing the CO_2 concentration should not change the expected phase formation in plain Portland cement [28, 168]. Nonetheless, experiments have shown that:

- The C-S-H carbonation rate increases with the applied CO_2 concentration [32]. The proportion of CaCO_3 originating from portlandite and C-S-H carbonation changes significantly from 1 % CO_2 onwards, in favor of C-S-H carbonation [169].

- A CO₂ concentration above 3 % favours formation of aragonite and vaterite [26, 170] due to pH reduction because of increased amounts of dissolved CO₂, [171], (Figure 11).
- A CO₂ concentration above 10 % leads to incomplete reaction of portlandite, e.g. due to a fast surface reaction causing an overgrowth of portlandite with calcite, which permanently prevents further portlandite carbonation [28, 170, 172]. A high CO₂ concentration also lowers the pH and thus the solubility of CO₂ in water or in solutions containing alkali hydroxides (such as cement pore fluids), leading to the formation of more HCO₃⁻ and less CO₃²⁻ [2, 171].
- However, in cementitious materials with limestone fillers only calcite is formed [168, 172-173]. In high-volume fly ash binder systems, the preferred precipitation of aragonite and vaterite over calcite could not be confirmed for 1 % and 10 % CO₂, but was evident at 0.03-0.04 % CO₂ [169].
- For a high CO₂ level, the amount of water produced during carbonation could be more than the porous matrix is capable of expelling in the same time interval. The time needed to establish a condition of equilibrium again is believed to slow down further carbonation [161, 174].
- The correlation between accelerated and natural carbonation coefficients decreased from laboratory to sheltered (R² = 0.69) and finally to unsheltered exposure (R² = 0.15). Key parameters to consider for natural carbonation are temperature, relative humidity and amount of precipitation [44, 96]. The correlation strongly depends on the microclimatic conditions (i.e. RH, orientation, wind, precipitation).

Rozière et al. [175] found correlation coefficients of only 0.45-0.67 when correlating natural to accelerated carbonation at 50% CO₂, although the ranking of the concrete types considered remained similar. This is in line with other studies [38-39, 176]. On the other hand, several researchers [175-177] noticed small changes in ranking between mixes when carbonated at 1%, 4% or 10% CO₂. Increasing the RH at 4 % CO₂ from 57 % to 70-80 % RH also affected the ranking for carbonation resistance, probably as the result of a different w/c and pore size distributions of the concrete types tested [44].

As the pore structure and the ratio w/CaO_{reactive} are cement-specific, the correlation between accelerated and natural carbonation depends strongly on the binder [150, 179]. Hainer 150 points out that clinker-reduced concrete shows relatively higher carbonation rates under field than under accelerated conditions. In contrast, Leemann et al. [96] and Bernal et al. [171] noted that accelerated carbonation is more aggressive than natural carbonation for concrete with SCMs. A detailed comparison of literature data is challenging due to the many different storage and exposure conditions assessed by different authors, and is beyond the scope of this review.

The increase in carbonation coefficient with increasing CO₂ concentration (CO_{2acc}) compared to natural CO₂ concentration (CO_{2nat}) is in most experimental investigations lower than what is expected from the theoretical relationship $\sqrt{CO_{2acc}/CO_{2nat}}$ [38, 96, 151]. According to these investigations, the deviation from the theoretical relationship is more pronounced for plain cements and cements with LS than for slag blended cementitious materials. It has been indicated [42] that a formula in which the carbonation depth relies on the square-root of the CO₂ concentration in play should be reliable up to 3 % CO₂. Yet, even from 1 % CO₂, the relationship does not seem to hold [169]. Given that this is the case, the assumption of pure diffusion control of carbonation kinetics appears to break down at higher CO₂ concentrations, and this needs more detailed investigation to determine what is the true rate-controlling step if accelerated test results are to be used to predict natural carbonation rates in standards and codes.

6. Effect of carbonation on porosity and transport properties

6.1. Porosity and pore size distribution

Porosity of cementitious mixtures plays an important role in relation to the carbonation resistance, as it is directly linked to the ingress of CO_2 . When investigating porosity, different aspects need to be considered, for instance pore volume, pore size distribution, tortuosity and interconnectivity. Castellote et al. [31] reported pore clogging and formation of dense, carbonated areas as the main cause for limited accelerated carbonation rates in plain PC pastes. Hyvert et al. [32] and Anstice et al. [180] confirmed a decreasing total porosity with an increasing CO_2 concentration, and Knöfel et al. [173] recorded a refinement in pore size distributions using mercury intrusion porosimetry. Mortars with plain PC showed increased amounts of gel pores, while the fraction of capillary pores decreased to around 10 %. The decrease in total porosity, and pore clogging, are attributed to the formation of calcium carbonate which takes up a larger volume than the initial hydration product $\text{Ca}(\text{OH})_2$. Several studies [24-25, 181] also identified a decrease in the total porosity of plain cement pastes due to carbonation in combination with a coarsening of the capillary pores. For BFS-containing binders a decrease in gel porosity but an increase in capillary pores (coarsening of the pore structure) has been reported in [26, 83, 182]. Similar are the findings at high FA or SF replacement levels [26, 27, 182-183]. This coarsening is usually associated with C-S-H/C-A-S-H carbonation. The higher the amount of reactive alumina provided by the SCM, the larger the increase in porosity on carbonation, due to the decomposition of AFm and AFt phases [75].

According to [106] the decrease in micro-pores is attributed to clogging by CaCO_3 from C-S-H carbonation, while the reduction of macro-pores is mainly attributed to pore clogging by CaCO_3 from portlandite carbonation. However, the increase in meso-pores has been interpreted differently by various authors, and the potential causes are listed in [106] as follows:

- (i) porous structure of silica gel formed during carbonation
- (ii) micro-cracks in the CaCO_3 layer surrounding portlandite crystals due to the hydric gradient, and
- (iii) micro-cracks induced by carbonation shrinkage.

The more pronounced increase in meso- and macro-pore volumes for FA, SF and slag blended cements upon carbonation can also be attributed to the lower Ca/Si ratio of C-S-H/C-A-S-H formed in these blended cements, by enabling the entrapment of alkalis reducing the amount of hydroxyl ions and also the increased carbonation shrinkage for Ca/Si less than ~ 1.3 [34].

Also Shah et al. [25] reported that because the replacement of PC with Si-rich SCMs results in less portlandite, the decalcification of the C-S-H present leads to an increase of the total porosity in combination with a coarsening of the pore structure. Consequently, the extent of pore coarsening and the increase of total porosity during carbonation depend on both the amount and the type of SCMs.

Prior to carbonation, SCMs can increase the porosity of cementitious materials at early ages but contribute to the development of a more refined pore structure over the time [184]. These two opposing effects will affect the resistance to carbonation of concretes depending on the type of SCM used and its ability to cause pore refinement, the amount of cement replacement, and the reaction degree as a function of time. Upon carbonation it is observed that the total porosity increases with increasing SCM replacement ratios [75, 82]. For example, when SF is used in concrete, Kulakowski et al. [185] found a 'critical threshold' related to the amount of replacement and w/b ratio: cement

replacement up to 10 wt.% by SF will result in an increased carbonation resistance. However, if SF replacement is higher than 10 %, this will lead to more carbonation.

The data collected in Table 1, from [82], show an increasing total porosity prior to carbonation when the replacement level by FA is increased from 0 to 30 wt.% and 60 wt.% substitution. Upon carbonation, the total pore volume decreases in all cases. The decrease of the pore volume in the MIP-accessible range (3 nm to 500 μm) during carbonation seems to be lower at higher replacement levels for the MIP measurements, and similar in the case of GRAM (gamma ray attenuation method) measurements (accessing coarse pores size 200 μm to 1000 μm [186]).

Table 1 Total porosity of cement paste (CN stands for w/c ratio of 0.45 and CP for w/c = 0.60) as a function of the replacement level by fly ash before and after carbonation measured with mercury intrusion porosimetry (MIP; pore size ~3 nm to 500 μm) and gamma ray attenuation method (GRAM; pore size ~200 μm to 1000 μm [186]); samples were cured for “at least” 6-11 months (minimum 6 for PC, 11 for blends), then preconditioned for 56 days at 45°C in an oven, plus 56 days at 20°C, 62±5% RH and carbonated at 3% CO₂. Data from [82].

Characteristics		Units	CN	CN30	CN60	CP	CP30
Fly ash		vol.%	0	30	60	0	30
Fly ash		wt.%	0	23	51	0	23
w/(c + fly ash)		-	0.45	0.45	0.45	0.6	0.6
w/c		-	0.45	0.64	1.13	0.6	0.86
<i>Non-carbonated</i>	Porosity (MIP)	%	19.2 ± 0.7	29.2 ± 1.1	37.8 ± 1.0	31.0 ± 2.1	42.7
	Porosity (GRAM)	%	37.9 ± 0.7	47.4 ± 1.2	52.9 ± 1.7	47.1 ± 0.6	54.9 ± 1.0
<i>Carbonated</i>	Porosity (MIP)	%	12.3 ± 1.1	23.4 ± 2.7	36.4 ± 1.2	23.1 ± 3.1	34.2 ± 2.1
	Porosity (GRAM)	%	30.2 ± 1.1	36.0 ± 0.8	46.5 ± 0.9	36.5 ± 1.3	48.8 ± 0.8

For ternary systems with 50 % clinker, 31 % calcined clay, 15 % limestone and 4 % gypsum, a clear increase of the total porosity was observed in Figure 12a [24], under both natural and accelerated (3 %) carbonation conditions. An experimental study on the use of slag in pastes [24] showed that an increase in total porosity is detected when the clinker replacement is 70 wt.%. The increase in capillary porosity due to carbonation further accelerates diffusion of detrimental substances and will therefore make concrete with SCMs more vulnerable to deterioration by coupled mechanisms.

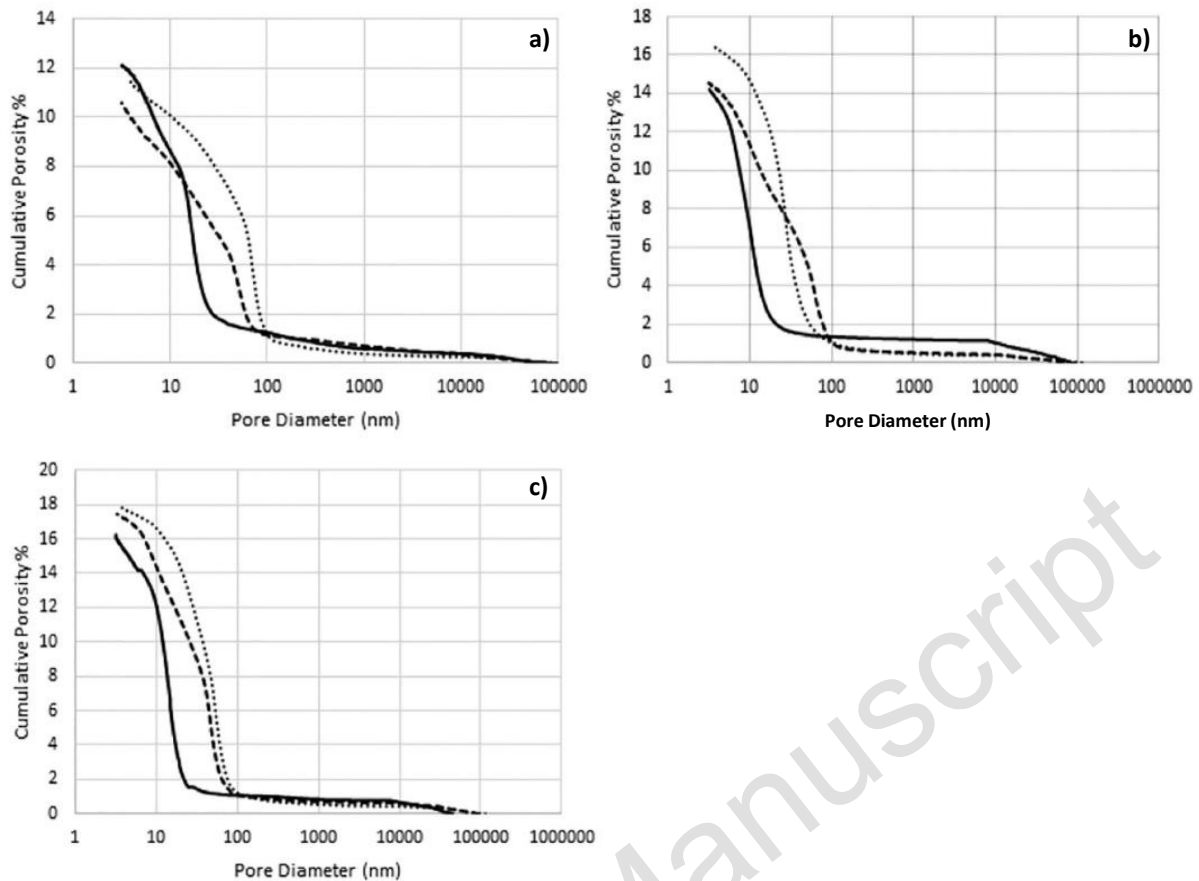


Figure 12 Mercury intrusion curve of uncarbonated cylindrical paste samples (solid line) compared with cylindrical paste samples carbonated in natural (dotted line) and accelerated conditions at 3% CO₂ (dashed line) cured in lime water for 120 day and preconditioned for 15 day at 60 % RH and 27°C; a) Cumulative intrusion curve of PC, b) Cumulative intrusion curve of 70 % PC + 30 % FA, c) Cumulative intrusion curve of limestone calcined clay cement (50% clinker, 31% calcined clay, 15% LS, 4% gypsum) from [24].

6.2. Transport properties

The alteration of the pore structure upon carbonation of plain and blended cementitious materials affects the vapour sorption/desorption isotherms, gas and moisture transport. The transport of CO₂ through cementitious materials is one of the governing parameters affecting carbonation rate and is strongly affected by moisture conditions as was discussed above. The degree of water saturation under steady-state and isothermal conditions has been determined by means of water vapour sorption /desorption tests [38, 74, 187]. Figure 13 shows sorption isotherms for plain and blended cement pastes. A benefit of adsorption/desorption isotherms is the provision of information about changes in micropores < 10 nm, which are less well reflected by MIP (molecule radius of H₂O is 0.1 nm, of nitrogen N₂ is 0.215 nm and both are smaller than that of mercury; it avoids also the risk of microcracking in MIP [106]).

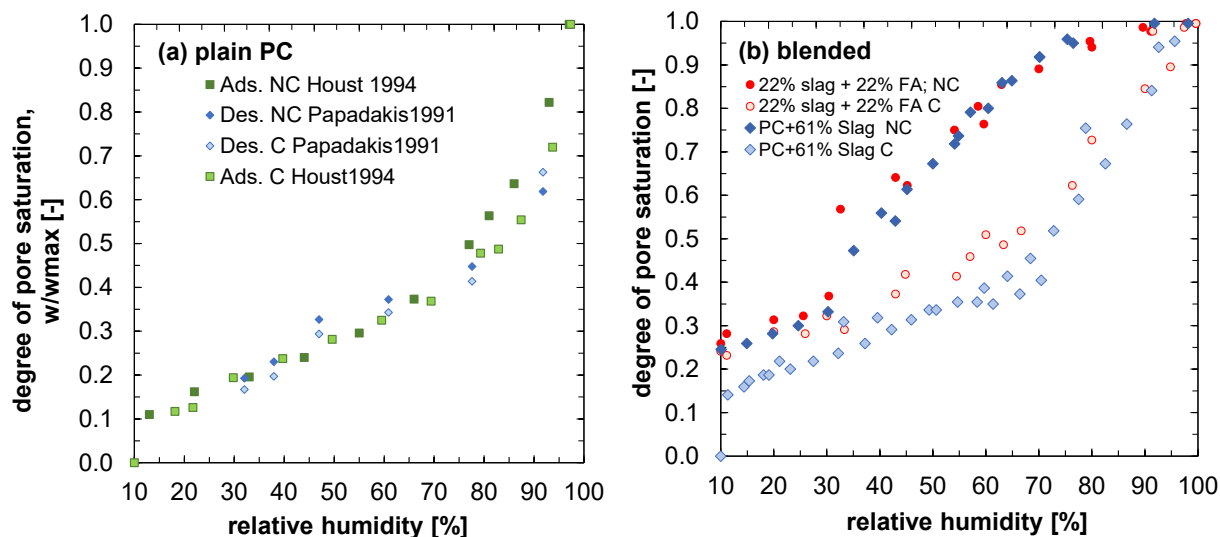


Figure 13 Effect of carbonation on degree of pore saturation (adsorption (Ads.)/ desorption (Des.) isotherms) of plain PC mortars with $w/c = 0.5$ from [38, 187] (a) and desorption isotherms with 22% slag + 22% FA (circle) or 61% slag (rhombus) blended mortars with $w/c = 0.4$ from [74] (b) for non-carbonated (NC) and carbonated (C) samples

Papadakis et al. [38] and Houst et al. [187] observed no alteration in water saturation degree at > 50 vol.-% CO_2 for plain cementitious materials. Borges et al. [75] found a small alteration at low RH when applying 3 vol.-% CO_2 to plain PC, indicating an increase in micro-porosity, compared to a pronounced alteration of pore saturation in FA and BFS blended cementitious materials upon carbonation, indicating an increase in micro-, meso- and macro porosity. Hyvert [188] determined a notable alteration of the water sorption isotherm for plain PC, and an even more evident alteration for blended cementitious materials. The reduced degree of saturation in carbonated samples at $50\% \leq RH \leq 85\%$ affects effective CO_2 diffusion coefficients in two ways: (i) the coarsened pore structure opens the path for CO_2 diffusion, as the capillary pores are the decisive pores for high diffusion rates; and (ii) the degree of saturation is reduced in the relative humidity ranges expected under common site conditions.

Effective CO_2 diffusion coefficients in non- and fully carbonated pastes, mortars and concretes have been determined experimentally under different conditions [21, 38-39, 44, 78, 105, 182, 187, 189-191].

Prior to carbonation it was found that the effective CO_2 diffusion coefficient decreases with:

- decreasing w/b (decreasing capillary porosity) [21, 39, 78, 105]
- increasing relative humidity above 40% RH, which increases the degree of water saturation [38, 105, 182, 187, 189]
- increasing PC replacement level by FA, SF or BFS, respectively increasing the fraction of the binder that is C(-A)-S-H [21, 78, 182, 189]
- increasing degree of hydration [182]

Upon carbonation the effective diffusion coefficient was found to:

- decrease in the case of plain cementitious materials and blends with portlandite or LS, with increasing ratio of portlandite carbonation [21, 38-39, 44, 78, 105, 182, 187, 189-191] for RH > 30% [182]
- increase with increasing cement replacement level by SF, FA, calcined clay, or mostly for BFS, due to increasing C(-A)-S-H carbonation [21, 78, 182, 190-191]. The difference becomes more pronounced with increasing degree of water saturation.
- Increase with carbonation degree at constant high RH (93%) for all mix design unless the water to cement ratio is very low (< 0.4) [191]

In water CO₂ diffusion coefficients have been found to be < 10⁻⁹ m²/s [192]. Water vapour diffusion coefficients are up to two orders of magnitude higher and increase with the difference in relative humidity, increasing w/b ratio and decrease with increasing replacement by SF or BFS [193]. As CO₂ is consumed by the carbonation reaction, CO₂ diffusion coefficients are often derived from O₂, N₂ or He diffusion coefficients [182, 187, 189]. The value of the corresponding CO₂ diffusion coefficient depends on whether the process is limited by the molecular mass (molecular diffusion dominating in larger pores) or by the Knudsen diffusion (i.e. diffusion in small pores, where the diffusion resistance is dominated by collisions with the pore walls). Furthermore, transport may also occur as surface diffusion, if the gas interacts by a succession of adsorption-desorption reactions with the surfaces [187, 194]. According to [187, 189] the CO₂ diffusion through non-carbonated cementitious materials is both a Knudsen and molecular diffusion process over the entire range of water saturation degree. However, upon carbonation this only holds for plain cements. For slag (approximately 80% replacement level) or FA and SF blended cements (replacement level > 44%) the pores can coarsen sufficiently that Knudsen processes involving pore walls are less important, and so transport instead becomes molecular diffusion controlled [182, 192].

Figure 14 shows effective O₂ diffusion coefficients ($D_{CO_2}/D_{O_2} \approx 1.4$) determined by Leemann et al. [21, 78] after oven drying. The determined effective diffusion coefficients are smaller or similar after carbonation for plain PC, portlandite-blended and limestone-blended cements, but higher for silica fume and slag blends, consistent with the preceding discussion for the rates of carbonation of cements containing these SCMs.

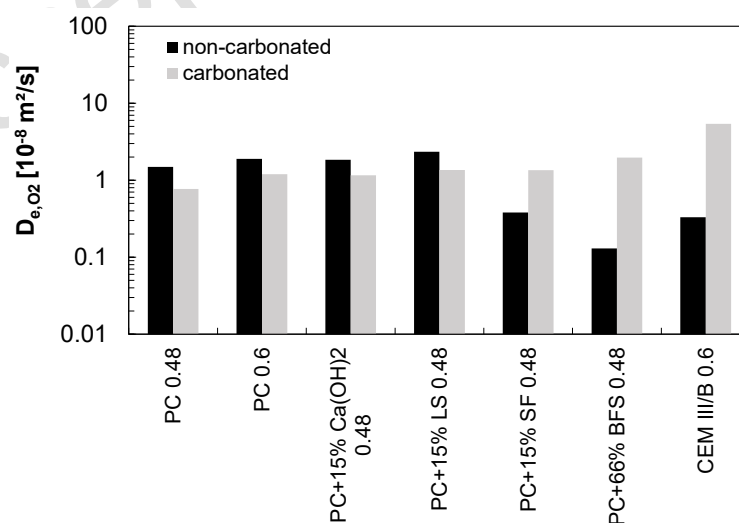


Figure 14 O₂ effective diffusion coefficients determined for non-carbonated and carbonated samples (age 28 days, oven dried) with plain and blended cements [21, 78] given with cement type, type and amount of addition as well as w/b e.g. PC 0.48 represents plain cement with w/b

0.48.

In some carbonation exposure conditions involving high pressure differences, both diffusive and convective transport coexist, and permeability may become dominant [195]. Gas permeability of carbonated and non-carbonated cementitious materials has been reported e.g. in [75, 104, 196-202] under the assumption of laminar flow. Gas permeability was in the range of $0.1 \cdot 10^{-9} \text{ m/s} < k_e < 10 \cdot 10^{-9} \text{ m/s}$. The gas permeability decreased with decreasing w/b ratio and increasing relative humidity or increasing cement replacement by SF, FA or BFS. Upon carbonation, gas permeability was increased or at least similar as prior to carbonation. But the increase was more pronounced for BFS blended cement systems with replacement levels of 75 wt.% to 90 wt.% [75, 198].

Water transport properties of cementitious materials have been reported e.g. in [55, 177-178]. The coefficient of water permeability is usually up to four orders of magnitude lower than the coefficient of gas permeability and may be related to gas permeability in dependency of the applied pressure head according to Klinkenberg explained in [203]. Upon carbonation the water permeability decreased in the case of plain and LS blended cementitious materials but increased for slag, FA and SF blended cementitious materials with moderate to high replacement levels [55,177-178]. Similarly, capillary sorption describes permeability of concrete where the pressure head is replaced by the capillary forces including water and water vapour transport [204-205].

Figure 15 shows coefficients of water sorptivity determined by Jansson et al. [101] for non- and partly-carbonated cementitious materials. He observed for non-carbonated samples a decrease in sorptivity from plain PC over blends with 20 or 35 wt.% FA, or 35, 50, or 65 wt.% BFS. After carbonation, the sorptivity was significantly reduced for PC samples, slightly reduced for samples containing 20 wt.% or 35 wt.% FA, or 35 wt.% or 50 wt.% BFS and increased for samples containing 65 wt.% BFS where a pronounced C-A-S-H carbonation can be expected. Similarly, a decrease in capillary sorptivity with carbonation has been observed for plain cement materials [204].

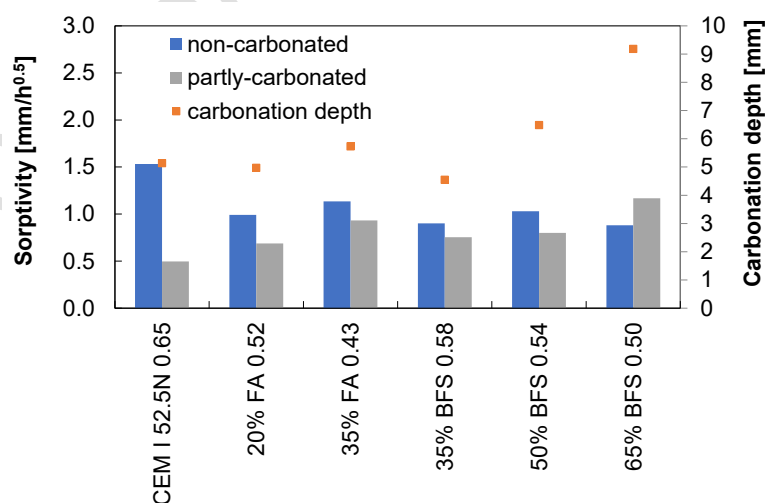


Figure 15 Coefficients of sorptivity reported in [101] for non- carbonated and partly carbonated concretes along with the carbonation depth (small squares), the notation shows the cement type respectively the amount and type of addition and the w/b ratio.

1 Gas permeability data shows an increase upon carbonation for most binder types, while both the
2 effective diffusion coefficients and the sorptivity coefficients show a decrease upon carbonation
3 except for SF or BFS blended cementitious materials. Hence it can be assumed, that the induced
4 pressure in gas permeability experiments alters the pore structure and mirrors mainly the transport
5 in larger pores. Moisture transport (sorption, capillary suction and water permeability) strongly
6 depends on the initial moisture conditions. Additionally, moisture transport may be altered by
7 chemical interaction of water with the cement, such as re-hydration of unreacted cement and
8 dehydrated cement pastes, changes of microstructure of C-A-S-H and secondary reaction products
9 (depending on the type of SCM used) during moisture transport, drying shrinkage induced by the
10 microscopic damage to pores due to capillary forces, and swelling associated with the water uptake
11 [204-209].
12
13

14 7. General remarks and conclusions

15 It is clear that the carbonation mechanism in cementitious systems containing SCMs differs from that
16 of plain Portland cement systems, due to the differences in the phase assemblage evolution, pore
17 structure, and pore solution chemistry. The main difference between these systems is the role of
18 portlandite carbonation, as it is expected that the amount of portlandite decreases at higher SCM
19 replacement levels. This is a consequence of the lower amount of Portland clinker in the cement
20 (which produces portlandite during its hydration) and the consumption of portlandite during the
21 pozzolanic reaction. Portlandite carbonation is the main contributor of released water during
22 carbonation, and usually leads to a reduction in pore size and total volume of meso- and macro-
23 pores due to CaCO_3 precipitation. However, the literature results are to some extent contradictory,
24 which may be due to the different measurement methods along with the different pore sizes
25 investigated. Portlandite carbonation may furthermore be incomplete due to the covering of
26 portlandite crystals by calcium carbonate.
27
28
29
30
31
32

33 With the reduced content of portlandite in SCM containing systems, carbonation will happen more
34 rapidly in the main CO_2 -binding phases, C-S-H in the case of using SF, and C-A-S-H phases in the case
35 of using BFS, FA, MK and other Al-containing SCMs. Carbonation of these hydrates seems to be the
36 main contributor to carbonation shrinkage (polymerisation shrinkage), especially for low Ca/Si C(-A)-
37 S-H and induces coarsening of pore structure upon carbonation and reduction of mechanical
38 strength. This is particularly critical when evaluating carbonation of concretes with SCMs, as
39 carbonation not only reduces the overall pH, but can also lead to a coarsening in pore structure,
40 consequently reducing the ability of these materials to withstand other forms of degradation by
41 chemical or physical attack.
42
43
44

45 Carbonation of C(-A)-S-H does not seem to contribute to the release of water prior to complete
46 polymerisation, but there is little investigation regarding structural changes and water released in
47 these hydrates upon carbonation, despite their role as the dominant binding phase present in
48 modern cements. There is an urgent need to determine the carbonation mechanism of Al substituted
49 C-S-H phases, and those containing alkalis (C-(N)-A-S-H), as a function of exposure conditions (e.g.
50 temperature, RH and CO_2 concentration), as these are the main CO_2 -binding phases identified in
51 SCM-containing cements, particularly those produced with BFS. The degree of crosslinking in these
52 gels and the reduced Ca/Si ratio compared with the C-S-H formed in plain PC systems will strongly
53 influence how carbonation proceeds.
54
55
56

57 There is little understanding in the role of secondary hydration products in the carbonation
58 resistance of systems with SCMs. In the case of using BFS, there is a consensus that Mg-Al layered
59 double hydroxides (LDHs) (e.g. hydrotalcite), whose formation is favoured when using BFS with
60
61
62
63
64
65

> 5 wt.% MgO, seem to play a key role in improving carbonation resistance in systems where higher quantities of these phases are formed. Understanding of the roles of other phases such as AFm and/or AFt phases, as well as zeolites present in some natural SCMs, in the carbonation process is imperative if next-generation binders are to be designed to favour formation of specific microstructural features to maximise their carbonation resistance.

There is no direct correlation between the carbonation rates identified in pastes, mortars and concretes with a given binder type, independent of the SCM used, which is consistent with the differences in the pore structure induced by the addition of aggregates and reduction of paste, and variation in degrees of saturations that can be achieved in these materials. All these factors will influence gas diffusivity and dissolution, and consequently the mechanism and kinetics of carbonation. Many studies centred on evaluating carbonation of SCM containing materials, particularly for new SCMs, are limited to the assessment of mortars. The carbonation coefficients obtained in those studies cannot directly be used to predict performance of concrete made with similar materials. It is important to understand the limitations of the tests conducted, which in the case of mortars can only give an indication of concrete performance but not a full description of the behaviour of the material.

It is well known that the carbonation exposure conditions (e.g. CO₂ concentration, RH and temperature) will strongly influence the kinetics of carbonation and the type and amount of carbonation products forming in different cementitious systems. In the case of plain PC systems this is well understood, and it has been suggested that the carbonation products forming when using > 3% CO₂ are not identical to those observed in naturally carbonated materials. This is of particular importance as several national accelerated carbonation standards prescribe the use of CO₂ concentration beyond this value, which can lead to misleading results.

The effect of temperature on carbonation is usually overlooked, particularly when evaluating carbonation under accelerated testing methods, as the majority of standard test methods have similar ranges of exposure temperatures. It is evident that temperature will play a key role in reaction kinetics and gas transport, which means that the results of accelerated carbonation tests using temperature conditions with no relevance to a specific region may not provide meaningful results to predict how these concretes will perform under real exposure conditions at a temperature very different from the testing temperature.

An overview of the effect of various parameters on the carbonation coefficient, as found in current literature as summarised in this review, is given in Table 2. It should be noted that these factors are strongly dependent on the composition of the material (type and replacement level of SCM) as well as on the carbonation conditions (i.e. CO₂ concentration and RH) and the preconditioning of the material prior to testing.

Table 2. Influences on the carbonation resistance based on literature data

Parameter		Carbonation coefficient	
Name	Range	increase ↑ decrease ↓ similar →	by a factor
w/b ¹⁾	0.4 → 0.65	↑	> 2.0 ²⁾ – > 3.5 ³⁾
w/CaO _{reactive}	0.4 → 0.9	↑	≈ 5
type of SCM (similar replacement level 25%), which affects the CaO content (FA,SF < BFS)	FA, SF → LS → BFS → PC	↓	≈ 2.3 (FA, SF), 1.9 (LS), 1.3 (BFS)

a/c ⁴⁾	change with factor 1.7 → 2.3	↑	1.1 ²⁾ , - 1.5 ³⁾
Concrete	changed to mortar	→ ↑	1.2-1.3
	changed to paste	↑	1.6-2.3
Coarse aggregate replaced by recycled aggregate		↑↓	< 1.0-2.0
Fine aggregate replaced by recycled aggregate		↑	3.75 ²⁾ , - 12.25 ³⁾
Lightweight aggregate		↓	-
Curing time	1 → 28 day	↓	1.1 – 2.5; ratio depends on SCM, degree of hydration, curing type
Curing temperature	20°C → 60°C	↓	ratio depends e.g. on type of SCM resp. on calcium carbonate polymorph formed
	60°C → 80°C	↑	
constant RH at 20°C	50-55% RH → 90 %RH	↓	0.4 ± 0.4 ²⁾
	50-55% RH → 10 %RH	↓	0.0 ²⁾
Temperature	20°C → 40°C	↑	1.13 ± 0.04 ²⁾ 1.17 ± 0.07 ³⁾
CO ₂ -concentration when related to natural CO ₂ by the square root relationship	> 1 – 100 vol.% CO ₂	↓ ⁶⁾	dependent on type and replacement level of SCM
O ₂ -, N ₂ - and CO ₂ -diffusion, H ₂ O-permeability	Upon carbonation	↑ ³⁾ ↓ ²⁾	Dependent on the moisture state
O ₂ -, CO ₂ - permeability	Upon carbonation	↑ ^{2), 3)}	
Capillary suction	Upon carbonation	↓ ^{2), 3), 5)}	0.3-0.9

¹⁾ water/cement+SCM, ²⁾ plain PC, ³⁾ blended cementitious material containing pozzolan or slag, ⁴⁾ aggregate/cement, ⁵⁾ except increase at high BFS replacement level

The preparation of this literature review enabled the members of RILEM TC 281-CCC to elucidate that there is a large number of open questions regarding carbonation of concretes with SCMs, although these materials are extensively, if not exclusively, used in modern infrastructure development. There is great scope for future research in this area, as questions at all scales need to be resolved to determine the best strategies to be implemented to increase the longevity of modern and future infrastructure concretes.

In an effort to answer some of these questions, the RILEM TC 281-CCC (WG1&2) is currently performing a round robin test to assess the effects on carbonation resistance in pastes, mortars and concretes produced with commercial SCM containing cements, when adopting different carbonation exposure conditions outlined in currently applied standards and test specifications.

Acknowledgements

The authors would like to thank all members of RILEM TC-281 CCC, for the valuable discussions regarding carbonation of concretes with SCMs, and their insight during the preparation and review of this paper.

Compliance with ethical standards

Funding

Participation of S.A. Bernal was partially sponsored by EPSRC through grants EP/R001642/1 and EP/T008407/1, and by the National Science Foundation (NSF) through award 1903457. The participation of J.L. Provis was sponsored by EPSRC through grant EP/T008407/1. N. De Belie and P. Van den Heede acknowledge the support of the Research Foundation Flanders (FWO) for funding a Bilateral Scientific Cooperation project with China (NSFC) - G0F3619N and for funding the postdoctoral fellowship of Philip Van den Heede (project No. 3E013917). Kosmas Sideris acknowledge TITAN S.A. Cement Company GREECE and Nordia S.A. Greece are thanked for providing materials. Charlotte Thiel acknowledges the support of the German research institution DFG. Elke Gryyaert and Hanne Vanoutrive would like to thank KU Leuven for the internal funding. Natalia Alderete would like to thank the Research Foundation-Flanders (FWO-Vlaanderen) for the financial support (12ZG820N).

Conflict of interest

The authors declare that they have no conflict of interest.

8. References

- [1] Kern M (1960) The hydration of carbon dioxide. *Journal of Chemical Education* 39:1-14. <https://doi.org/10.1021/ed037p14>
- [2] Stumm W, Morgan J (1995) *Aquatic Chemistry: Chemical Equilibria and Rates in Natural Waters*. John Wiley & Sons, New York
- [3] Adamczyk K, Prémont-Schwarz M, Pines D, Pines E, Nibbering ETJ (2009) Real-time observation of carbonic acid formation in aqueous solution. *Science* 326: 1690-1694
- [4] Dubina E, Korat L, Black L, Strupi-Šuput J, Plank J (2013) Influence of water vapour and carbon dioxide on free lime during storage at 80 °C, studied by Raman spectroscopy. *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy* 111: 299-303. <https://doi.org/10.1016/j.saa.2013.04.033>
- [5] Tai C, Chen FB (2004) Polymorphism of CaCO₃, precipitated in a constant-composition environment. *AIChE Journal* 44(8). <https://doi.org/10.1002/aic.690440810>
- [6] Fernández-Díaz L, Prieto M (2010) The role of sulfate groups in controlling CaCO₃ polymorphism. *Geochimica et Cosmochimica Acta* 74(21):6064-6076. <https://doi.org/10.1016/j.gca.2010.08.010>
- [7] De Choudens-Sánchez V, González LA (2009) Calcite and Aragonite Precipitation Under Controlled Instantaneous Supersaturation: Elucidating the Role of CaCO₃ Saturation State and Mg/Ca Ratio on Calcium Carbonate Polymorphism. *Journal of Sedimentary Research* 79(6): 363–376. <https://doi.org/10.2110/jsr.2009.043>
- [8] Rodríguez-Navarro C, Kudłacz K, Cizer Ö, Ruiz-Agudo E (2015) Formation of amorphous calcium carbonate and its transformation into mesostructured calcite. *CrystEngComm* 17:58-72. DOI: 10.1039/C4CE01562B

- 1 [9] Ostwald WZ (1987) Studien über die Bildung und Umwandlung fester Körper. Zeitschrift für
2 Physikalische Chemie 22:289-330. <https://doi.org/10.1515/zpch-1897-2233>
- 3 [10] Cizer Ö, Rodriguez-Navarro C, Ruiz-Agudo E, Elsen J, Gemert DV, Balen KV (2012) Phase and
4 morphology evolution of calcium carbonate precipitated by carbonation of hydrated lime. Journal of
5 Materials Science 47:6151-6165. <https://doi.org/10.1007/s10853-012-6535-7>
- 6 [11] Black L, Breen C, Yarwood J, Garbev K, Stemmermann P, Gasharova B (2007) Structural features
7 of C-S-H(I) and its carbonation in air - A Raman spectroscopic study. Part II: Carbonated phases.
8 Journal of the American Ceramic Society 90(2):908-917. [https://doi.org/10.1111/j.1551-
9 2916.2006.01429.x](https://doi.org/10.1111/j.1551-2916.2006.01429.x)
- 10 [12] Lagerblad B (2005) Carbon dioxide uptake during concrete life cycle - state of the art. CBI Report
11 2, Swedish Cement and Concrete Research Institute, Stockholm Sweden.
- 12 [13] Groves GW, Brough A, Richardson IG, Dobson CM (1991) Progressive changes in the structure of
13 hardened C₃S cement pastes due to carbonation. Journal of the American Ceramic Society
14 74(11):2891-2896. <https://doi.org/10.1111/j.1151-2916.1991.tb06859.x>
- 15 [14] Hargis CW, Lothenbach B, Müller CJ, Winnefeld F (2017) Carbonation of calcium sulfoaluminate
16 mortars. Cement and Concrete Composites 80:123-134.
17 <https://doi.org/10.1016/j.cemconcomp.2017.03.003>
- 18 [15] De Weerd K, Plusquellec G, Revert AB, Geiker MR, Lothenbach B (2019) Effect of carbonation on
19 the pore solution of mortar. Cement and Concrete Research 118:38-56.
20 <https://doi.org/10.1016/j.cemconres.2019.02.004>
- 21 [16] Shi Z, Lothenbach B, Geiker MR, Kaufmann J, Leemann A, Ferreira S, Skibsted J (2016)
22 Experimental studies and thermodynamic modeling of the carbonation of Portland cement -
23 metakaolin - limestone mortars. Cement and Concrete Research 88:60-72.
24 <https://doi.org/10.1016/j.cemconres.2016.06.006>
- 25 [17] Femenias YS, Angst U, Elsener B (2017) pH-monitoring in mortar with thermally-oxidized iridium
26 electrodes. RILEM Techn Lett 2:59-66.
- 27 [18] Houst Y, Wittmann F (2002) Depth profiles of carbonates formed during natural carbonation.
28 Cement and Concrete Research 32:1923-1930.
- 29 [19] Grengg C, Müller B, Staudinger C, Mittermayr F, Breininger J, Ungerböck B, Borisov S, Mayr T,
30 Dietzel M (2019) High-resolution optical pH imaging of concrete exposed to chemically corrosive
31 environments. Cement and Concrete Research 116:231-237
- 32 [20] Khan MSH, Noushini A, Castel A (2017) Carbonation of a low-calcium fly ash geopolymer
33 concrete. Magazine of Concrete Research 69(1):24-34. <https://dx.doi.org/10.1680/jmacr.15.00486>
- 34 [21] Leemann A, Pahlke H, Loser R, Winnefeld F (2018) Carbonation resistance of mortar produced
35 with alternative cements. Materials and Structures 51:114. [https://doi.org/10.1617/s11527-018-
36 1239-3](https://doi.org/10.1617/s11527-018-1239-3)
- 37 [22] Galan I, Glasser FP, Baza D, Andrade C (2015) Assessment of the protective effect of carbonation
38 on portlandite crystals. Cement and Concrete Research 74:68-77.
39 <https://doi.org/10.1016/j.cemconres.2015.04.001>
- 40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

- 1 [23] Cizer Ö, Van Balen K, Elsen J, Van Gemert D (2012) Real-time investigation of reaction rate and
2 mineral phase modifications of lime carbonation. *Construction and Building Materials* 35:741-751.
3 <https://doi.org/10.1016/j.conbuildmat.2012.04.036>
- 4 [24] Shah V, Scrivener K, Bhattacharjee B, Bishnoi S (2018) Changes in microstructure characteristics
5 of cement paste on carbonation. *Cement and Concrete Research* 109:184-197.
6 <https://doi.org/10.1016/j.cemconres.2018.04.016>
- 7 [25] Shah V, Bishnoi S (2018) Carbonation resistance of cements containing supplementary
8 cementitious materials and its relation to various parameter of concrete. *Construction and Building*
9 *Materials* 178:219-232. <https://doi.org/10.1016/j.conbuildmat.2018.05.162>
- 10 [26] Auroy M, Poyet S, Le Bescop P, Torrenti JM, Charpentier T, Moskura M, Bourbon X (2018)
11 Comparison between natural and accelerated carbonation (3% CO₂): Impact on mineralogy,
12 microstructure, water retention and cracking. *Cement and Concrete Research* 109:64-80.
13 <https://doi.org/10.1016/j.cemconres.2018.04.012>
- 14 [27] Morandea A, Thiéry M, Dangla P (2014) Investigation of the carbonation mechanism of CH and
15 C-S-H in terms of kinetics, microstructure changes and moisture properties. *Cement and Concrete*
16 *Research* 56:153-170. <https://doi.org/10.1016/j.cemconres.2013.11.015>
- 17 [28] Visser JHM (2014) Influence of the carbon dioxide concentration on the resistance to
18 carbonation of concrete. *Construction and Building Materials* 67:8-13.
19 <https://doi.org/10.1016/j.conbuildmat.2013.11.005>
- 20 [29] Sevelsted TF, Skibsted J (2015) Carbonation of C-S-H and C-A-S-H samples studied by ¹³C, ²⁷Al
21 and ²⁹Si MAS NMR spectroscopy. *Cement and Concrete Research* 71:56-65.
22 <https://doi.org/10.1016/j.cemconres.2015.01.019>
- 23 [30] Steiner S, Lothenbach B, Borgschulte A, Proske T, Winnefeld F (2018) Effect of relative humidity
24 on the carbonation rate of portlandite, calcium silicate hydrates and ettringite. 20. Internationale
25 Baustofftagung (ibausil), 12.-14. September 2018, Weimar Germany
- 26 [31] Castellote M, Fernandez L, Andrade C, Alonso C (2009) Chemical changes and phase analysis of
27 OPC pastes carbonated at different CO₂ concentrations. *Materials and Structures* 42:515-525.
28 <https://doi.org/10.1617/s11527-008-9399-1>
- 29 [32] Hyvert N, Sellier A, Duprat F, Rougeau P, Francisco P (2010) Dependency of C-S-H carbonation
30 rate on CO₂ pressure to explain transition from accelerated tests to natural carbonation. *Cement and*
31 *Concrete Research* 40:1582-1589. <https://doi.org/10.1016/j.cemconres.2010.06.010>
- 32 [33] Wu B, Ye G (2019) Study of carbonation rate of synthetic C-S-H by XRD, NMR and FTIR. *HERON*
33 64(1-2):21-38.
- 34 [34] Chen JJ, Thomas JJ, Jennings HM (2006) Decalcification shrinkage of cement paste. *Cement and*
35 *Concrete Research* 36:801-809. <https://doi.org/10.1016/j.cemconres.2005.11.003>
- 36 [35] Groves GW, Rodway DI, Richardson IG (1990) The carbonation of hardened cement pastes.
37 *Advances in Cement Research* 3(11):117-125. <https://doi.org/10.1680/adcr.1990.3.11.117>
- 38 [36] Swenson EG, Sereda PJ (1968) Mechanism of the carbonation shrinkage of lime and hydrated
39 cement. *Journal of Applied Chemistry* 18:111-117.

- 1 [37] Galan I, Andrade C, Mora P, Sanjuan MA (2010) Sequestration of CO₂ by concrete carbonation.
2 Environmental Science and Technology 44:3181-3186. <https://doi.org/10.1021/es903581d>
- 3 [38] Papadakis VG, Vayenas CG, Fardis MN (1991) Fundamental modeling and experimental
4 investigation of concrete carbonation. ACI Materials Journal 88:363-373
- 5
6 [39] Papadakis VG, Vayenas CG, Fardis MN (1991) Physical and chemical characteristics affecting the
7 durability of concrete. ACI Materials Journal 88:186-196
- 8
9 [40] Visser JHM (2012) Accelerated carbonation testing of mortar with supplementary cementing
10 materials: Limitation of the acceleration due to drying. Heron 57(3):231-246.
- 11
12 [41] von Greve-Dierfeld S (2015) Bemessungsregeln zur Sicherstellung der Dauerhaftigkeit von XC
13 exponierten Stahlbetonbauteilen (in German). Dissertation, Technical University Munich
- 14
15 [42] Sisomphon K, Franke L (2007) Carbonation rates of concretes containing high volume of
16 pozzolanic materials. Cement and Concrete Research 37(12):1647-1653.
17 <https://doi.org/10.1016/j.cemconres.2007.08.014>
- 18
19 [43] Hunkeler F, Greve-Dierfeld S (2019) Karbonatisierung von Beton und Korrosionsgeschwindigkeit
20 der Bewehrung im karbonatisierten Beton (Carbonation of concrete and reinforcement corrosion
21 rate in carbonated concrete). Research report published by the Swiss Federal Roads Office VSS No.
22 696.
- 23
24 [44] Leemann A, Moro F (2017) Carbonation of concrete: the role of CO₂ concentration, relative
25 humidity and CO₂ buffer capacity. Materials and Structures 50:30. DOI 10.1617/s11527-016-0917-2
- 26
27 [45] Johannesson B, Utgenannt P (2001) Microstructural changes caused by carbonation of cement
28 mortar. Cement and Concrete Research 31(6):925-931. [https://doi.org/10.1016/S0008-
29 8846\(01\)00498-7](https://doi.org/10.1016/S0008-8846(01)00498-7).
- 30
31 [46] Taylor HF (1997) Cement chemistry. Vol. 2 London: Thomas Telford.
- 32
33 [47] Lothenbach B, Scrivener K, Hooton RD (2011) Supplementary cementitious materials. Cement
34 and Concrete Research 41(12):1244-1256. <https://doi.org/10.1016/j.cemconres.2010.12.001>
- 35
36 [48] Juenger M, Snellings R, Bernal SA (2019) Supplementary cementitious materials: New sources,
37 characterization, and performance insights. Cement and Concrete Research 122:257-273.
38 <https://doi.org/10.1016/j.cemconres.2019.05.008>
- 39
40 [49] De Belie N, Soutos M, Gruyaert E. (2018) Properties of fresh and hardened concrete containing
41 supplementary cementitious materials, State-of-the-Art Report of the RILEM Technical Committee
42 238-SCM Working Group 4, Springer Nature, Switzerland
- 43
44 [50] Scrivener K, Lothenbach B, De Belie N, Gruyaert E, Skibsted J, Snellings R, Vollpracht A (2015) TC
45 238-SCM: hydration and microstructure of concrete with SCMs. Materials and Structures 48:835-862.
46 <https://doi.org/10.1617/s11527-015-0527-4>
- 47
48 [51] Villagrán-Zaccardi Y, Vollpracht A, Gruyaert E, De Belie N (2018) Recommendation of RILEM TC
49 238-SCM: determination of the degree of reaction of siliceous fly ash and slag in hydrated cement
50 paste by the selective dissolution method. Materials and Structures 51(27).
51 <https://doi.org/10.1617/s11527-017-1134-3>
- 52
53
54
55
56
57
58
59
60
61
62
63
64
65

- 1 [52] Gruyaert E, Van Den Heede P, De Belie N (2013) Carbonation of Slag Concrete: Effect of the
2 Cement Replacement Level and Curing on the Carbonation Coefficient - Effect of Carbonation on the
3 Pore Structure. *Cement and Concrete Composites* 35(1):39–48.
4 <https://doi.org/10.1016/j.cemconcomp.2012.08.024>
- 5 [53] Gruyaert E. (2010) Effect of blast furnace slag as cement replacement on hydration,
6 microstructure, strength and durability of concrete. Dissertation, Ghent University
- 7 [54] Herterich J (2017) Microstructure and Phase Assemblage of Low-Clinker Cements during Early
8 Stages of Carbonation. Dissertation, School of Civil Engineering at the University of Leeds
- 9 [55] Deschner F, Winnefeld F, Lothenbach B, Seufert S, Schwesig P, Dittrich S, Goetz-Neunhoeffler F,
10 Neubauer J (2012) Hydration of Portland cement with high replacement by siliceous fly ash. *Cement and
11 Concrete Research* 42(10):1389-1400. <https://doi.org/10.1016/j.cemconres.2012.06.009>
- 12 [56] Prentice D, Bernal S, Bankhead M, Hayes M, Provis J (2018) Phase evolution of slag-rich
13 cementitious grouts for immobilisation of nuclear wastes. *Advances in Cement Research* 30(8):345-
14 360. <https://doi.org/10.1680/jadcr.17.00198>
- 15 [57] Vollpracht A, Lothenbach B, Snellings R, Haufe J (2016) The pore solution of blended cements: a
16 review. *Materials and Structures* 46:3341-3367. <https://doi.org/10.1617/s11527-015-0724-1>
- 17 [58] Azad VJ, Suraneni P, Trejo D, Weiss WJ, Isgor B (2018) Thermodynamic investigation of allowable
18 admixed chloride limits in concrete. *ACI Materials Journal* 115(5): 727-738.
- 19 [59] Kunther W, Zhuo D, Skibsted J (2015) Thermodynamic modelling of Portland cement –
20 metakaolin – limestone blends. 1st international conference on calcined clays for sustainable
21 concrete doi.org/10.1007/978-94-017-9939-3
- 22 [60] Skocek J, Zajac M, Stabler C, Ben Haha M (2017) Predictive modelling of hydration and
23 mechanical performance of low Ca composite cements: Possibilities and limitations from industrial
24 perspective. *Cement and Concrete Research* 100:68-83.
25 <https://doi.org/10.1016/j.cemconres.2017.05.020>
- 26 [61] Lothenbach B, Rentsch D, Wieland E (2014) Hydration of a silica fume blended low-alkali
27 shotcrete cement. *Physics and Chemistry of the Earth, Parts A/B/C* 70-71:3-16.
28 <https://doi.org/10.1016/j.pce.2013.09.007>
- 29 [62] McPolin DO, Basheer PAM, Long AE (2009) Carbonation and pH in mortars manufactured with
30 supplementary cementitious materials. *Journal of Materials in Civil Engineering* 21(5):217-225
- 31 [63] Sadrilmomtazi A, Khoshkijari R, Tahmouresi B (2018) Effect of fly ash and silica fume on
32 transition zone, pore structure and permeability of concrete. *Magazine of Concrete Research*
33 70(10):519-532. <http://dx.doi.org/10.1680/jmacr.16.00537>
- 34 [64] De Weerd K, Ben Haha M, Saout G, Kjellsen KO, Justnes H, Lothenbach B (2011) Hydration
35 mechanism of ternary Portland cements containing limestone powder and fly ash. *Cement and
36 Concrete Research* 41(3):279-291. <https://doi.org/10.1016/j.cemconres.2010.11.014>
- 37 [65] De Weerd K, Ben Haha M, Le Saout G, Kjellsen KO, Justness H, Lothenbach B (2012) The effect
38 of temperature on the hydration of composite cements containing limestone powder and fly ash.
39 *Materials and Structures* 45:1101-1114. <https://doi.org/10.1617/s11527-011-9819-5>
- 40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

- 1 [66] Lothenbach B, Le Saout G, Galucci E, Scrivener K (2008) Influence of limestone on the hydration
2 of Portland cements. *Cement and Concrete Research* 38(6):848-860.
3 <https://doi.org/10.1016/j.cemconres.2008.01.002>
- 4 [67] Tennis PE, Thomas MDA., Weiss WJ (2011) State-of-the-Art Report on use of limestone in
5 cements at levels up to 15%. Report of the Portland Cement Association, Illinois USA.
- 6 [68] Snellings R, Mertens G, Elsen J (2012) Supplementary cementitious materials. Review in
7 *Mineralogy and Geochemistry* 74:211-278. <https://doi.org/10.2138/rmg.2012.74.6>
- 8 [69] Irbe L. (2019) The role of aluminium in C-A-S-H during chemical attack on concrete. Dissertation
9 TU München, Germany.
- 10 [70] Li J, Yu Q, Huang H, Yin S (2019) Effects of Ca/Si Ratio, Aluminum and Magnesium on the
11 Carbonation Behavior of Calcium Silicate Hydrate. *Materials* 12:1268. doi:10.3390/ma12081268
- 12 [71] Ortaboy S, Li J, Geng G, Myers R, Monteiro PJM, Maboudian R, Carraro C (2017) Effects of CO₂
13 and temperature on the structure and chemistry of C-(A-)S-H investigated by Raman spectroscopy.
14 *RSC Advances* 7:48925-48933. DOI: 10.1039/C7RA07266J
- 15 [72] Drouet E, Poyet S, Le Bescop P, Torrenti JM, Bourbon X (2019) Carbonation of hardened cement
16 pastes: Influence of temperature. *Cement and Concrete Research* 115:445-459.
17 <https://doi.org/10.1016/j.cemconres.2018.09.019>
- 18 [73] Thiery M, Faure P, Morandeau A, Platre G, Boutelou J, Dangl P, Baroghel-Bouney V (2011) Effect
19 of carbonation on the microstructure and moisture properties of cement-based materials. 12th
20 International Conference on Durability of Building Materials and Components, 12th-15th April 2011,
21 Porto Portugal
- 22 [74] Auroy M, Poyet S, Le Bescop P, Torrenti JM (2015) Impact of carbonation on unsaturated water
23 transport properties of cement-based materials. *Cement and Concrete Research* 74:44-58.
24 <https://doi.org/10.1016/j.cemconres.2015.04.002>
- 25 [75] Borges P, Costa J, Milestone N, Lynsdale C, Streatfield R (2010) Carbonation of CH and C-S-H in
26 Composite Cement Pastes Containing High Amounts of BFS. *Cement and Concrete Research*
27 40(2):284-292. <https://doi.org/10.1016/j.cemconres.2009.10.020>
- 28 [76] Van den Heede P, De Schepper M, De Belie N (2019) Accelerated and natural carbonation of
29 concrete with high volumes of fly ash: chemical, mineralogical and microstructural effects. *Royal*
30 *Society open Science* 6:181665. <https://doi.org/10.1098/rsos.181665>
- 31 [77] Branch JL, Epps R, Kosson DS (2018) The impact of carbonation on bulk and ITZ porosity in
32 microconcrete materials with fly ash replacement. *Cement and Concrete Research* 103:170-178.
33 <https://doi.org/10.1016/j.cemconres.2017.10.012>
- 34 [78] Leemann A., Loser R., Münch B., Lura P. (2017) Steady-state O₂ and CO₂ diffusion in carbonated
35 mortars produced with blended cements. *Materials and Structures* 50:247.
36 <https://doi.org/10.1617/s11527-017-1118-3>
- 37 [79] Parrott L (1996) Some effects of cement and curing upon carbonation and reinforcement
38 corrosion in concrete. *Materials and Structures* 29:164-173. <https://doi.org/10.1007/BF02486162>
- 39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

- 1 [80] Wierig H. (1985) Longtime studies on the carbonation on concrete under normal outdoor
2 exposure. RILEM Seminar on the Durability of Concrete Structures under normal outdoor exposure.
3 Materials and Structures 18:323. <https://doi.org/10.1007/BF02472928>
- 4 [81] Younsy A, Turcry P, Ait-Mokhtar A, Staquet S (2013) Accelerated carbonation of concrete with
5 high content of mineral additions: Effect of interactions between hydration and drying. Cement and
6 Concrete Research 43:25-33. <https://doi.org/10.1016/j.cemconres.2012.10.008>
- 7 [82] Morandeau A, Thiery M, Dangla P (2015) Impact of accelerated carbonation on OPC cement
8 paste blended with fly ash. Cement and Concrete Research 67:226-236.
9 <https://doi.org/10.1016/j.cemconres.2015.10.003>
- 10 [83] Saillio M, Bertin M, Baroghel-Bouny V (2019) Coupling effect and durability in cement pastes and
11 concretes with supplementary cementitious materials. International conference on sustainable
12 materials, system and structures (SMSS2019), 20-22 March 2019, Rovinj Croatia
- 13 [84] Hussain S, Bhunia D, Singh S (2017) Comparative study of accelerated carbonation of plain
14 cement and fly-ash concrete. Journal of Building Engineering 10:26–31.
15 <https://doi.org/10.1016/j.jobe.2017.02.001>
- 16 [85] Van den Heede P, De Belie N (2015) Durability Based Life Cycle Assessment of Concrete with
17 Supplementary Cementitious Materials Exposed. International Conference on Sustainable Structural
18 Concrete, La Plata Argentina, (1):13–24, LEMIT (Laboratorio de Entrenamiento Multidisciplinario para
19 la Investigación Tecnológica)
- 20 [86] Lu C, Wang W, Li Q, Hao M, Xu Y (2018) Effects of micro-environmental climate on the
21 carbonation depth and the pH value in fly ash. Journal of Cleaner Production 181:309-317.
22 <https://doi.org/10.1016/j.jclepro.2018.01.155>
- 23 [87] Burdon D. (2006) The durability of concrete containing high levels of fly ash. PCA R&D Serial No.
24 2989, Portland Cement Association, Skokie US
- 25 [88] Sideris K, Savva A (2001) Resistance of fly ash and natural pozzolans blended cement mortars
26 and concrete to carbonation, sulfate attack and chloride ion penetration. Seventh CANMET/ACI
27 international conference on fly ash, silica fume, slag and natural pozzolans in concrete, Mandras
28 India
- 29 [89] Papadakis V. (1999) Effect of fly ash on Portland cement systems: Part I. Low-calcium fly ash.
30 Cement and Concrete Research 29(11): 1727-1736. [https://doi.org/10.1016/S0008-8846\(99\)00153-2](https://doi.org/10.1016/S0008-8846(99)00153-2)
- 31 [90] Papadakis V. (2000) Effect of fly ash on Portland cement systems. Part II: High calcium fly ash.
32 Cement and Concrete Research 30(10):1647-1654. [https://doi.org/10.1016/S0008-8846\(00\)00388-4](https://doi.org/10.1016/S0008-8846(00)00388-4)
- 33 [91] Thomas M, Matthews J (1992) Carbonation of fly ash concrete. Magazine of Concrete Research
34 44(160):217-228. <https://doi.org/10.1680/macr.1992.44.160.217>
- 35 [92] Wu B, Ye G (2019) X-ray diffraction study of carbonation rate of C-S-H with different Ca/Si ratio.
36 International conference on sustainable materials, system and structures (SMSS2019), 20-22 March
37 2019, Rovinj Croatia
- 38 [93] Newlands M. (2001) Development of a simulated natural carbonation test of selected CEM II
39 concretes. Dissertation, University Dundee

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65
- [94] Thienel KC, Beuntner N (2012) Effects of calcined clay as low carbon cementing materials on the properties of concrete. *Concrete in the Low Carbon Era*, 9.-11. July, Dundee UK
- [95] Shao Y, Rostami V, He Z, Boyd A (2014) Accelerated carbonation of Portland limestone cement. *Journal of Materials in Civil Engineering* 26(1):117-124. [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0000773](https://doi.org/10.1061/(ASCE)MT.1943-5533.0000773)
- [96] Leemann A, Nygaard P, Kaufmann J, Loser R (2015) Relation between carbonation resistance, mix design and exposure of mortar and concrete. *Cement and Concrete Composites* 62:33-43. <https://doi.org/10.1016/j.cemconcomp.2015.04.020>
- [97] von Greve-Dierfeld S, Gehlen C (2016) Performance-based durability design, carbonation, part 2 – classification of concrete. *Structural Concrete* 17:523-532. <https://doi.org/10.1002/suco.201600067>
- [98] Ribeiro A, Santos T, Goncalves A (2018) Performance of concrete exposed to natural carbonation: Use of the k-value concept. *Construction and Building Materials* 175:360-370. <https://doi.org/10.1016/j.conbuildmat.2018.04.206>
- [99] Nobis C, Vollpracht A (2015) k-Value for Carbonation of Concretes with Supplementary Cementitious Materials. 27th Biennial National Conference of the Concrete Institute of Australia in Conjunction with the 69th RILEM Week - Concrete 2015, 30 Aug. - 2 Sept. 2015, Melbourne Australia
- [100] Shi Z. (2016) Durability of Portland Cement - Calcined Clay - Limestone Blends. Dissertation. Aarhus University Denmark
- [101] Jansson H, Snibb R, Bohlin K, Löfgren I (2017) Carbonation of concrete with mineral additions. XXIII Nordic Concrete Research Symposium, Aalborg Denmark
- [102] Müller, C. (2019) Konzepte zur Herstellung von ressourceneffizienten Betonen am Beispiel Zement (Concepts for the production of resource efficient concretes with the example cement). *Beton* 69(9):311-314.
- [103] Imamoto K, Neves R, Torrent R (2016) Carbonation rate in old structures assessed with air-permeability site NDT. IABMAS 2016 Paper 426, Foz do Iguacu, Brazil, 26-30 June 2016.
- [104] Russel D, Basheer PAM, Rankin IB, Long AE (2001) Effect of relative humidity and air permeability on prediction of the rate of carbonation of concrete. *Structures & Buildings* 146(3):319–526.
- [105] Jung SH, Lee MK, Oh BH (2011) Measurement device and characteristics of diffusion coefficient of carbon dioxide in concrete. *ACI Materials Journal* 108(6):589– 595.
- [106] Pham S, Prince W (2014) Effects of carbonation on the microstructure of cement materials: Influence of measuring methods and types of cement. *International Journal of Concrete Structures and Materials* 8:327-333. <https://doi.org/10.1007/s40069-014-0079-y>
- [107] Cortvriendt M, Gruyaert E, Vanoutrive H (2019) Comparison between the carbonation of cement paste, mortar and concrete with supplementary cementitious materials. Master Thesis KU Leuven
- [108] Schwartzenruber A, Catherine C (2000) Method of the concrete equivalent mortar (CEM) – A new tool to design concrete containing admixture (in French). *Materials and Structures* 33(232):475–482. <https://doi.org/10.1007/BF02480524>

- 1 [109] Akcay B (2017) Aggregate Restraining Effect on Autogenous Shrinkage of Cementitious
2 Materials` KSCE Journal of Civil Engineering 22(6):3102-3111. DOI: 10.1007/s12205-017-0635-5
- 3 [110] Guo H, Shi C, Guan X, Zhu J, Ding Y, Ling TC, Zhang H, Wang Y (2018) Durability of recycled
4 aggregate concrete – A review. Cement and Concrete Composites 89:251-259.
5 <https://doi.org/10.1016/j.cemconcomp.2018.03.008>
- 6 [111] Silva RV, Neves R, de Brito J, Dhir RK (2015) Carbonation behaviour of recycled aggregate
7 concrete. Cement and Concrete Composites 62:22-32.
8 <https://doi.org/10.1016/j.cemconcomp.2015.04.017>
- 9 [112] Singh N, Singh SP (2016) Carbonation and electrical resistance of self-compacting concrete
10 made with recycled concrete aggregates and metakaolin. Construction and Building Materials
11 121:400-409. <https://doi.org/10.1016/j.conbuildmat.2016.06.009>
- 12 [113] de Brito J, Ferreira J, Pacheco J, Soares D, Guerreiro M (2016) Structural, material, mechanical
13 and durability properties and behaviour of recycled aggregates concrete. Journal of Building
14 Engineering 6:1-16. <https://doi.org/10.1016/j.job.2016.02.003>
- 15 [114] Kou SC, Poon CS (2012) Enhancing the durability properties of concrete prepared with coarse
16 recycled aggregate. Construction and Building Materials 35:69-76.
17 <https://doi.org/10.1016/j.conbuildmat.2012.02.032>
- 18 [115] Buyle-Bodin F, Hadjieva-Zaharieva R (2002) Influence of industrially produced recycled
19 aggregates on flow properties of concrete. Materials and Structures 35:504-509.
20 <https://doi.org/10.1007/BF02483138>
- 21 [116] Amorim P, de Brito J, Evangelista L (2012) Concrete Made with Coarse Concrete Aggregate:
22 Influence of Curing on Durability. ACI Materials Journal 109:195-204
- 23 [117] Jiménez LF, Moreno EI (2015) Durability indicators in high absorption recycled aggregate
24 concrete. Advances in Materials Science and Engineering ID505423:8.
25 <http://dx.doi.org/10.1155/2015/505423>
- 26 [118] Limbachiya M, Meddah MS, Ouchagour Y (2012) Performance of Portland/Silica Fume Cement
27 Concrete Produced with Recycled Concrete Aggregate. ACI Materials Journal 109:91-100.
- 28 [119] Xiao J, Lei B, Zhang C (2012) On carbonation behavior of recycled aggregate concrete. Science
29 China Technological Sciences 55:2609-2616. <https://doi:10.1007/s11431-012-4798-5>
- 30 [120] Pedro D, de Brito J, Evangelista L (2015) Performance of concrete made with aggregates
31 recycled from precasting industry waste: influence of the crushing process. Materials and Structures
32 48: 3965-3978. <https://doi:10.1617/s11527-014-0456-7>
- 33 [121] Otsuki N, Miyazato S, Yodsudjai W (2003) Influence of recycled aggregate on interfacial
34 transition zone, strength, chloride penetration and carbonation of concrete. Journal of Materials in
35 Civil Engineering 15(5):443-451. [https://doi.org/10.1061/\(ASCE\)0899-1561\(2003\)15:5\(443\)](https://doi.org/10.1061/(ASCE)0899-1561(2003)15:5(443))
- 36 [122] Zhang K, Xiao J (2018) Prediction model of carbonation depth for recycled aggregate concrete.
37 Cement and Concrete Composites 88:86-99. <https://doi.org/10.1016/j.cemconcomp.2018.01.013>
- 38 [123] Kisku N, Joshi H, Ansari M, Panda SK, Nayak S, Dutta SC (2017) A critical review and assessment
39 for usage of recycled aggregate as sustainable construction material. Construction and Building
40 Materials 131:721-740. <https://doi.org/10.1016/j.conbuildmat.2016.11.029>

- 1 [124] Xiao J, Lu D, Ying J (2013) Durability of Recycled Aggregate Concrete: An Overview. *Journal of*
2 *Advanced Concrete Technology* 11:347-359. Doi:10.315/jact.11.347
- 3 [125] Levy SM, Helene P (2004) Durability of recycled aggregates concrete: a safe way to sustainable
4 development. *Cement and Concrete Research* 34: 1975-1980.
5 <https://doi.org/10.1016/j.cemconres.2004.02.009>
- 6 [126] Medina C, Frías M, Sánchez de Rojas MI, Thomas C, Polanco JA (2012) Gas permeability in
7 concrete containing recycled ceramic sanitary ware aggregate. *Construction and Building Materials*
8 37:597-605. <https://doi.org/10.1016/j.conbuildmat.2012.08.023>
- 9 [127] Evangelista L, de Brito J (2010) Durability performance of concrete made with fine recycled
10 concrete aggregates. *Cement and Concrete Composites* 32:9-14.
11 <https://doi.org/10.1016/j.cemconcomp.2009.09.005>
- 12 [128] Zega CJ, Di Maio AA (2011) Use of recycled fine aggregate in concretes with durable
13 requirements. *Waste Manage.* 31:2336-2340. <https://doi.org/10.1016/j.wasman.2011.06.011>
- 14 [129] Geng J, Sun J (2013) Characteristics of the carbonation resistance of recycled fine aggregate
15 concrete, *Construction and Building Materials* 49:814-820.
16 <https://doi.org/10.1016/j.conbuildmat.2013.08.090>
- 17 [130] Vieira T, Alves A, de Brito J, Correia JR, Silva RV (2016) Durability-related performance of
18 concrete containing fine recycled aggregates from crushed bricks and sanitary ware. *Materials and*
19 *Design* 90:767-776. <https://doi.org/10.1016/j.matdes.2015.11.023>
- 20 [131] Sveindottir EL, Maage M, Poot S, Hansen EA, Bennenk HW, Helland S, Norden G, Kwint E,
21 Milencovic A, Smeplass S, Tarquis F, Holand I, Price B., van Breugel K, Thienel KC (1998) LWAC
22 Material Properties - State-of-the-Art. The European Union – Brite EuRam III, Gouda Netherlands
- 23 [132] Hossain KMA, Ahmed S, Lachemi M (2011) Lightweight concrete incorporating pumice based
24 blended cement and aggregate: Mechanical and durability characteristics. *Construction and Building*
25 *Materials* 25: 1186-1195. <https://doi.org/10.1016/j.conbuildmat.2010.09.036>
- 26 [133] Vaysburd A (1992) Durability of Lightweight Concrete and its Connections with the Composition
27 of Concrete, Design, and Construction Methods. *ACI Special Publication* 136:295-318
- 28 [134] Holm TA, Bremner TW, Vaysburd A (1988) Carbonation of Marine Structural Lightweight
29 Concretes. *ACI Special Publication* 109:667-676
- 30 [135] Thienel KC, Schmidt-Döhl F, Feldrappe V (2000) In-Situ Tests on Existing LWAC Structures.
31 Second International Conference on Structural Lightweight Aggregate Concrete, Kristiansand Norway
- 32 [136] Swamy RN, Jiang ED (1992) Pore Structure and Carbonation of Lightweight Concrete after 10
33 Years Exposure. *Materials Science*. DOI:10.14359/4012
- 34 [137] Expanded Shale, Clay & Slate Institute (2006). Internal Curing. Using Expanded Shale, Clay and
35 Slate Lightweight Aggregate. Publication n° 4362 ([https://www.escsi.org/internal-curing/technical-](https://www.escsi.org/internal-curing/technical-docs/)
36 [docs/](https://www.escsi.org/internal-curing/technical-docs/) - Accessed date: 2019-06-03)
- 37 [138] Sanjuan A, Andrade C, Cheyrezy M (2003) Concrete carbonation tests in natural and in
38 accelerated conditions. *Advances in Cement Research* 15(4):171-180.
39 <https://doi.org/10.1680/adcr.2003.15.4.171>
- 40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

- 1 [139] Fattuhi NI (1988) Concrete Carbonation as Influenced by Curing Regime. *Cement and Concrete*
2 *Research* 18(3):426–30. [https://doi.org/10.1016/0008-8846\(88\)90076-2](https://doi.org/10.1016/0008-8846(88)90076-2)
- 3 [140] Sanjuán MÁ, Estévez E, Argiz C, del Barrio D (2018) Effect of Curing Time on Granulated Blast-
4 Furnace Slag Cement Mortars Carbonation. *Cement and Concrete Composites* 90(2):257–65.
5 <https://doi.org/10.1016/j.cemconcomp.2018.04.006>
- 6 [141] Bier T (1986) Influence of Type of Cement and Curing on Carbonation Progress and Pore
7 Structure of Hydrated Cement Pastes. *Symposium M – Microstructural Development During*
8 *Hydration of Cement* 85:123. <https://doi.org/10.1557/PROC-85-123>
- 9 [142] Ekolu SO (2016) A Review on Effects of Curing, Sheltering, and CO₂ Concentration upon Natural
10 Carbonation of Concrete. *Construction and Building Materials* 127: 306–20.
11 <https://doi.org/10.1016/j.conbuildmat.2016.09.056>
- 12 [143] Sideris KK, Zarras SC (2006) Influence of curing time on the durability of concrete against
13 carbonation induced corrosion. 16th Hellenic Concrete Conference, October 25-27, Alexandroupolis
14 Greece.
- 15 [144] Saillio M (2012) Interactions physico-chimiques ions-matrice dans les bétons sains ou
16 carbonatés: influence sur le transport ionique. Dissertation (in French), University Paris-Est
- 17 [145] Bucher R, Diederich P, Escadeilla G, Cyr M (2017) Service life of metakaolin-based concrete
18 exposed to carbonation - Comparison with blended cement containing fly ash, blast furnace slag and
19 limestone filler. *Cement and Concrete Research* 99:18–29.
20 <https://doi.org/10.1016/j.cemconres.2017.04.013>
- 21 [146] Atis CD (2003) Accelerated carbonation and testing of concrete made with fly ash. *Construction*
22 *and Building Materials* 17:147–152. [https://doi.org/10.1016/S0950-0618\(02\)00116-2](https://doi.org/10.1016/S0950-0618(02)00116-2)
- 23 [147] Thomas M (2004) The effect of curing and concrete quality on the durability of concretes with
24 high-volumes of supplementary cementing materials. University of New Brunswick Fredericton,
25 Canada
- 26 [148] Li G, Yao F, Li P, Yan C (2016) Long-term carbonation resistance of concrete under initial high-
27 temperature curing. *Materials and Structures* 49(7):2799–2806. [https://doi.org/10.1617/s11527-015-](https://doi.org/10.1617/s11527-015-0686-3)
28 [0686-3](https://doi.org/10.1617/s11527-015-0686-3).
- 29 [149] Schiessl P, Gehlen C et. al. (2006) *fib Bulletin 34: Model Code for service life design*. ISBN: 2-
30 88394-074-6
- 31 [150] Hainer S, Prosk T, Graubner C (2015) Effect of curing on the carbonation of concrete (Einfluss
32 der Nachbehandlung auf das Karbonatisierungsverhalten von Beton aus klinkerarmen Zementen, in
33 German). *Beton- und Stahlbetonbau* 110:1. <https://doi.org/10.1002/best.201400042>
- 34 [151] Hunkeler F, Lammer A (2012) Requirements for the carbonation resistance of concrete (in
35 German). *AGB2008/012*, Federal Roads Office FEDRO, Switzerland
- 36 [152] Von Greve-Dierfeld S, Gehlen C (2016) Performance-based durability design, carbonation, part
37 1 – benchmarking of deemed-to-satisfy rules. *Structural Concrete* 17:309-328.
38 <https://doi.org/10.1002/suco.201600066>
- 39 [153] Verbeck G (1958) Carbonation of hydrated Portland cement. *ASTM Special Technical*
40 *Publication* 205:17–36. <https://doi.org/10.1520/STP39460S>
- 41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

- 1 [154] Thiery M (2005) Modélisation de la carbonatation atmosphérique des matériaux cimentaires
2 (in French). Dissertation, Ecole Nationale des Ponts et Chaussées (ENPC) Paris
- 3 [155] Galan I, Andrade C, Castellote M (2013) Natural and accelerated CO₂ binding kinetics in cement
4 paste at different relative humidities. Cement and Concrete Research 49:21–28.
5 <https://doi.org/10.1016/j.cemconres.2013.03.009>
- 6 [156] Essai pour béton durci - Essai de carbonatation accélérée - Mesure de l'épaisseur de béton
7 carbonaté. XP P 18-458, French standard, AFNOR 2008.
- 8 [157] Testing hardened concrete - Part 12: Determination of the potential carbonation resistance of
9 concrete: Accelerated carbonation method. EN 12390-12:2020
- 10 [158] Diamond S (1971) A critical comparison of mercury porosimetry and capillary condensation
11 pore size distributions of portland cement pastes. Cement and Concrete Research 1:531–545.
12 [https://doi.org/10.1016/0008-8846\(71\)90058-5](https://doi.org/10.1016/0008-8846(71)90058-5)
- 13 [159] Baroghel-Bouny V (2007) Water vapour sorption experiments on hardened cementitious
14 materials part I: essential tool for analysis of hygral behaviour and its relation to pore structure.
15 Cement and Concrete Research 37:414–437. <https://doi.org/10.1016/j.cemconres.2006.11.019>
- 16 [160] De Ceukelaire L, Van Nieuwenburg D (1993) Accelerated carbonation of a blast-furnace cement
17 concrete. Cement and Concrete Research 23(2):442–52. [https://doi.org/10.1016/0008-8846\(93\)90109-M](https://doi.org/10.1016/0008-8846(93)90109-M)
- 18 [161] Saetta AV, Vitaliani RV (2004) Experimental investigation and numerical modeling of
19 carbonation process in reinforced concrete structures: Part I: theoretical formulation. Cement and
20 Concrete Research 34:571–579. <https://doi.org/10.1016/j.cemconres.2003.09.009>
- 21 [162] Glasser FP, Pedesen J, Goldthorpe K, Atkins M (2005) Solubility reactions of cement
22 components with NaCl solutions: Ca(OH)₂ and CSH. Advances in Cement Research 17(2):57-64.
23 <https://doi.org/10.1680/adcr.2005.17.2.57>
- 24 [163] Chaussadent T (1999) Etats des lieux et réflexions sur la carbonatation du béton armé.
25 Laboratoire Central des Ponts et Chausees (LCPC)
- 26 [164] He R (2010) A Study on Carbonation for Low Calcium Fly Ash Concrete under Different
27 Temperature and Relative Humidity. EJGE 15(Q):1871-1877.
- 28 [165] Tai CY, Chen FB (1998) Polymorphism of CaCO₃, precipitated in a constant-composition
29 environment. AIChE Journal 44:1790–1798. <https://doi.org/10.1002/aic.690440810>
- 30 [166] Gehlen, C (2000) Probabilistische Lebensdauerbemessung von Stahlbetonbauwerken:
31 Zuverlässigkeitsbetrachtungen zur wirksamen Vermeidung von Bewehrungskorrosion (in German).
32 Dissertation, RWTH Aachen
- 33 [167] Uomoto T, Takada Y (1993) Factors affecting concrete carbonation ratio. Doboku Gakkai
34 Ronbunshu 1992(451):119-128. https://doi.org/10.2208/jscej.1992.451_119
- 35 [168] Thiel C (2019) Einfluss von CO₂-Druck auf das Porengefüge zementgebundener Werkstoffe
36 während der Carbonatisierung. Dissertation, Technische Universität München
- 37 [169] Van den Heede P, De Belie N (2019) Difference in carbonation behavior at 0.04%, 1% and 10%
38 CO₂ for high-volume fly ash mortar: effect on internal humidity, and resistivity. International

1 Conference on Sustainable Materials, Systems and Structures (SMSS2019), March 18-22, Rovinj,
2 Croatia, vol. 3, pp. 317-324

3 [170] Thierry M, Villain G, Dangla P, Platret G (2007) Investigation of the carbonation front shape on
4 cementitious materials: Effects of the chemical kinetics. *Cement and Concrete Research* 37(7):1047-
5 1058. <https://doi.org/10.1016/j.cemconres.2007.04.002>

6 [171] Bernal SA, Provis JL, Brice DG, Kilcullen A, Duxson P, van Deventer JSJ (2012) Accelerated
7 carbonation testing of alkali-activated binders significantly underestimate the real service life: the
8 role of the pore solution. *Cement and Concrete Research* 42:1317-1326

9 [172] Thiel C, Schön A, Gehlen C (2018) Einfluss der CO₂-Permeation auf die Carbonatisierung
10 zementgebundener Baustoffe. 20. Internationale Baustofftagung (ibausil), 12.-14. September 2018,
11 Weimar Germany

12 [173] Knöfel D, Eßer G (1993) Einfluss unterschiedlicher Kohlendioxidkonzentrationen auf
13 Zementmörtel (in German). *Werkstoffwissenschaften und Bausanierung*, Wittmann F H, Bartz W J
14 (eds), Tagungsbericht des 3. Int. Koll. 1408-1418.

15 [174] Da Silva FG, Helene P, Castro-Borges P, Liborio J (2009) Sources of variations when comparing
16 concrete carbonation results. *Journal of Materials in Civil Engineering* 21(7):333.
17 [https://doi.org/10.1061/\(ASCE\)0899-1561\(2009\)21:7\(333\)](https://doi.org/10.1061/(ASCE)0899-1561(2009)21:7(333))

18 [175] Rozière E, Loukili A, Cussigh F (2009) A performance based approach for durability of concrete
19 exposed to carbonation. *Construction and Building Materials* 23(1):190-199.
20 <https://doi.org/10.1016/j.conbuildmat.2008.01.006>

21 [176] Durán-Herrera A, Mendoza-Rangel J, De-Los-Santos E, Vazquez P, Bentz D (2013) Accelerated
22 and Natural Carbonation of Concretes with Internal Curing and Shrinkage/Viscosity Modifiers.
23 *Materials and Structures* 48:1207-1214. <https://doi.org/10.1617/s11527-013-0226-y>

24 [177] Harrison TA, Jones MR, Newlands MD, Kandasami S, Khanna G (2012) Experience of using the
25 prTS 12390-12 accelerated carbonation test to assess the relative performance of concrete.
26 *Magazine of Concrete Research* 64(8):737-747. <https://doi.org/10.1680/macr.11.00162>

27 [178] Dunster AM (2000) *Accelerated Carbonation Testing of Concrete*. Ihs Bre Press, Bracknell UK.
28 ISBN13 9781860814549

29 [179] Neves R, Branco F, de Brito J (2013) Field assessment of the relationship between natural and
30 accelerated concrete carbonation resistance. *Cement and Concrete Composites* 41:9–15.
31 <https://doi.org/10.1016/j.cemconcomp.2013.04.006>

32 [180] Anstice DJ, Page CL, Page MM (2005) The pore solution phase of carbonated cement pastes.
33 *Cement and Concrete Research* 35:377-383. <https://doi.org/10.1016/j.cemconres.2004.06.041>

34 [181] Ngala VT, Page CL (1997) Effects of carbonation on pore structure and diffusional properties of
35 hydrated cement pastes. *Cement and Concrete Research* 27(7):995–1007.
36 [https://doi.org/10.1016/S0008-8846\(97\)00102-6](https://doi.org/10.1016/S0008-8846(97)00102-6)

37 [182] Boumaaza M, Turcry P, Huet B, Ait-Mokhtar A (2020) Influence of carbonation on the
38 microstructure and the gas diffusivity of hardened cement pastes. *Construction and Building*
39 *Materials* 253:119227. <https://doi.org/https://doi.org/10.1016/j.conbuildmat.2020.119227>

- 1 [183] Justness H, Skocek J, Øsnor TA, Engelsen CJ, Skjølsvold O (2020) Microstructural changes of
2 hydrated cement blended with fly ash upon carbonation. Cement and Concrete Research
3 137:106192. <https://doi.org/10.1016/j.cemconres.2020.106192>
- 4 [184] Berodier E, Scrivener K (2015) Evolution of pore structure in blended systems. Cement and
5 Concrete Research 73:25–35. <https://doi.org/10.1016/j.cemconres.2015.02.025>
- 6 [185] Kulakowski M, Pereira F, Dal Molin D (2009) Carbonation-induced reinforcement corrosion in
7 silica fume concrete. Construction and Building Materials 23(3):1189–1195.
8 <https://doi.org/10.1016/j.conbuildmat.2008.08.005>
- 9 [186] Moreira AC, Appoloni CR, Rocha WRD, Oliveira LF, Fernandes CP, Lopes RT (2010)
10 Determination of the porosity and pore size distribution of SiC ceramic foams by nuclear
11 methodologies. Advances in Applied Ceramics 109(7): 416-420. DOI
12 10.1179/174367510X12722693956158
- 13 [187] Houst Y, Wittmann F (1994) Influence of porosity and water content on the diffusivity of CO₂
14 and O₂ through hydrated cement paste. Cement and Concrete Research 24(6):1165-1176.
15 [https://doi.org/10.1016/0008-8846\(94\)90040-X](https://doi.org/10.1016/0008-8846(94)90040-X)
- 16 [188] Hyvert N (2009) Application de l'approche probabiliste à la durabilité des produits préfabriqués
17 en béton (in French). Dissertation, University of Toulouse
- 18 [189] Dutzer V, Dridi W, Poyet S, Le Bescop P, Bourbon X (2019) The link between gas diffusion and
19 carbonation in hardened cement pastes. Cement and Concrete Research 123(9):105795.
20 <https://doi.org/10.1016/j.cemconres.2019.105795>
- 21 [190] Soja W, Maraghechi H, Georget F, Scrivener K (2018) Changes of microstructure and diffusivity
22 in blended cement pastes to natural carbonation. 5th International Conference on Concrete Repair,
23 Rehabilitation, and Retrofitting (ICRRR 2018), Cape Town, South Africa.
- 24 [191] Boumaaza M, Huet B, Pham G, Ait-Mokhtar A, Gehlen C (2018) A new test method to
25 determine the gaseous oxygen diffusion coefficient of cement pastes as a function of hydration
26 duration, microstructure and relative humidity. Materials and Structures 51:51.
27 <https://doi.org/10.1617/s11527-018-1178-z>
- 28 [192] Zeebe R (2011) On the molecular diffusion of dissolved CO₂, HCO₃⁻ and CO₃²⁻ and their
29 dependence on isotopic mass. Geochimica et Cosmochimica Acta 75:2483-2498.
30 <https://doi.org/10.1016/j.gca.2011.02.010>
- 31 [193] Olsson N, Nilsson L O, Ahs M, Baroghel-Bouney V (2018) Moisture transport and sorption in
32 cement based materials containing slag or silica fume. Cement and Concrete Research 106:23-32.
33 <https://doi.org/10.1016/j.cemconres.2018.01.018>
- 34 [194] Secombe J, Vidal R, Galle C, Adenot F (2006) Experimental study of gas diffusion in cement
35 paste. Cement and Concrete Research 37(4):579-588. 10.1016/j.cemconres.2006.12.003.cea-
36 02360113
- 37 [195] Zou D, Liu T, Du C, Teng J (2015) Influence of Wind Pressure on the Carbonation of Concrete.
38 Materials 8:4652-4667. doi:10.3390/ma8084652
- 39 [196] Villain G, Thiery M (2005) Impact of carbonation on microstructure and transport properties of
40 concrete. 10th International conference on durability of building materials and components, 17-20
41 April 2005, Lyon France

- 1 [197] Dinku A, Reinhardt HW (1997) Gas permeability coefficient of cover concrete as a performance
2 control. *Materials and Structures* 30:387-393. <https://doi.org/10.1007/BF02498560>
- 3 [198] Amsler D, Bur M (2018) Einfluss der Kapillaren Wasseraufnahme auf die Karbonatisierung von
4 Beton. CAS Arbeit der Fachhochschule Nordwestschweiz, Switzerland
- 5
6 [199] Pham S, Prince W (2013) Effects of carbonation on the microstructure and macro physical
7 properties of cement mortars. *World Academy of Science and Technology International Journal of*
8 *Civil and environmental Engineering* 7(6):434-437.
- 9
10 [200] Juhart J, Bregar R, David G, Krüger M (2019) Air permeability, water penetration and water
11 absorption to specify durability of eco-efficient concrete. *RILEM Technical Letters* 4:67-73. DOI:
12 <http://dx.doi.org/10.21809/rilemtechlett.2019.86>
- 13
14 [201] Claisse P, Elsayad H, Shaaban I (1999) Permeability and pore volume of carbonated concrete.
15 *Materials Journal* 96(3):378-381
- 16
17 [202] Tracz T, Zdeb T (2019) Effect of hydration and carbonation progress on the porosity and
18 permeability of cement pastes. *Materials* 192 (12). Doi:10.3390/ma12010192.
- 19
20 [203] Claisse PA, Elsayad HI, Ganjian E (2009) Water vapour and liquid permeability measurements in
21 cementitious samples. *Advances in Cement Research* 21(2):83-89. DOI: 10.1680/adcr.8.00046
- 22
23 [204] Dias WPS (2000) Reduction of concrete sorptivity with age through carbonation. *Cement and*
24 *Concrete Research* 30(8):1255-1261. DOI: 10.1016/S0008-8846(00)00311-2
- 25
26 [205] Zhang SP, Zong I (2014) Evaluation of relationship between water absorption and durability of
27 concrete materials. *Advances in Materials Science and Engineering* 2014.
28 <https://dx.doi.org/10.1155/2014/650373>
- 29
30 [206] Zhang Z, Thierry M, Baroghel-Bouny V (2016) Investigation of moisture transport properties of
31 cementitious materials. *Cement and Concrete Research* DOI: 10.1016/j.cemconres.2016.08.013
- 32
33 [207] Alderete N, Villagran Zaccardi Y, Snoeck D, Van Belleghem B, Van den Heede P, Van Tittelboom
34 K, De Belie N (2019) Capillary imbibition in mortars with natural pozzolan, limestone powder and slag
35 evaluated through neutron radiography, electrical conductivity, and gravimetric analysis. *Cement and*
36 *Concrete Research* 118:57-68. <https://doi.org/10.1016/j.cemconres.2019.02.011>
- 37
38 [208] Edvardsen C (1999) Water permeability and autogenous healing of cracks in concrete. *ACI*
39 *Materials Journal* 96(4):448–54
- 40
41 [209] Hall C (2019) Capillary imbibition in cement-based materials with time-dependent
42 permeability. *Cement and Concrete Research* 124:105835.
43 <https://doi.org/10.1016/j.cemconres.2019.105835>
- 44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65